

PetroLOGIC Solutions, Inc.

3997 Oak Hill Road
Douglasville, GA 30135
Tel: (678) 313-4146
email: rlkath@comcast.net




ATTACHMENT 1

PHOTOMICROGRAPHS OF SELECT THIN SECTIONS

Lakeland Electric

PHOTO 1


CCR2A 23.0-23.5

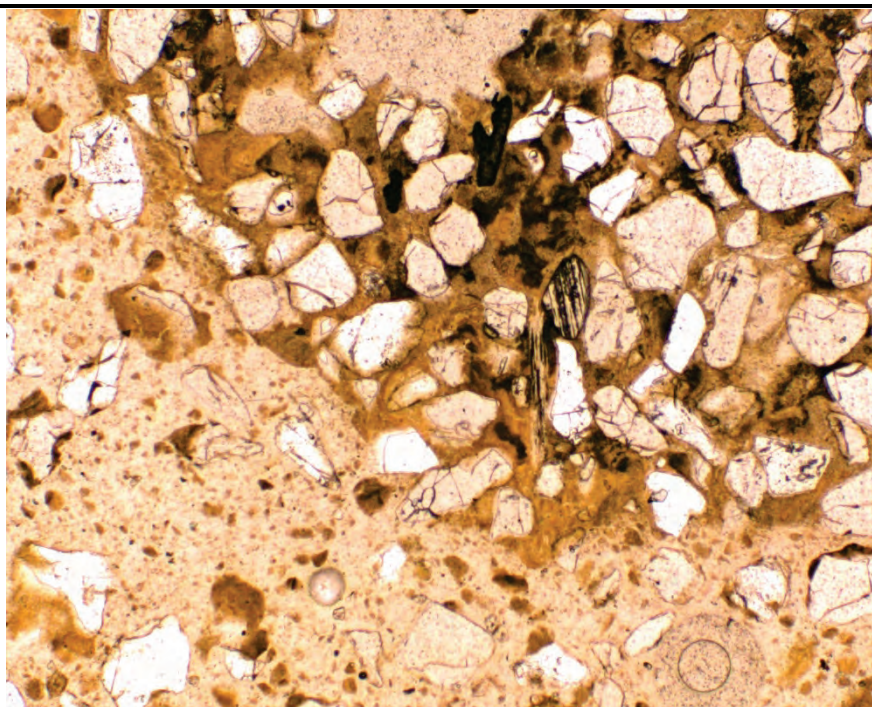

Subangular to subrounded quartz grains in a kaolinite and wavellite matrix (brown). Striated high-relief mineral is kyanite. Minor rutile. Plane light.

PHOTO 2

CCR2A 23.0-23.5

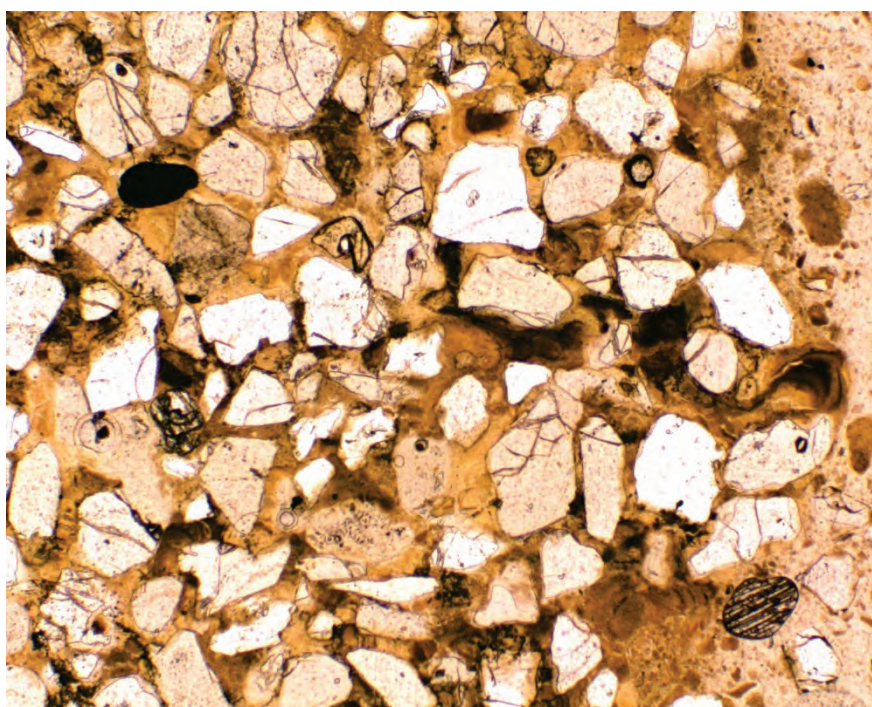


Subangular to subrounded quartz grains in a kaolinite and wavellite matrix (brown). Striated high-relief mineral is kyanite; rounded opaque grain is ilmenite; pleochroic yellow minerals are staurolite. Plane light.

Unless otherwise indicated, all images were taken at 5x magnification; the long-edge of the field of view in the photographs is approximately 2.5 mm in length.

Lakeland Electric

PHOTO 3


CCR2A 23.0-23.5

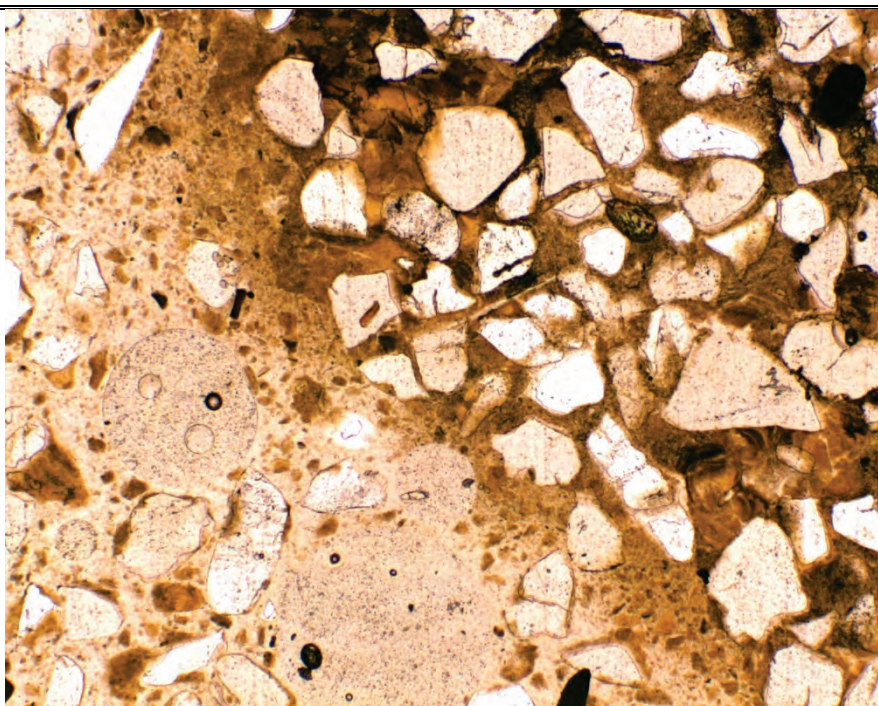

Subangular to subrounded quartz grains in a kaolinite and wavellite matrix (brown). Greenish mineral is zircon; elongate mineral is muscovite. Plane light.

PHOTO 4

CCR2A 23.0-23.5

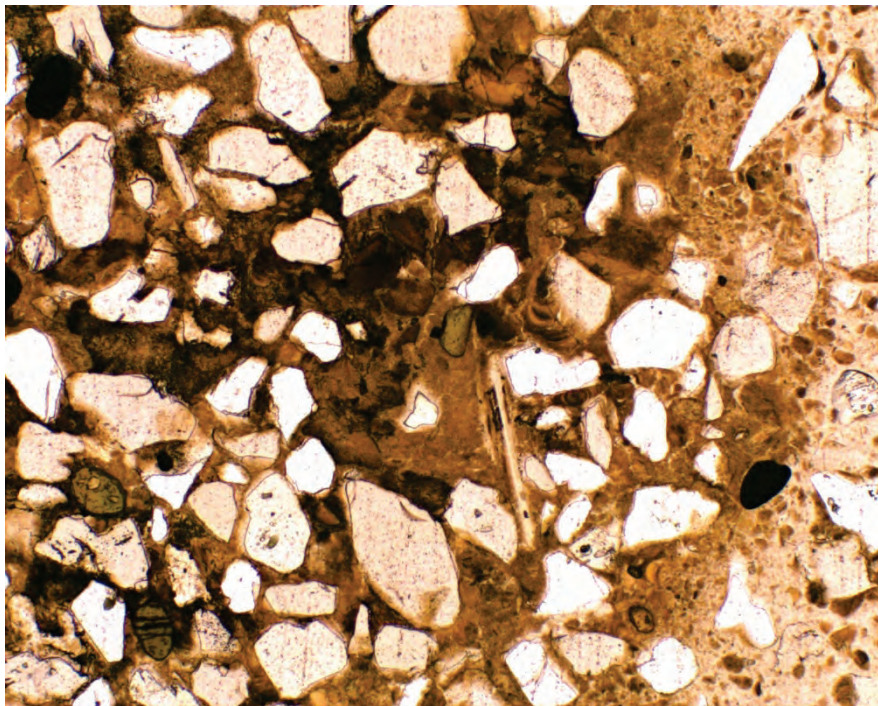


Subangular to subrounded quartz grains in a kaolinite and wavellite matrix (brown). Greenish minerals are zircon; elongate mineral is muscovite; rounded opaque mineral is ilmenite. Plane light.

Unless otherwise indicated, all images were taken at 5x magnification; the long-edge of the field of view in the photographs is approximately 2.5 mm in length.

Lakeland Electric

PHOTO 1


CCR4A 26.1-26.4

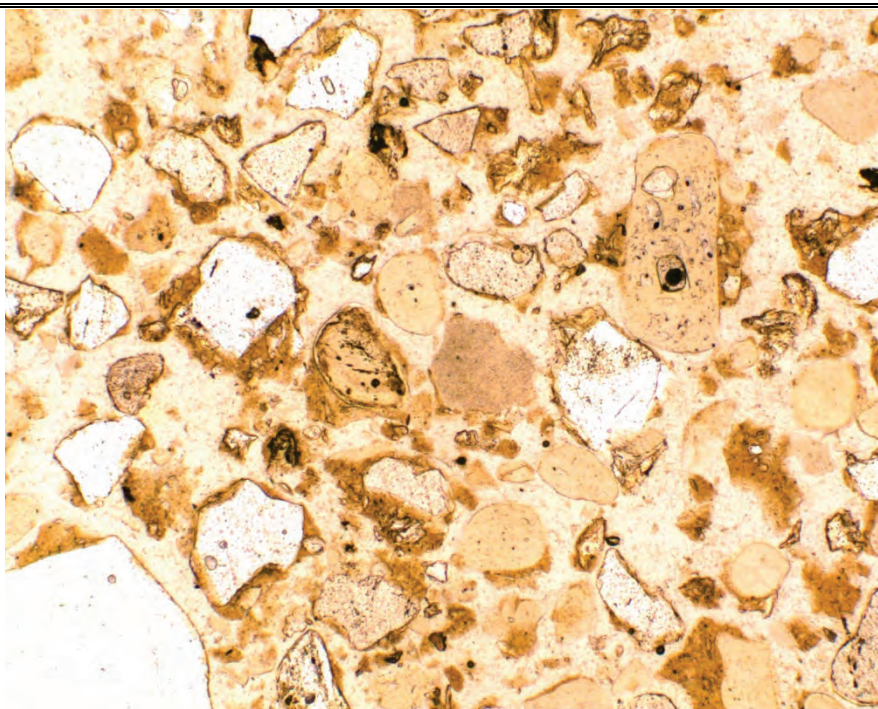

Subangular to subrounded quartz grains in a kaolinite, wavellite, and apatite matrix (brown). Plane light.

PHOTO 2

CCR4A 26.1-26.4

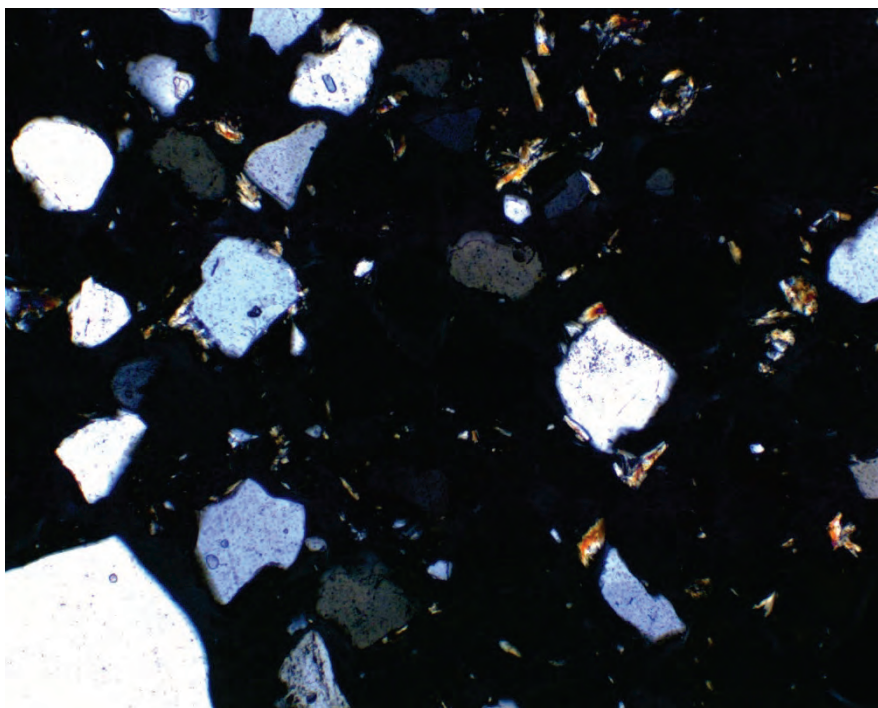


Subangular to subrounded quartz grains in a kaolinite, wavellite, and apatite matrix (brown). Polarized light.

Unless otherwise indicated, all images were taken at 5x magnification; the long-edge of the field of view in the photographs is approximately 2.5 mm in length.

Lakeland Electric

PHOTO 1


CCR7A 23.2-23.5

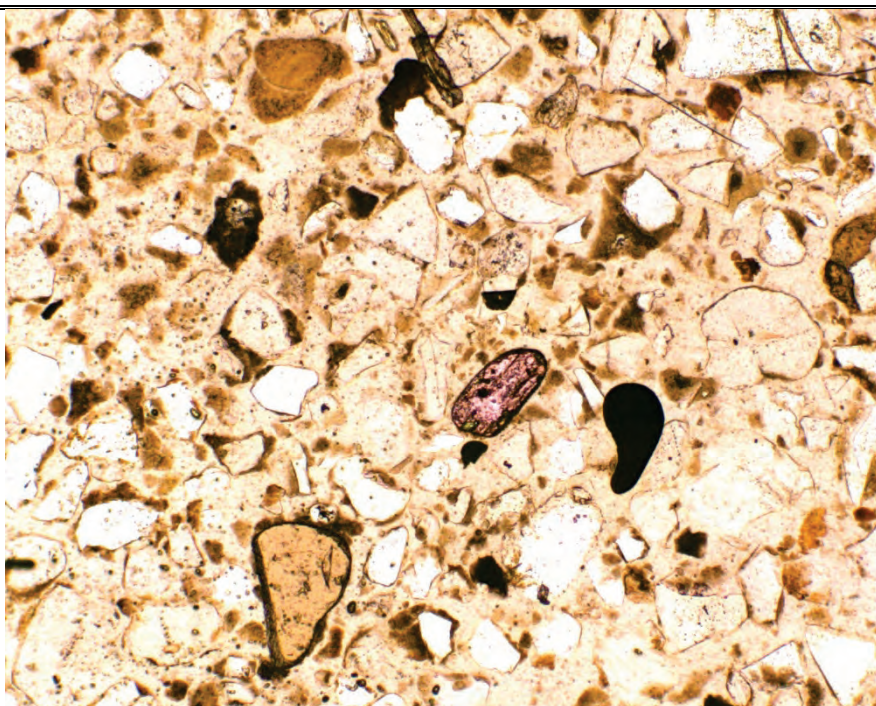

Subangular to subrounded quartz grains in a kaolinite, apatite, and wavellite matrix (brown). Yellow and pleochroic minerals are staurolite; opaque mineral is ilmenite. Plane light.

PHOTO 2

CCR7A 23.2-23.5

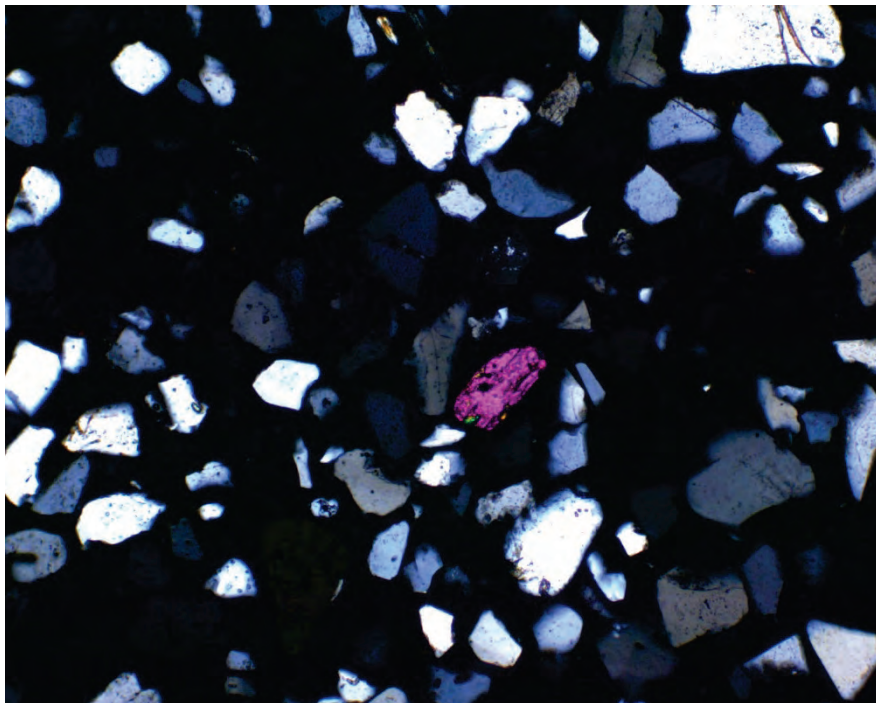


Subangular to subrounded quartz grains in a kaolinite, apatite, and wavellite matrix (brown). Greenish and purple mineral are staurolite. Polarized light.

Unless otherwise indicated, all images were taken at 5x magnification; the long-edge of the field of view in the photographs is approximately 2.5 mm in length.

Lakeland Electric

PHOTO 1


CCR13A 27.8-28.2

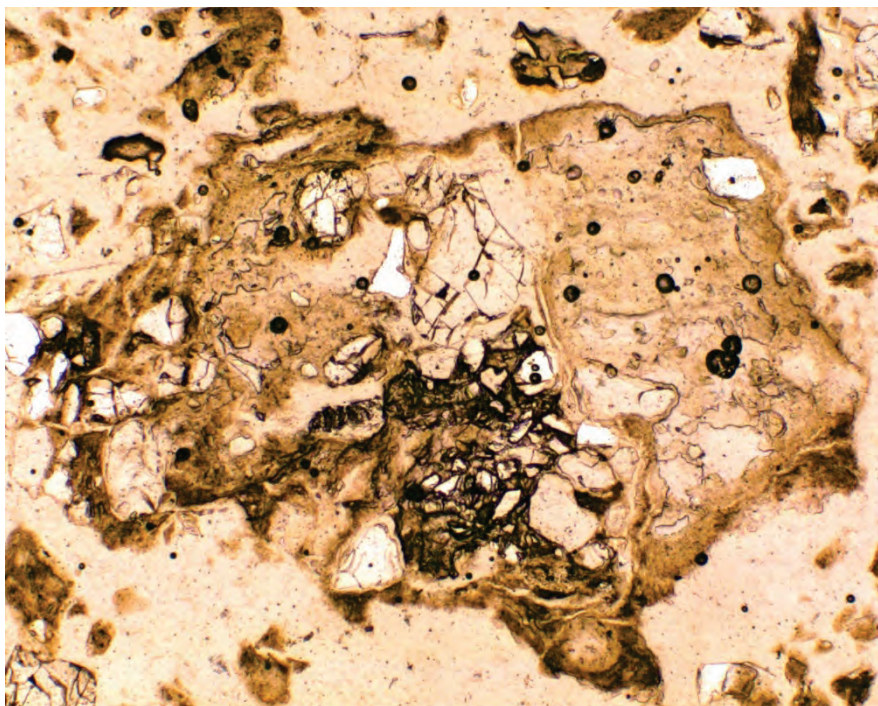

Minor subangular quartz grains in a clay and wavellite matrix. Plane light.

PHOTO 2

CCR13A 27.8-28.2

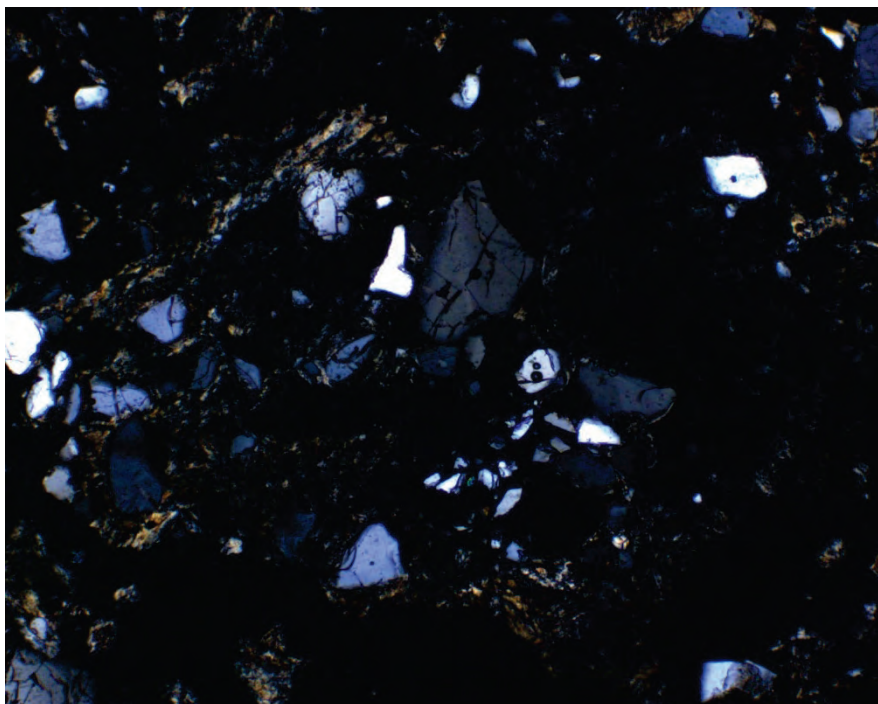


Minor subangular quartz grains in a clay and wavellite matrix. Polarized light.

Lakeland Electric

PHOTO 3


CCR13A 27.8-28.2

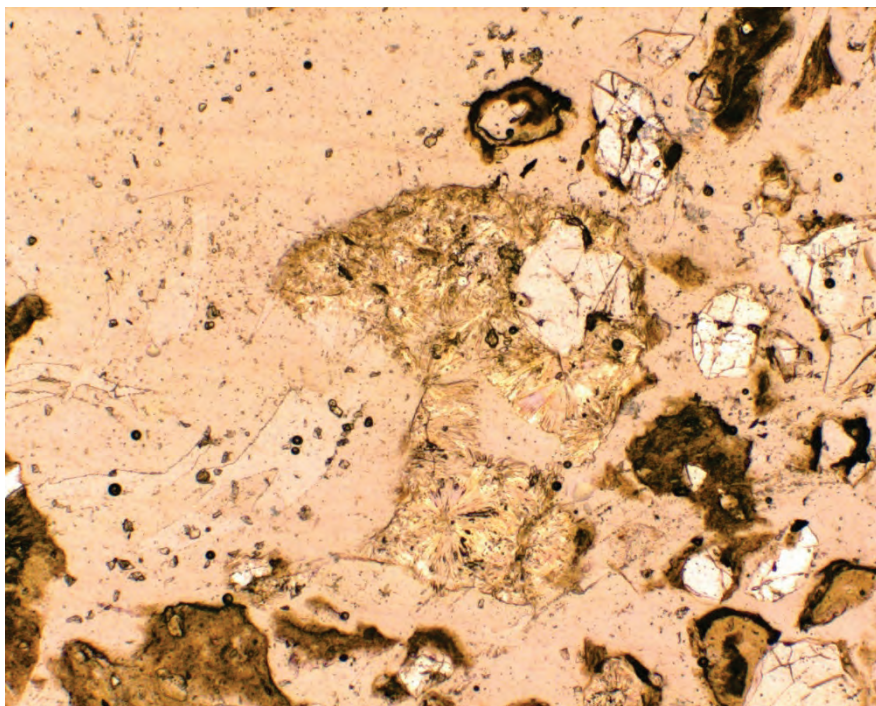

Wavellite cement around an angular quartz grain. Plane light.

PHOTO 4

CCR13A 27.8-28.2

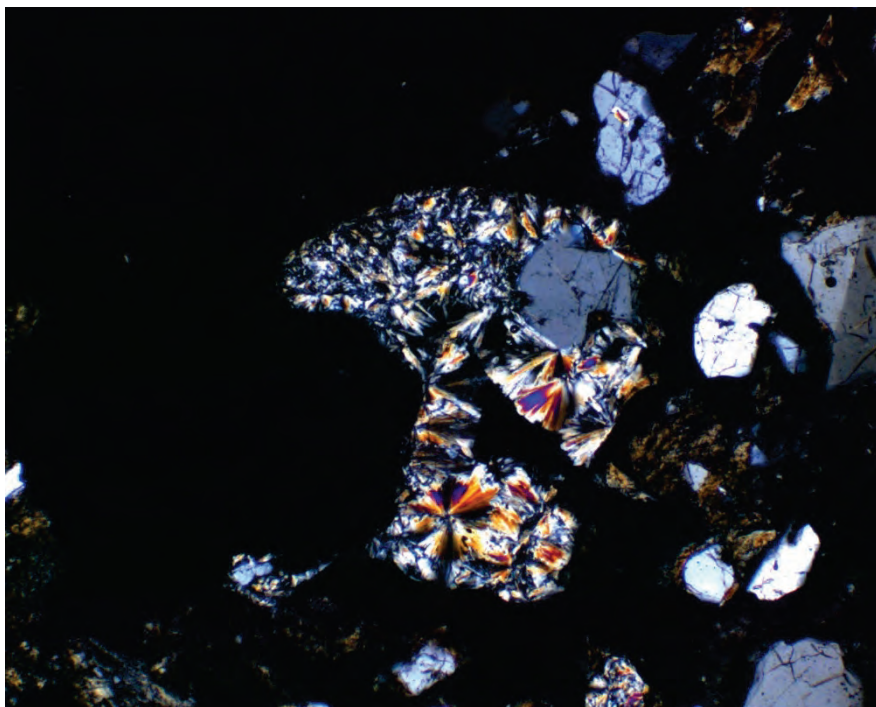


Wavellite cement around an angular quartz grain. Polarized light.

Unless otherwise indicated, all images were taken at 5x magnification; the long-edge of the field of view in the photographs is approximately 2.5 mm in length

Lakeland Electric

PHOTO 1


CCR14A 28.3-28.66

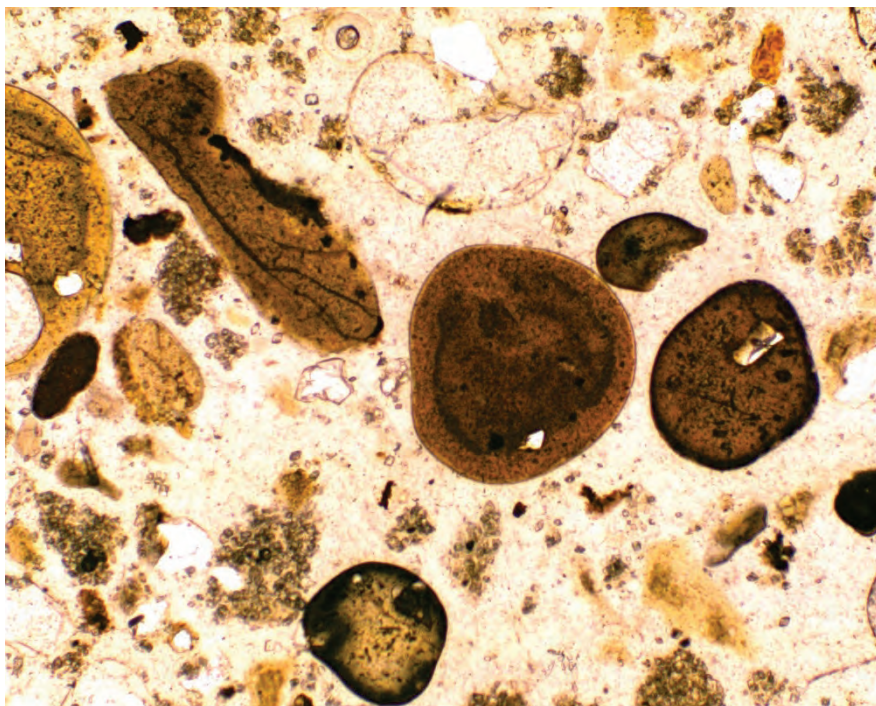

Collophane apatite "balls" in a clay matrix. Plane light

PHOTO 2

CCR14A 16.5-18.0

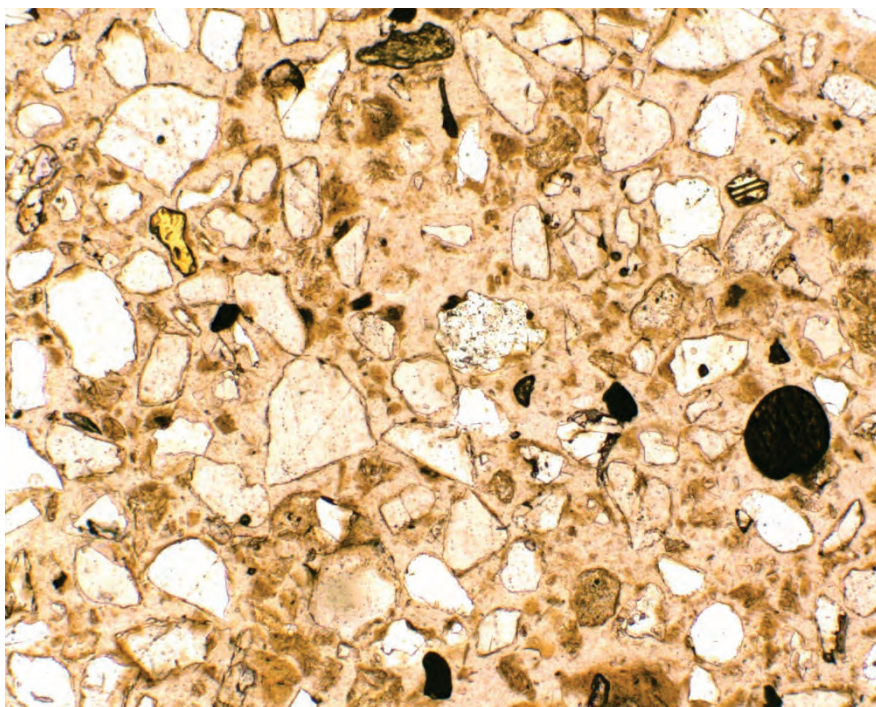


Subangular to subrounded quartz grains in a kaolinite and wavellite matrix (brown). Yellow mineral is staurolite, striated high-relief mineral is kyanite, and large round mineral is rutile. Plane light.

Unless otherwise indicated, all images were taken at 5x magnification; the long-edge of the field of view in the photographs is approximately 2.5 mm in length

Lakeland Electric

PHOTO 3


CCR14A 28.3-28.66

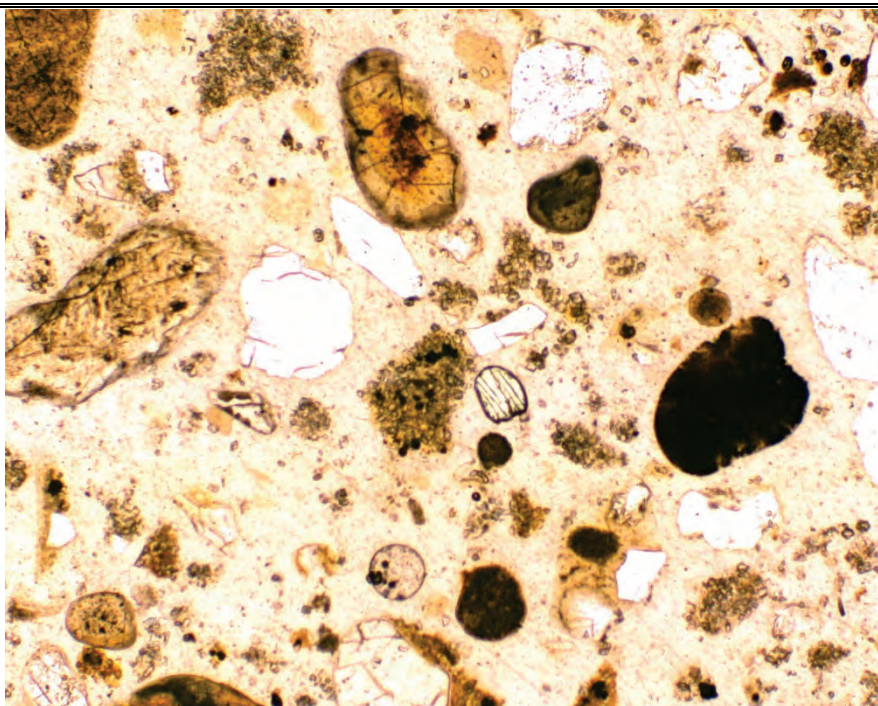

Collophane apatite "balls" in a clay and dolomite matrix. Pleochroic grain near the center of the image is staurolite. Plane light.

PHOTO 4

CCR14A 16.5-18.0

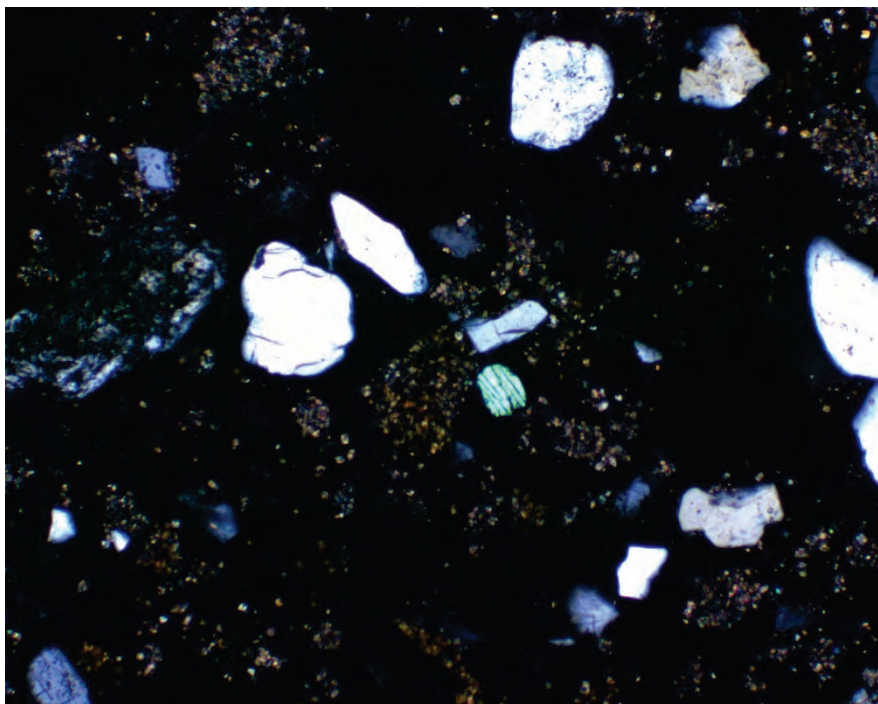


Collophane apatite "balls" in a clay and dolomite matrix. Greenish grain near the center of the image is staurolite. Polarized light.

Unless otherwise indicated, all images were taken at 5x magnification; the long-edge of the field of view in the photographs is approximately 2.5 mm in length

Lakeland Electric

PHOTO 5


CCR14A 28.3-28.66

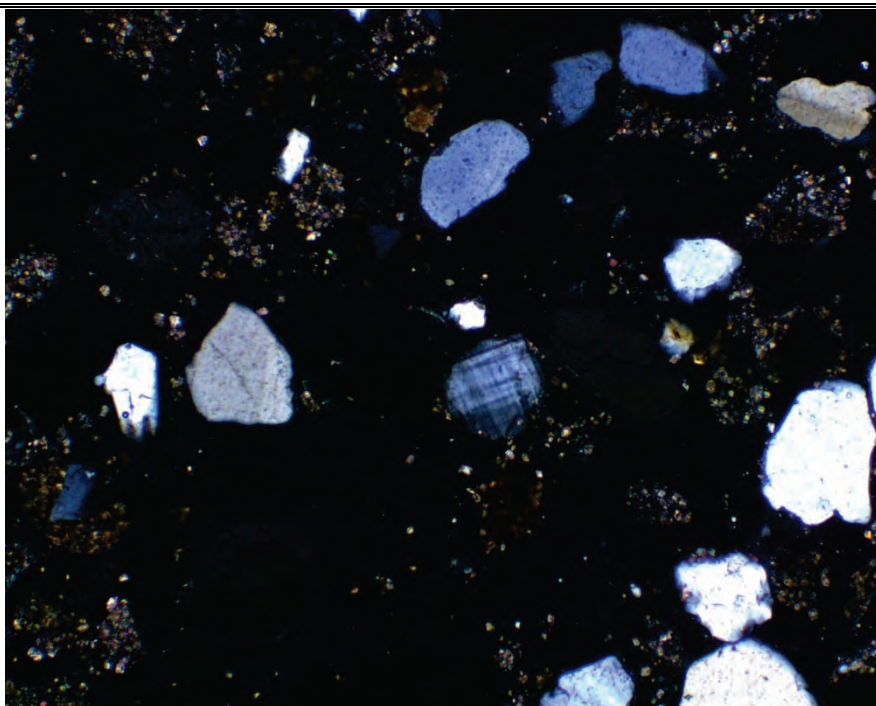

Microcline grain (showing twinning) in a clay and wavellite matrix. Polarized light.

PHOTO 6

CCR14A 16.5-18.0

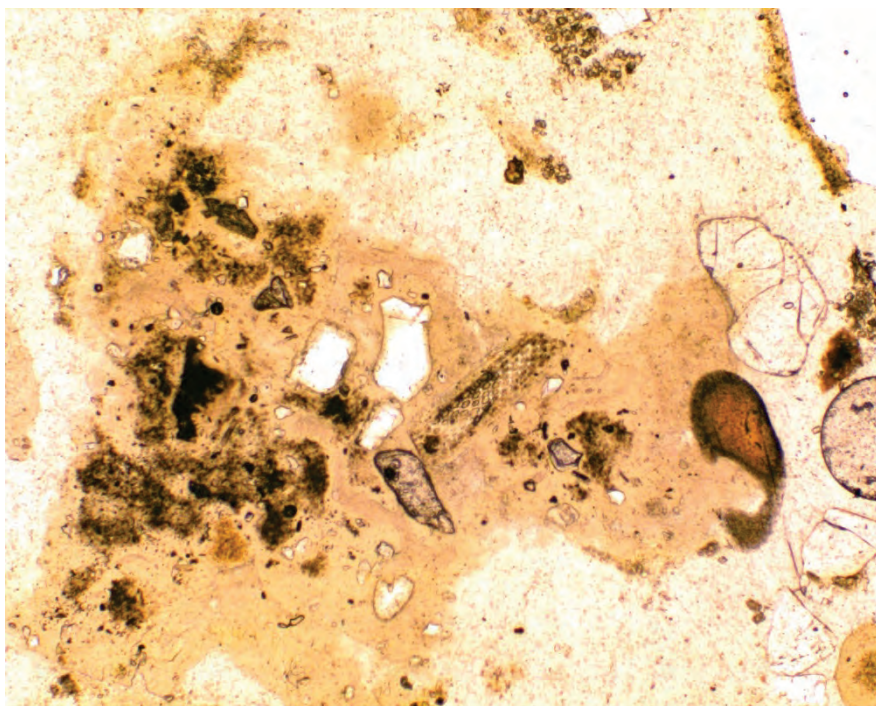


Fossil fragment (bryozoan?) in a clay-rich matrix . Plane light.

Unless otherwise indicated, all images were taken at 5x magnification; the long-edge of the field of view in the photographs is approximately 2.5 mm in length

Lakeland Electric

PHOTO 7


CCR14A 28.3-28.66

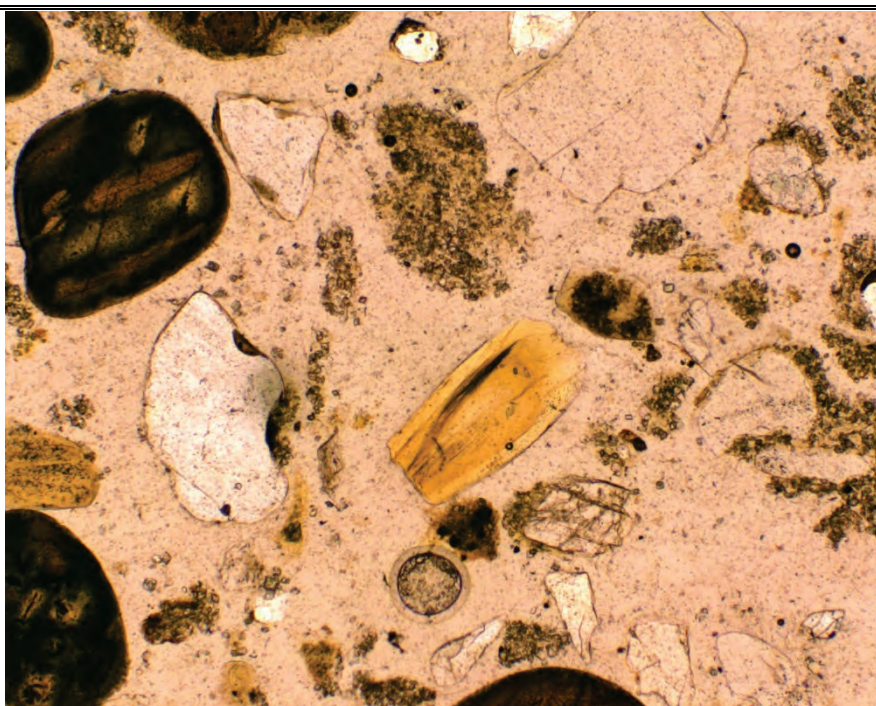

Phosphatic bone fragment and collophane "balls" in a dolomitic, clay-rich matrix (brown). Polarized light.

PHOTO 8

CCR14A 16.5-18.0

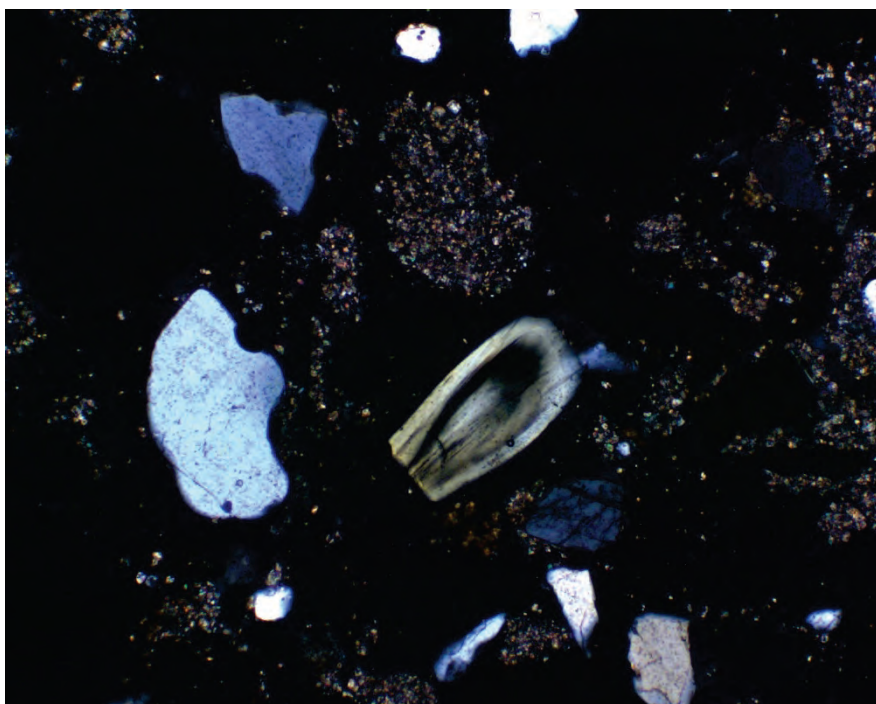

Phosphatic bone fragment and collophane "balls" in a dolomitic, clay-rich matrix (brown). Note undulatory extinction. Polarized light.

Unless otherwise indicated, all images were taken at 5x magnification; the long-edge of the field of view in the photographs is approximately 2.5 mm in length


PetroLOGIC Solutions, Inc.

3997 Oak Hill Road
Douglasville, GA 30135
Tel: (678) 313-4146
email: rlkath@comcast.net




ATTACHMENT 2


QUALITATIVE X-RAY DIFFRACTION DATA

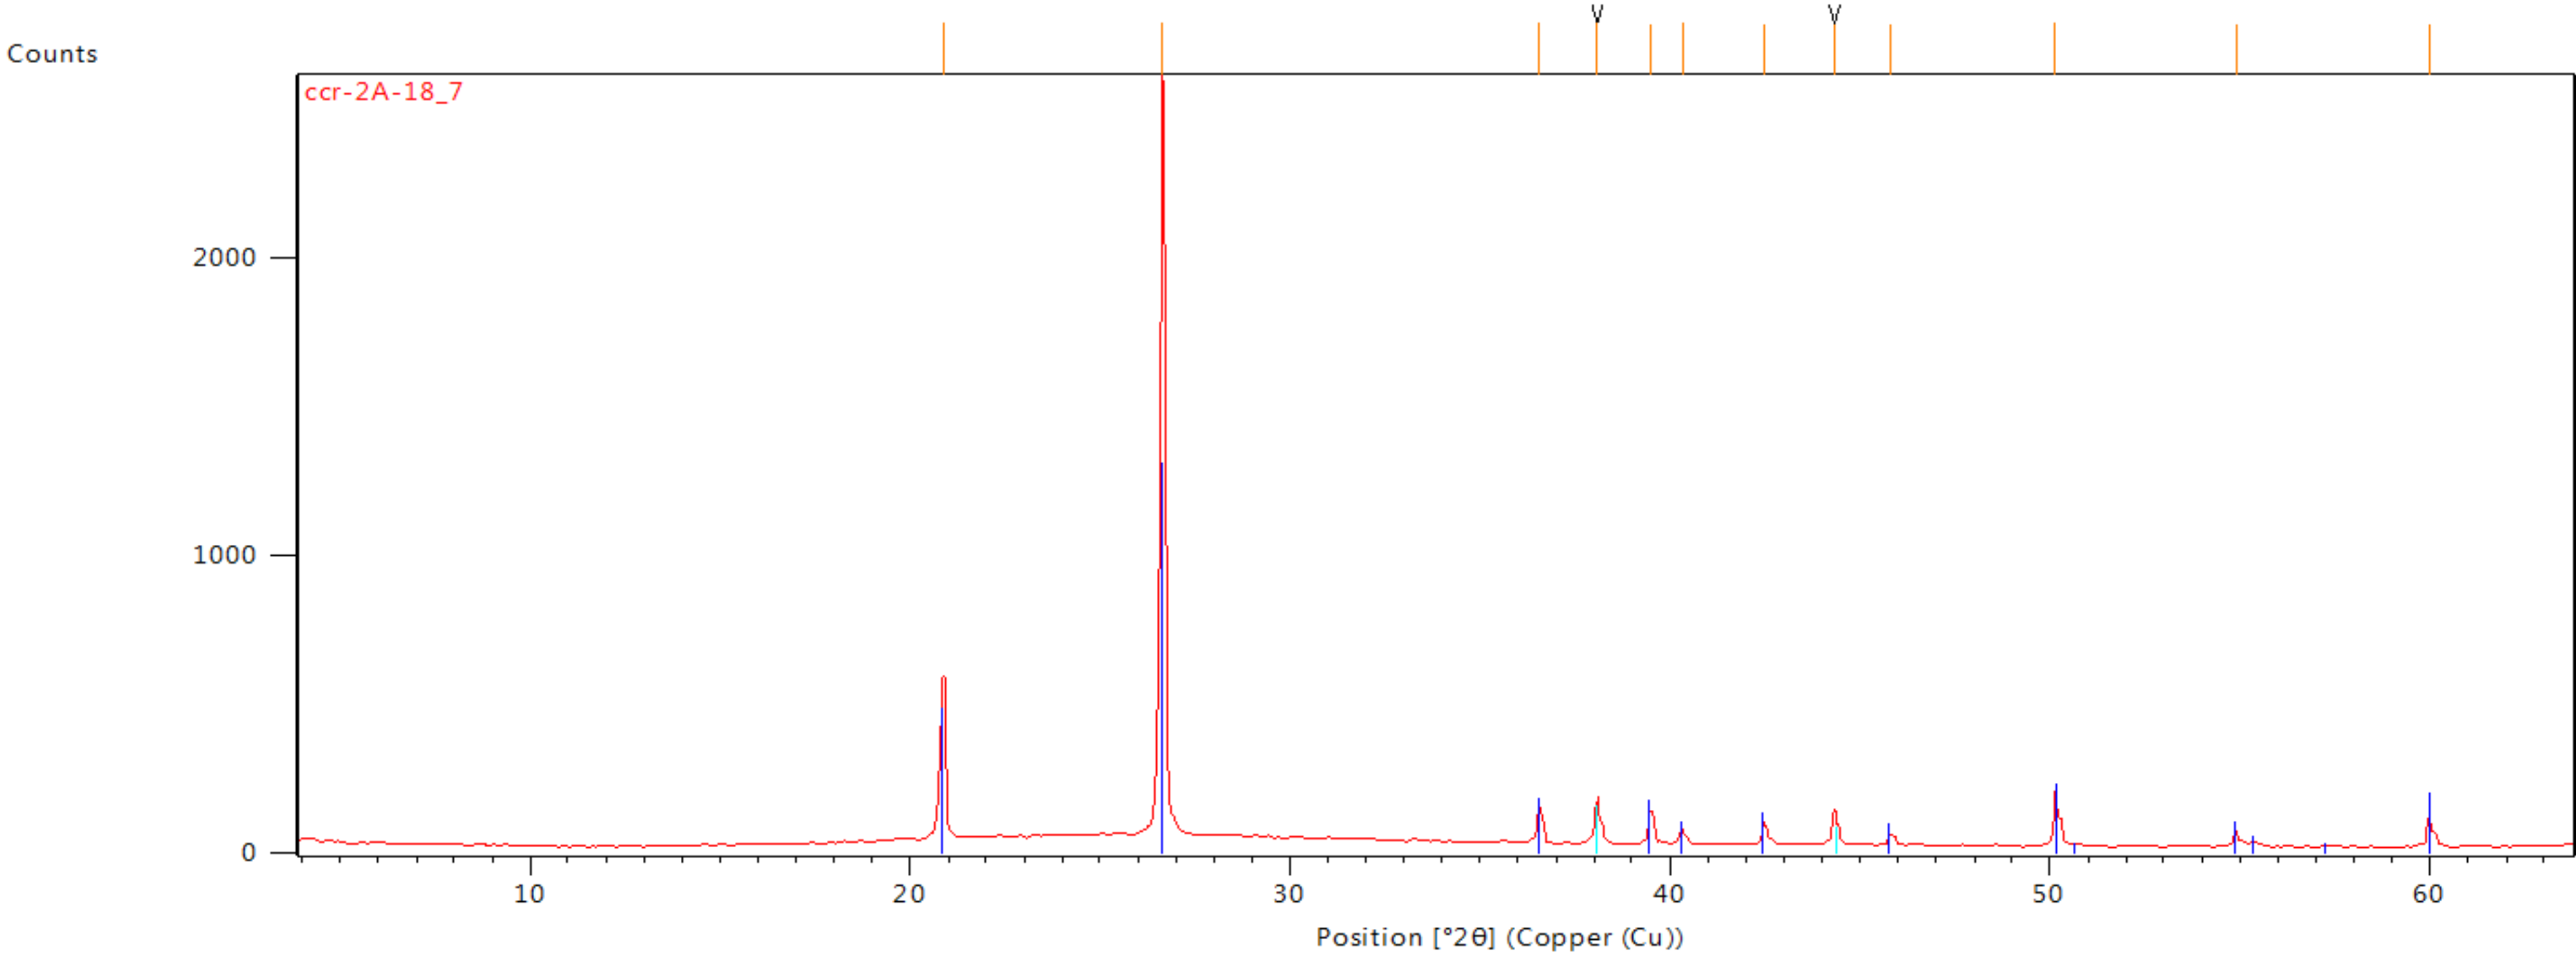


Peak List
00-005-0490; Quartz, low
00-004-0787; Aluminum, syn [NR]

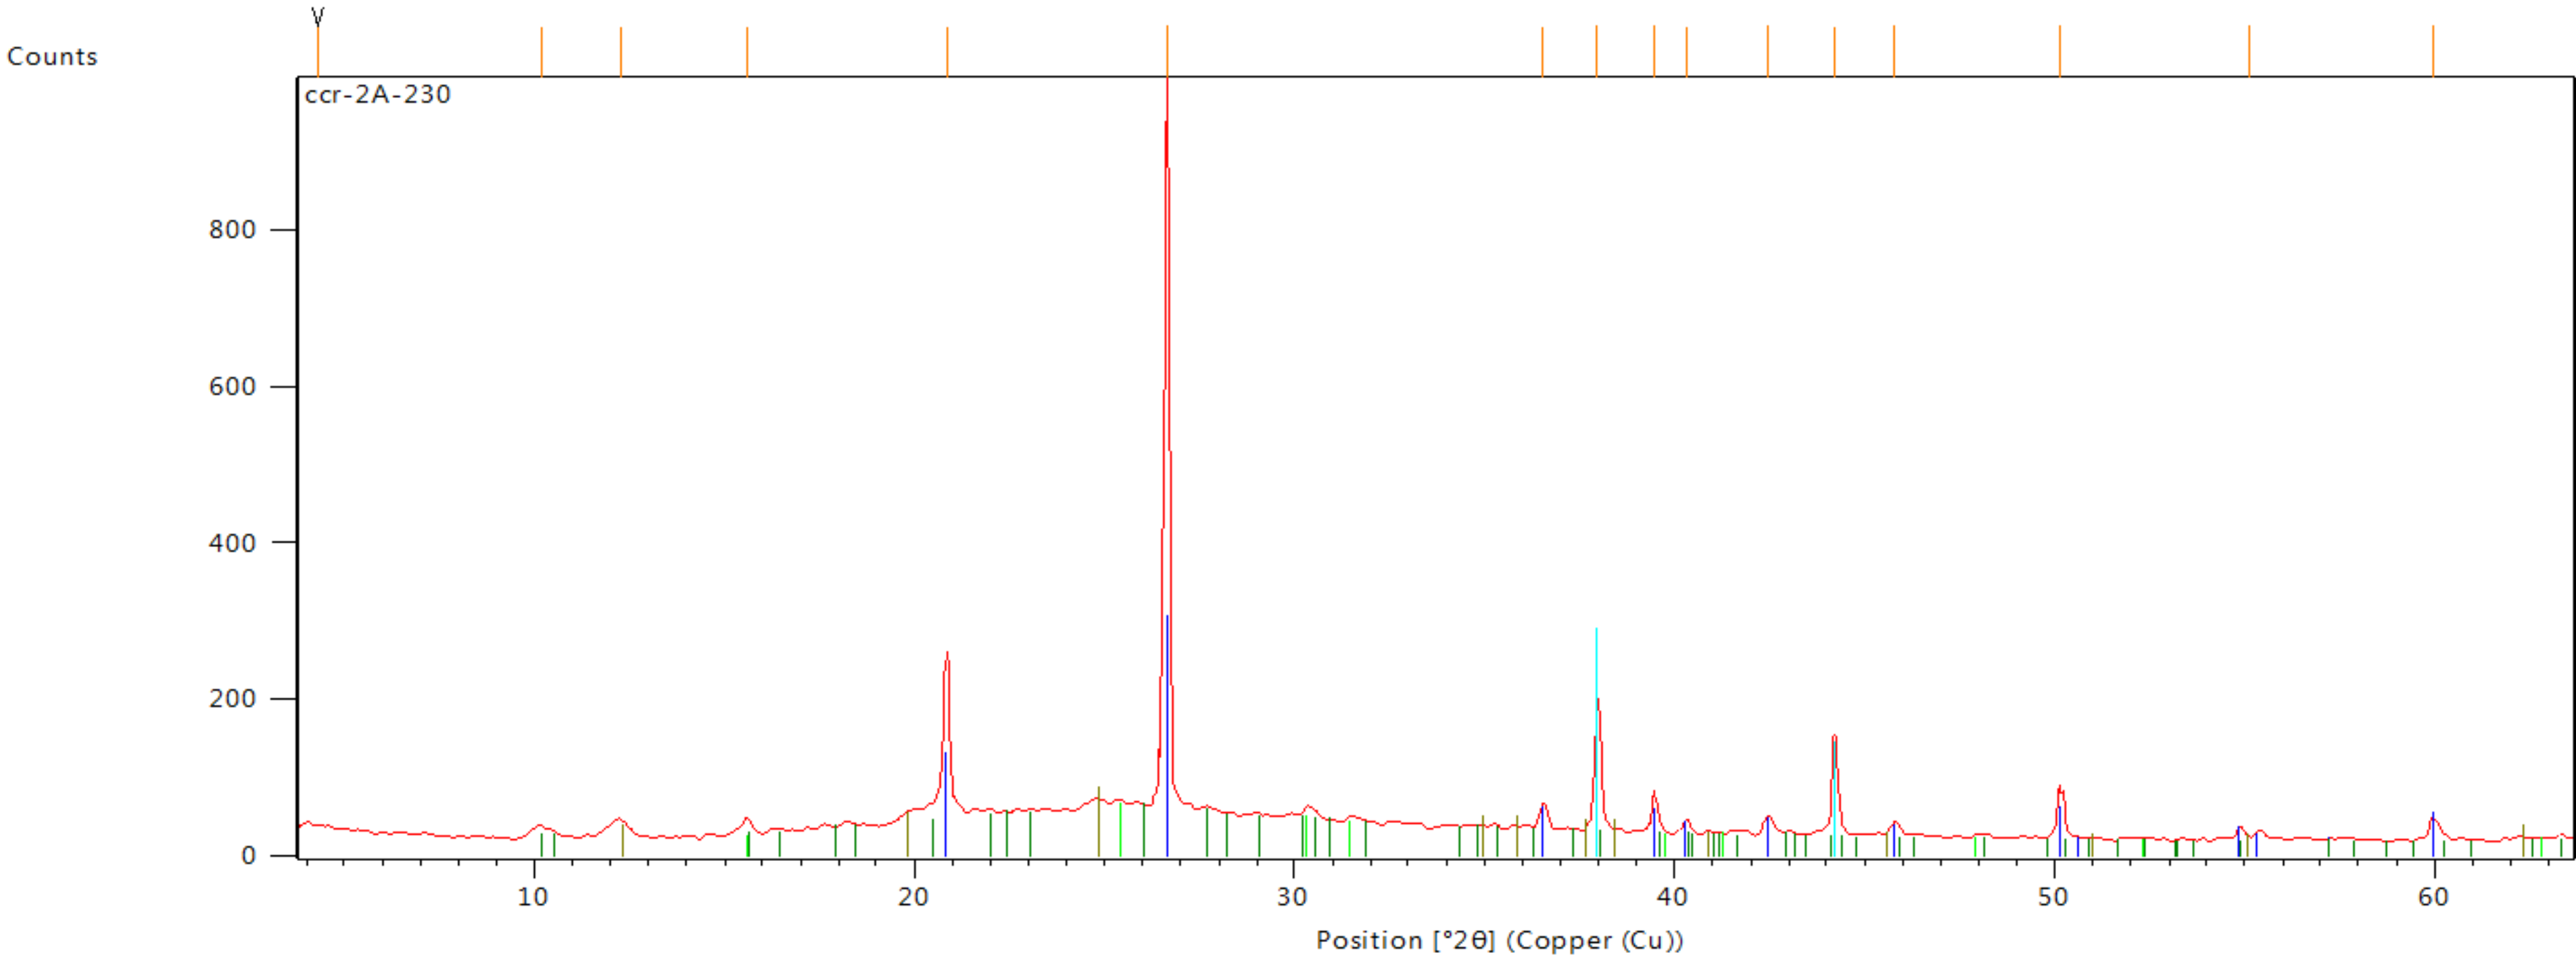

Peak List	
00-006-0221; Kaolinite 1Md	
00-026-0991; Eylettersite	
00-005-0490; Quartz, low	
00-004-0787; Aluminum, syn [NR]	
00-025-0020; Wavellite	

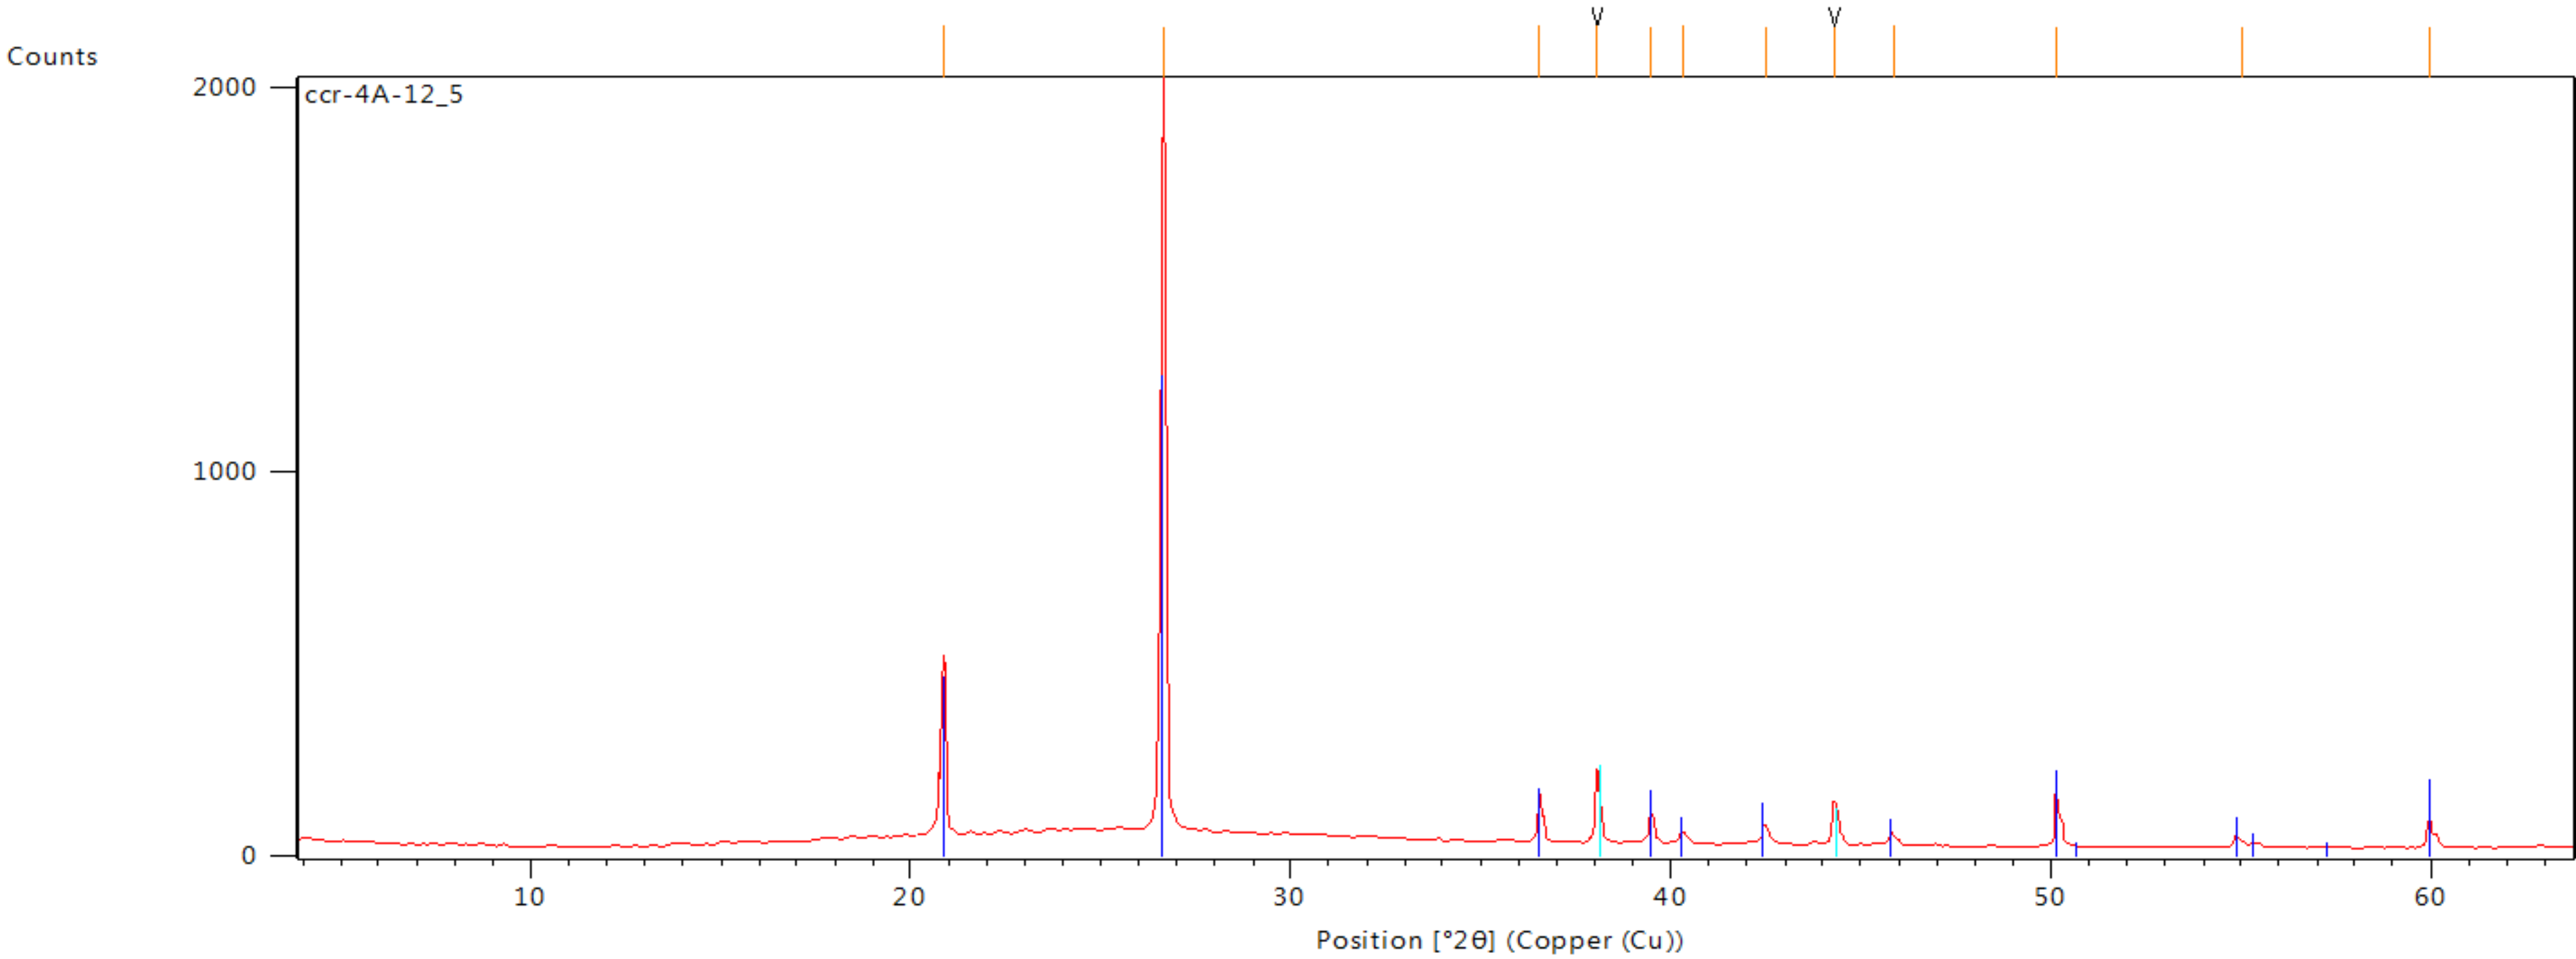


Peak List
00-005-0490; Quartz, low
00-004-0787; Aluminum, syn [NR]

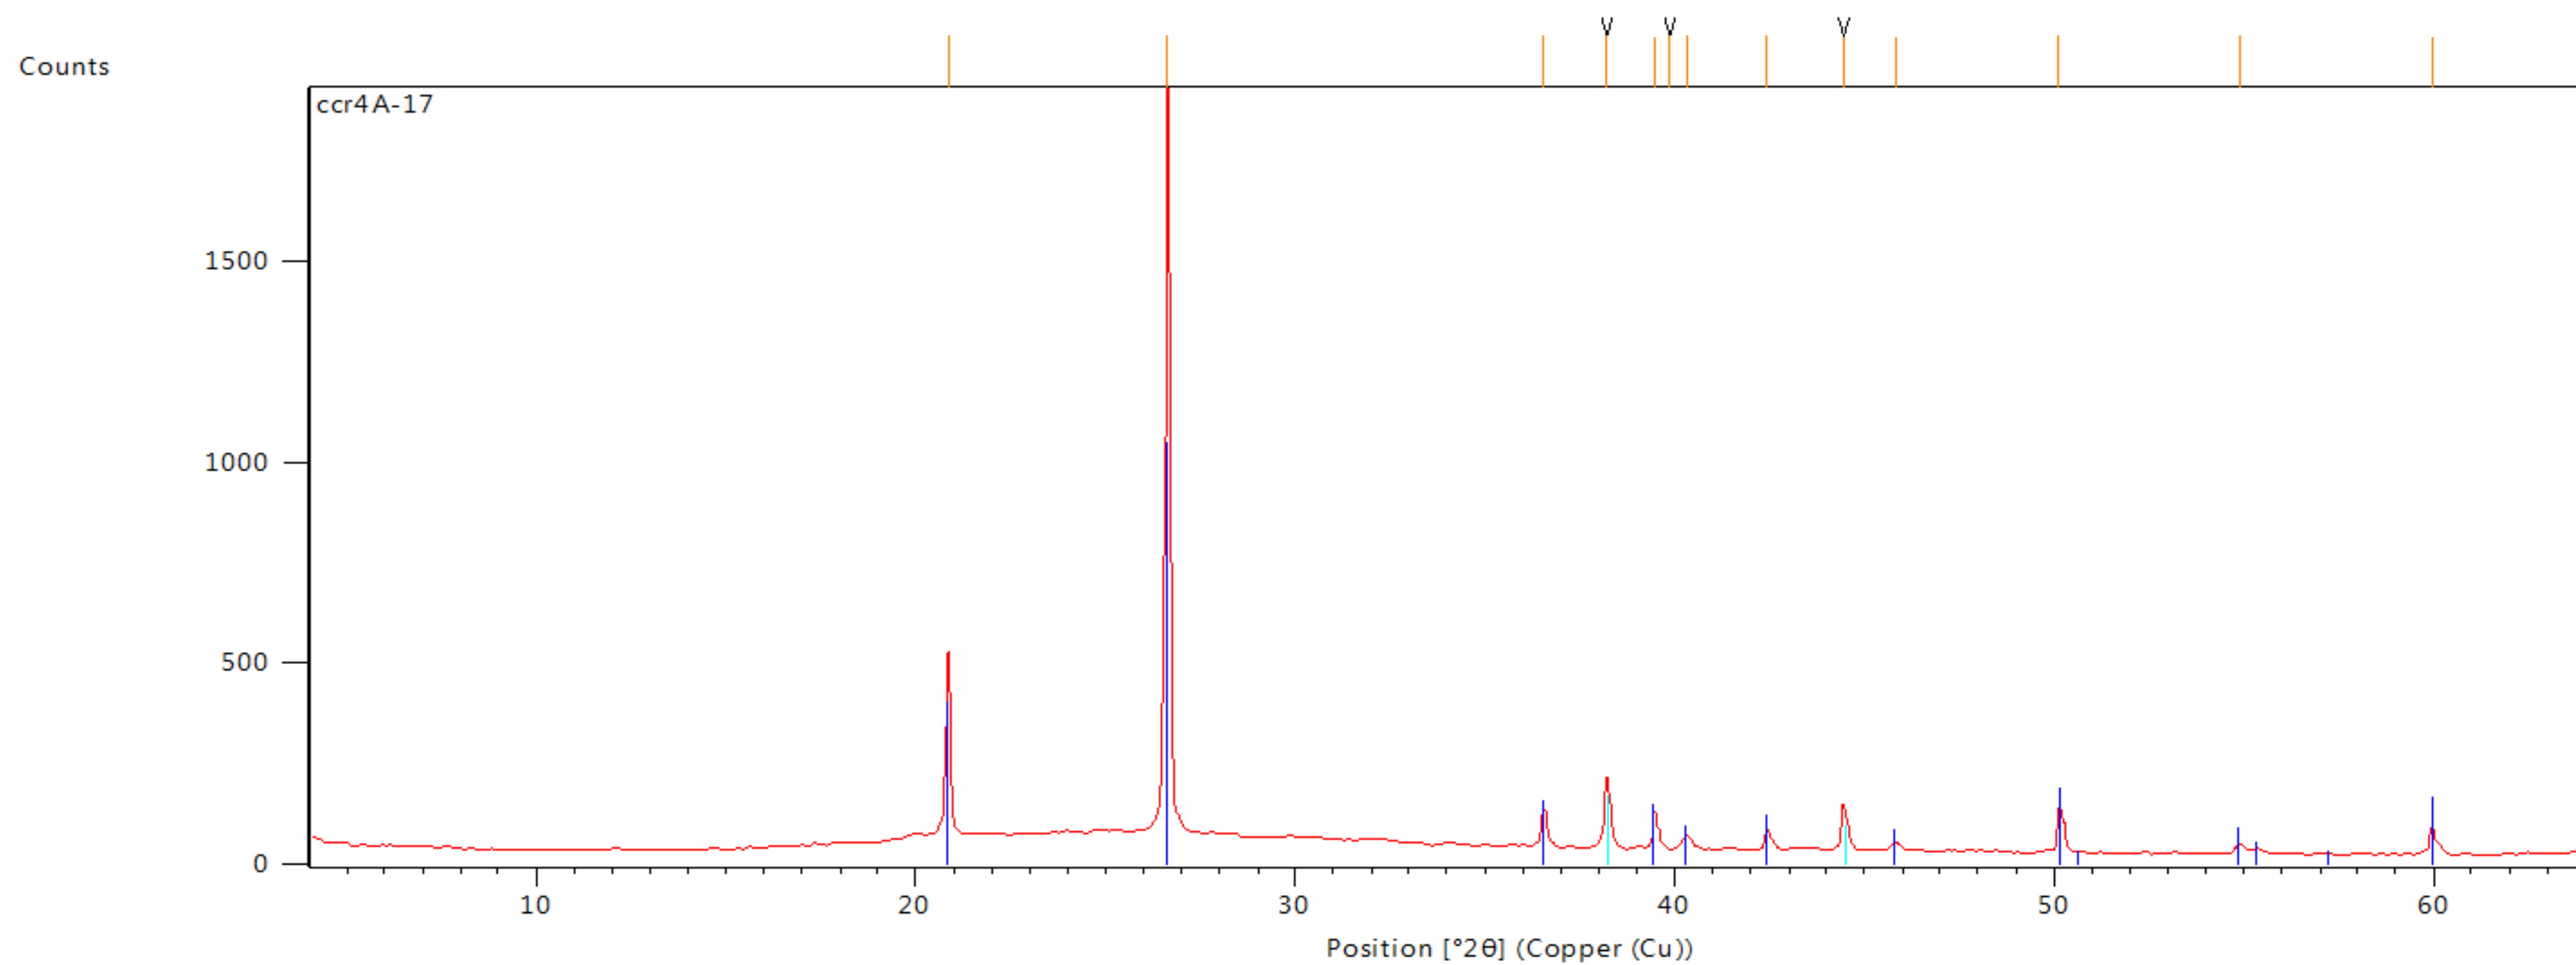

Peak List

00-005-0490; Quartz, low

00-004-0787; Aluminum, syn [NR]

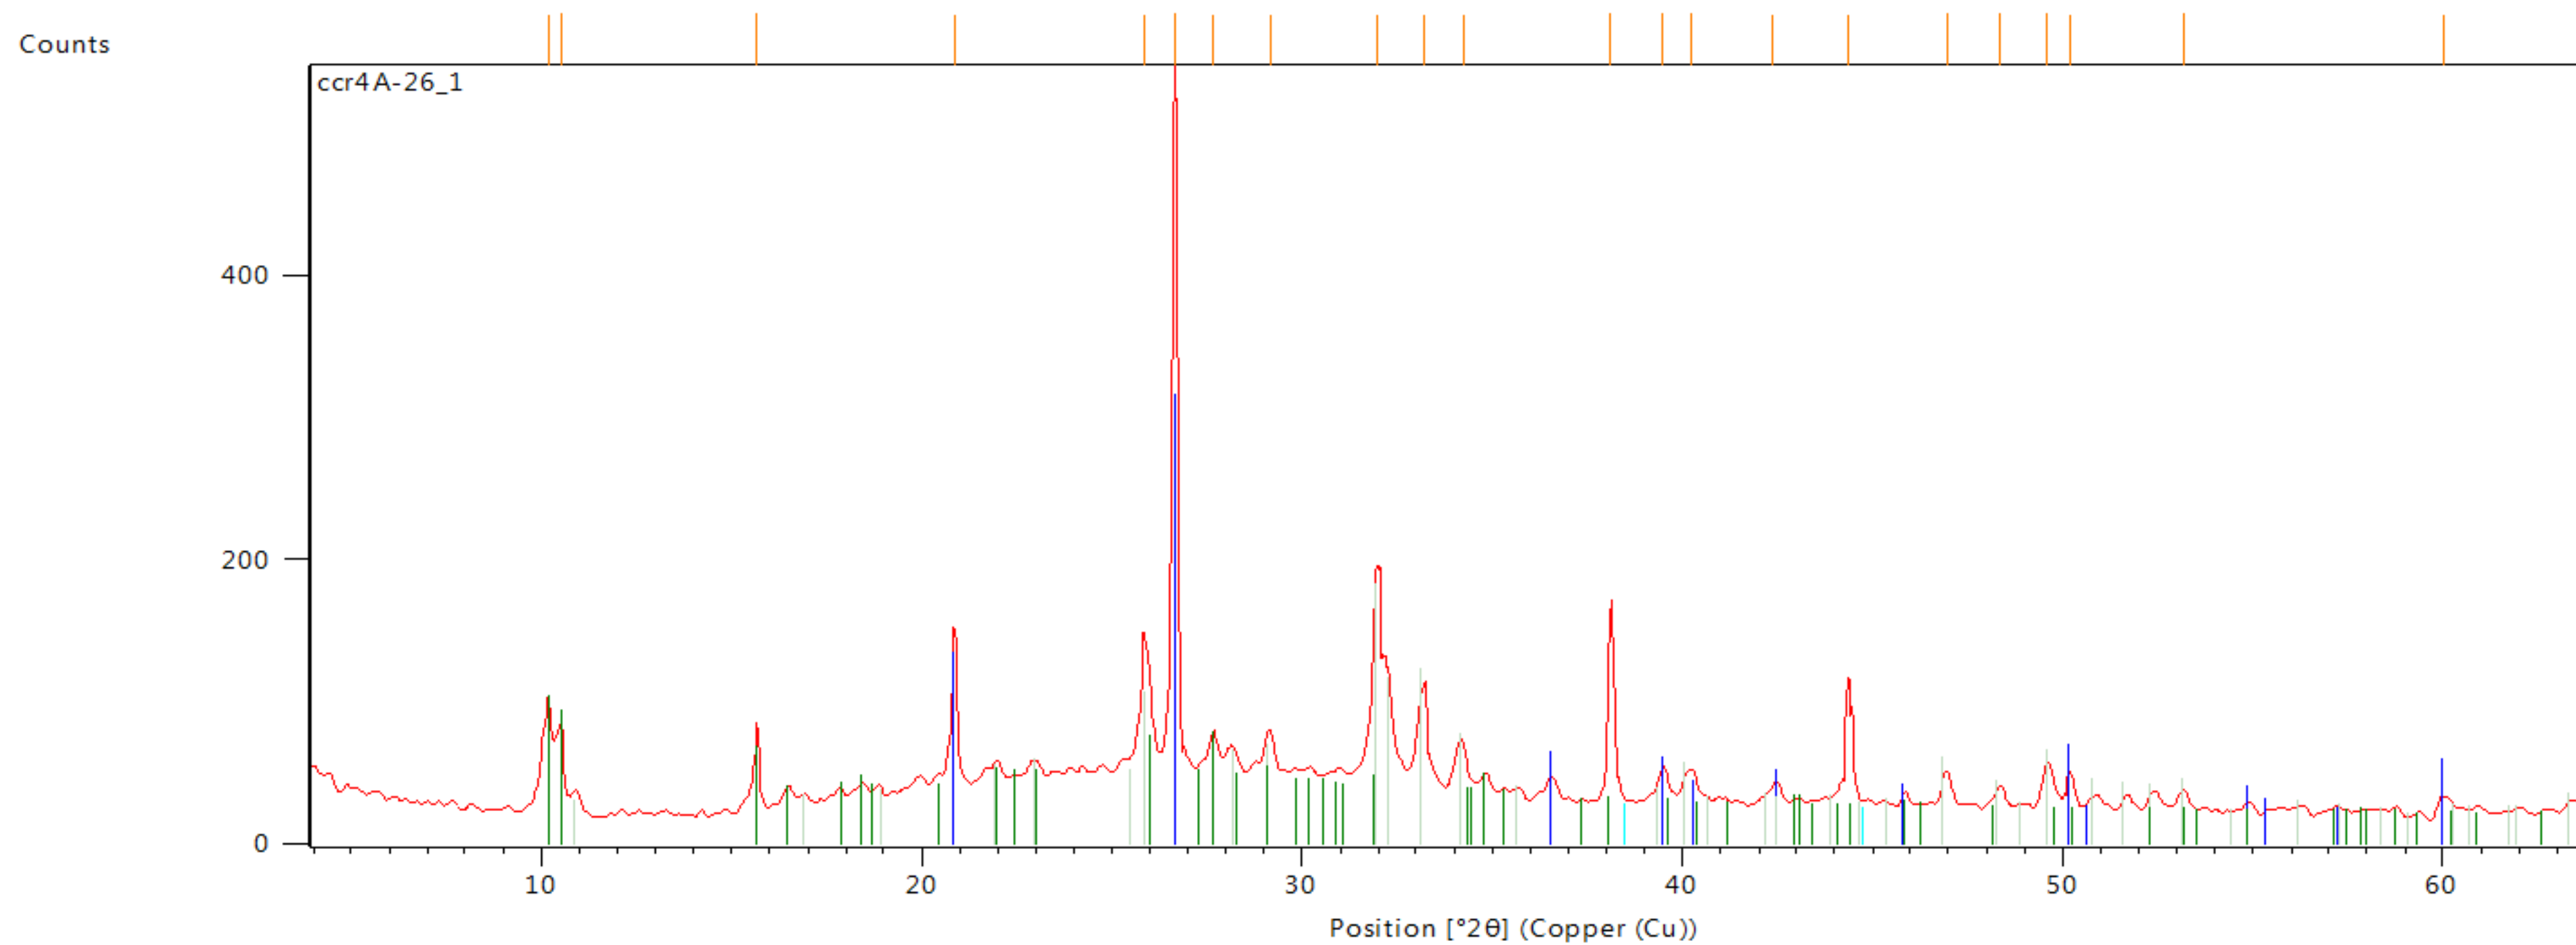


Peak List

00-005-0490; Quartz, low


00-004-0787; Aluminum, syn [NR]

00-015-0876; Fluorapatite, syn


00-027-0019; Wavellite

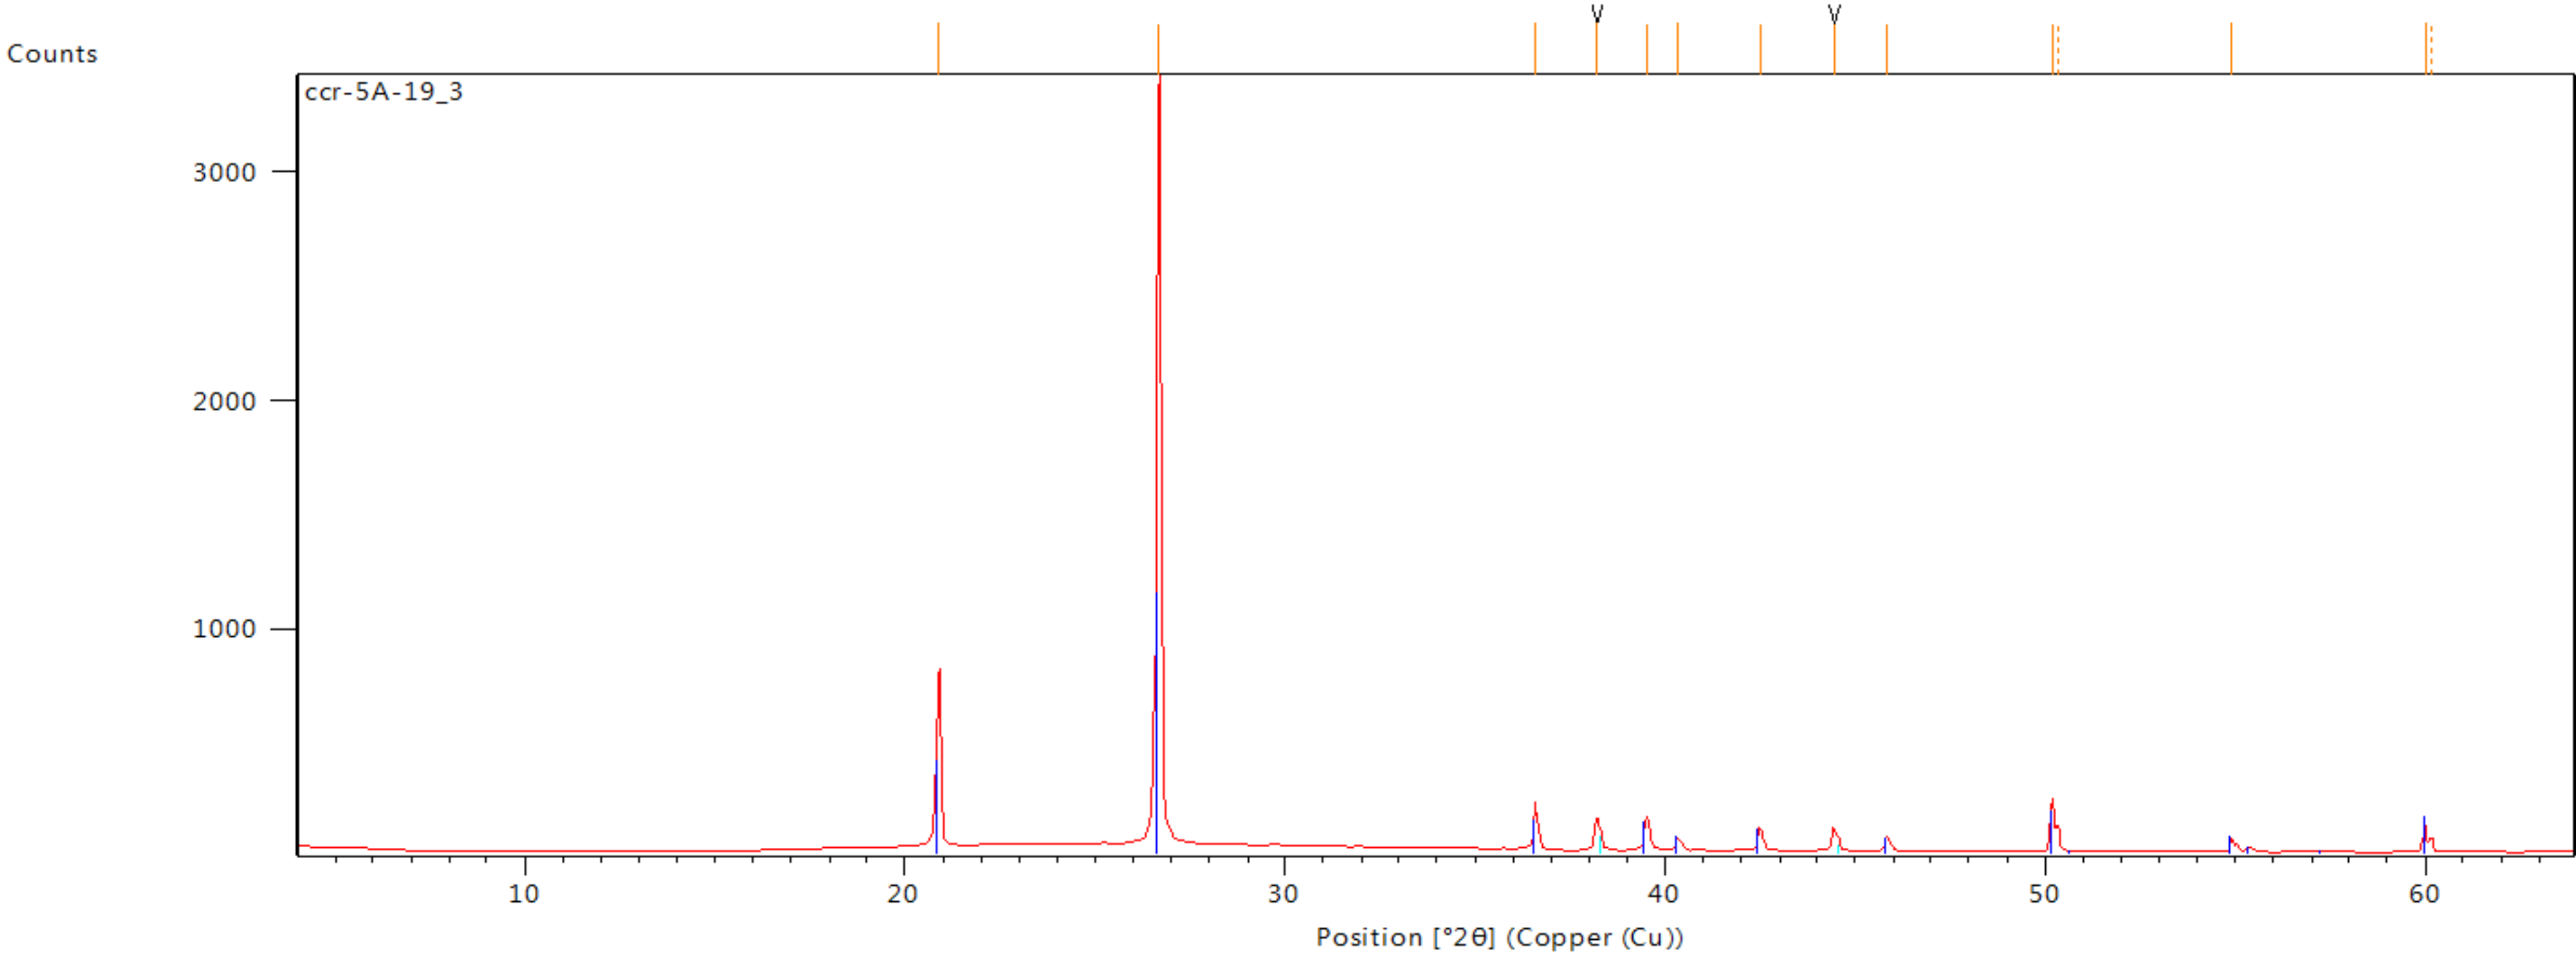


Peak List	
00-005-0490; Quartz, low	
00-004-0787; Aluminum, syn [NR]	

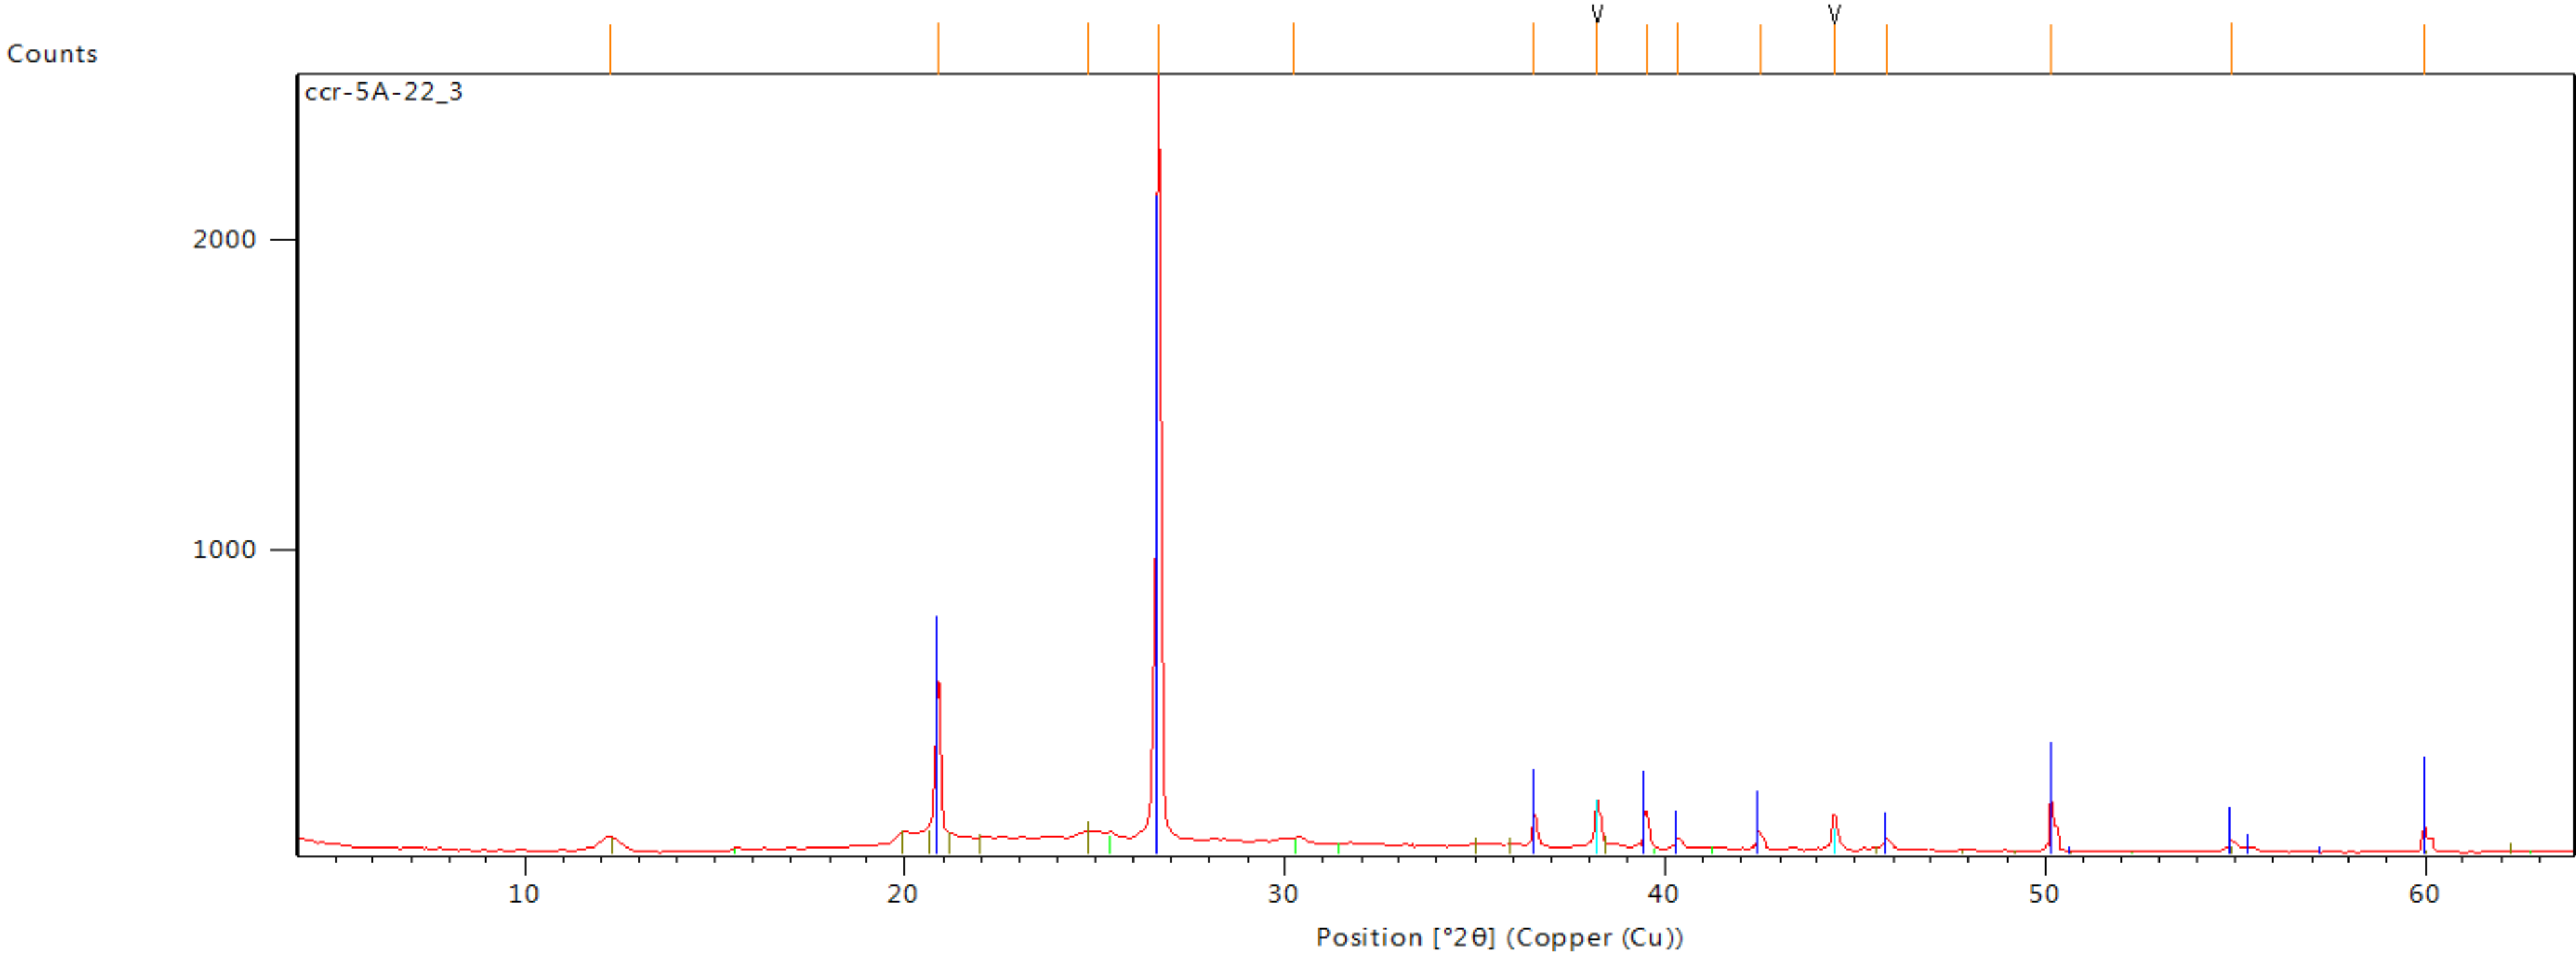


Residue + Peak List	
00-005-0490; Quartz, low	
00-004-0787; Aluminum, syn [NR]	
00-026-0991; Eylettersite	
00-001-0527; Kaolinite	

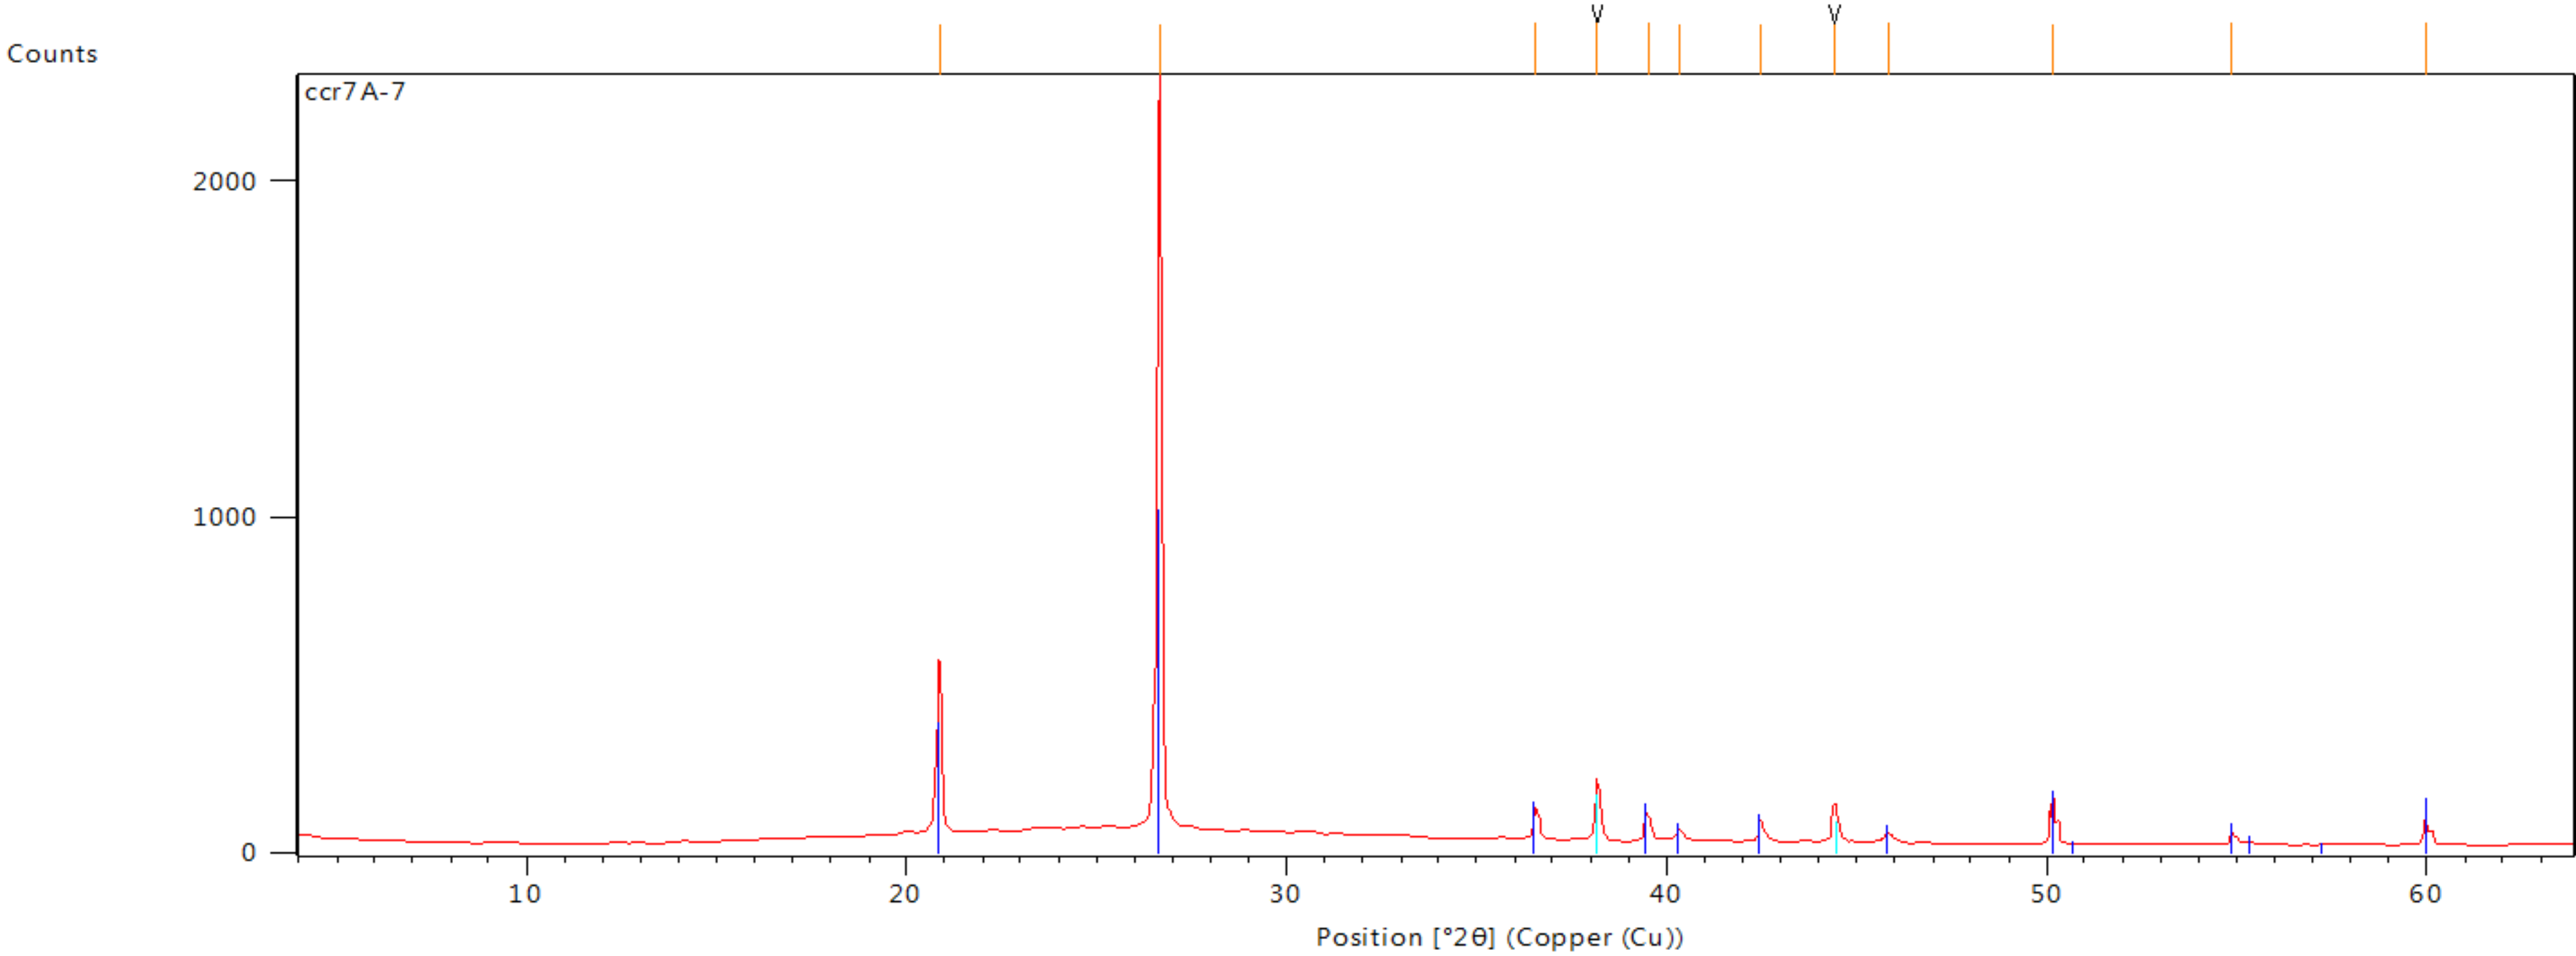


Peak List	
00-005-0490; Quartz, low	
00-004-0787; Aluminum, syn [NR]	

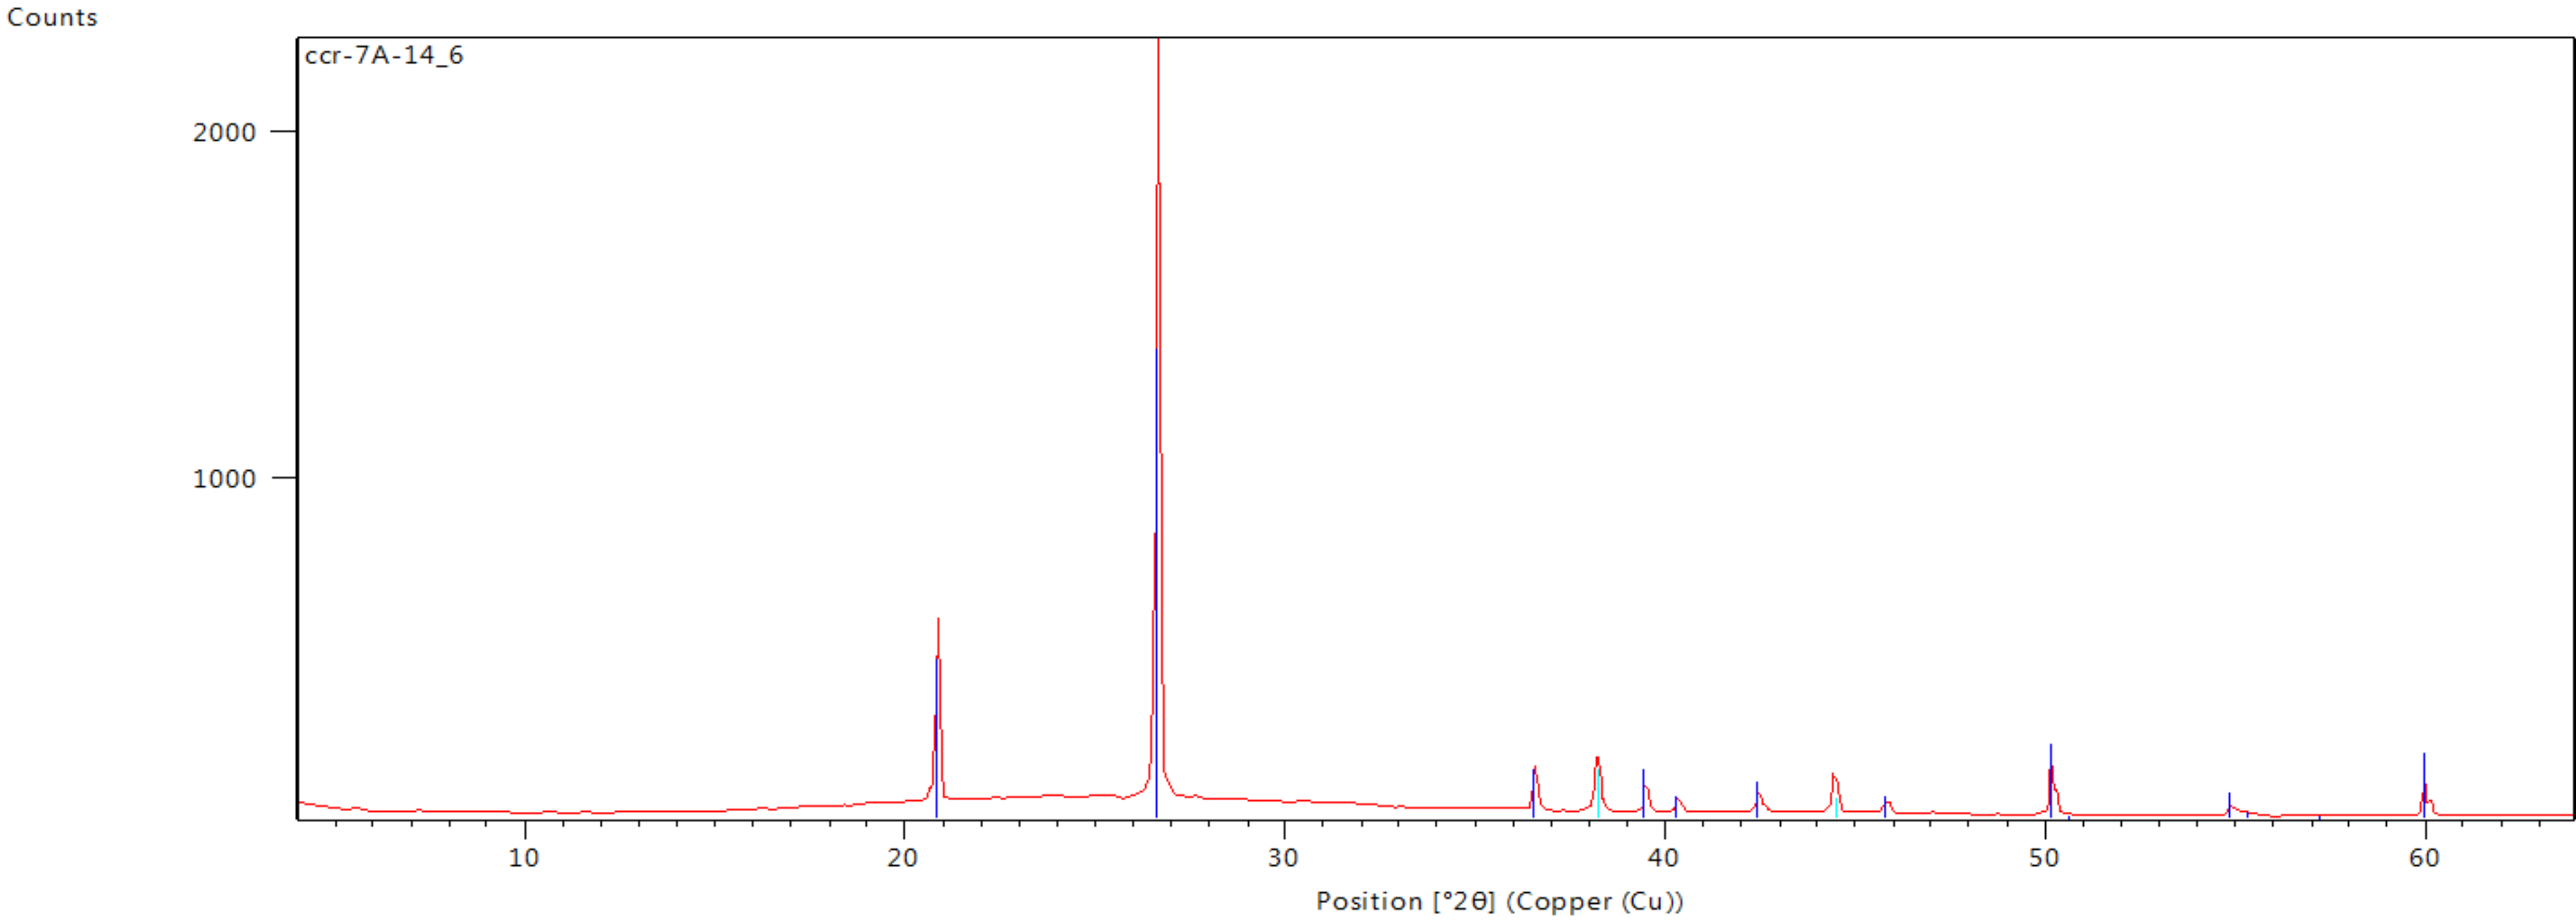


Peak List	
00-005-0490; Quartz, low	
00-004-0787; Aluminum, syn [NR]	

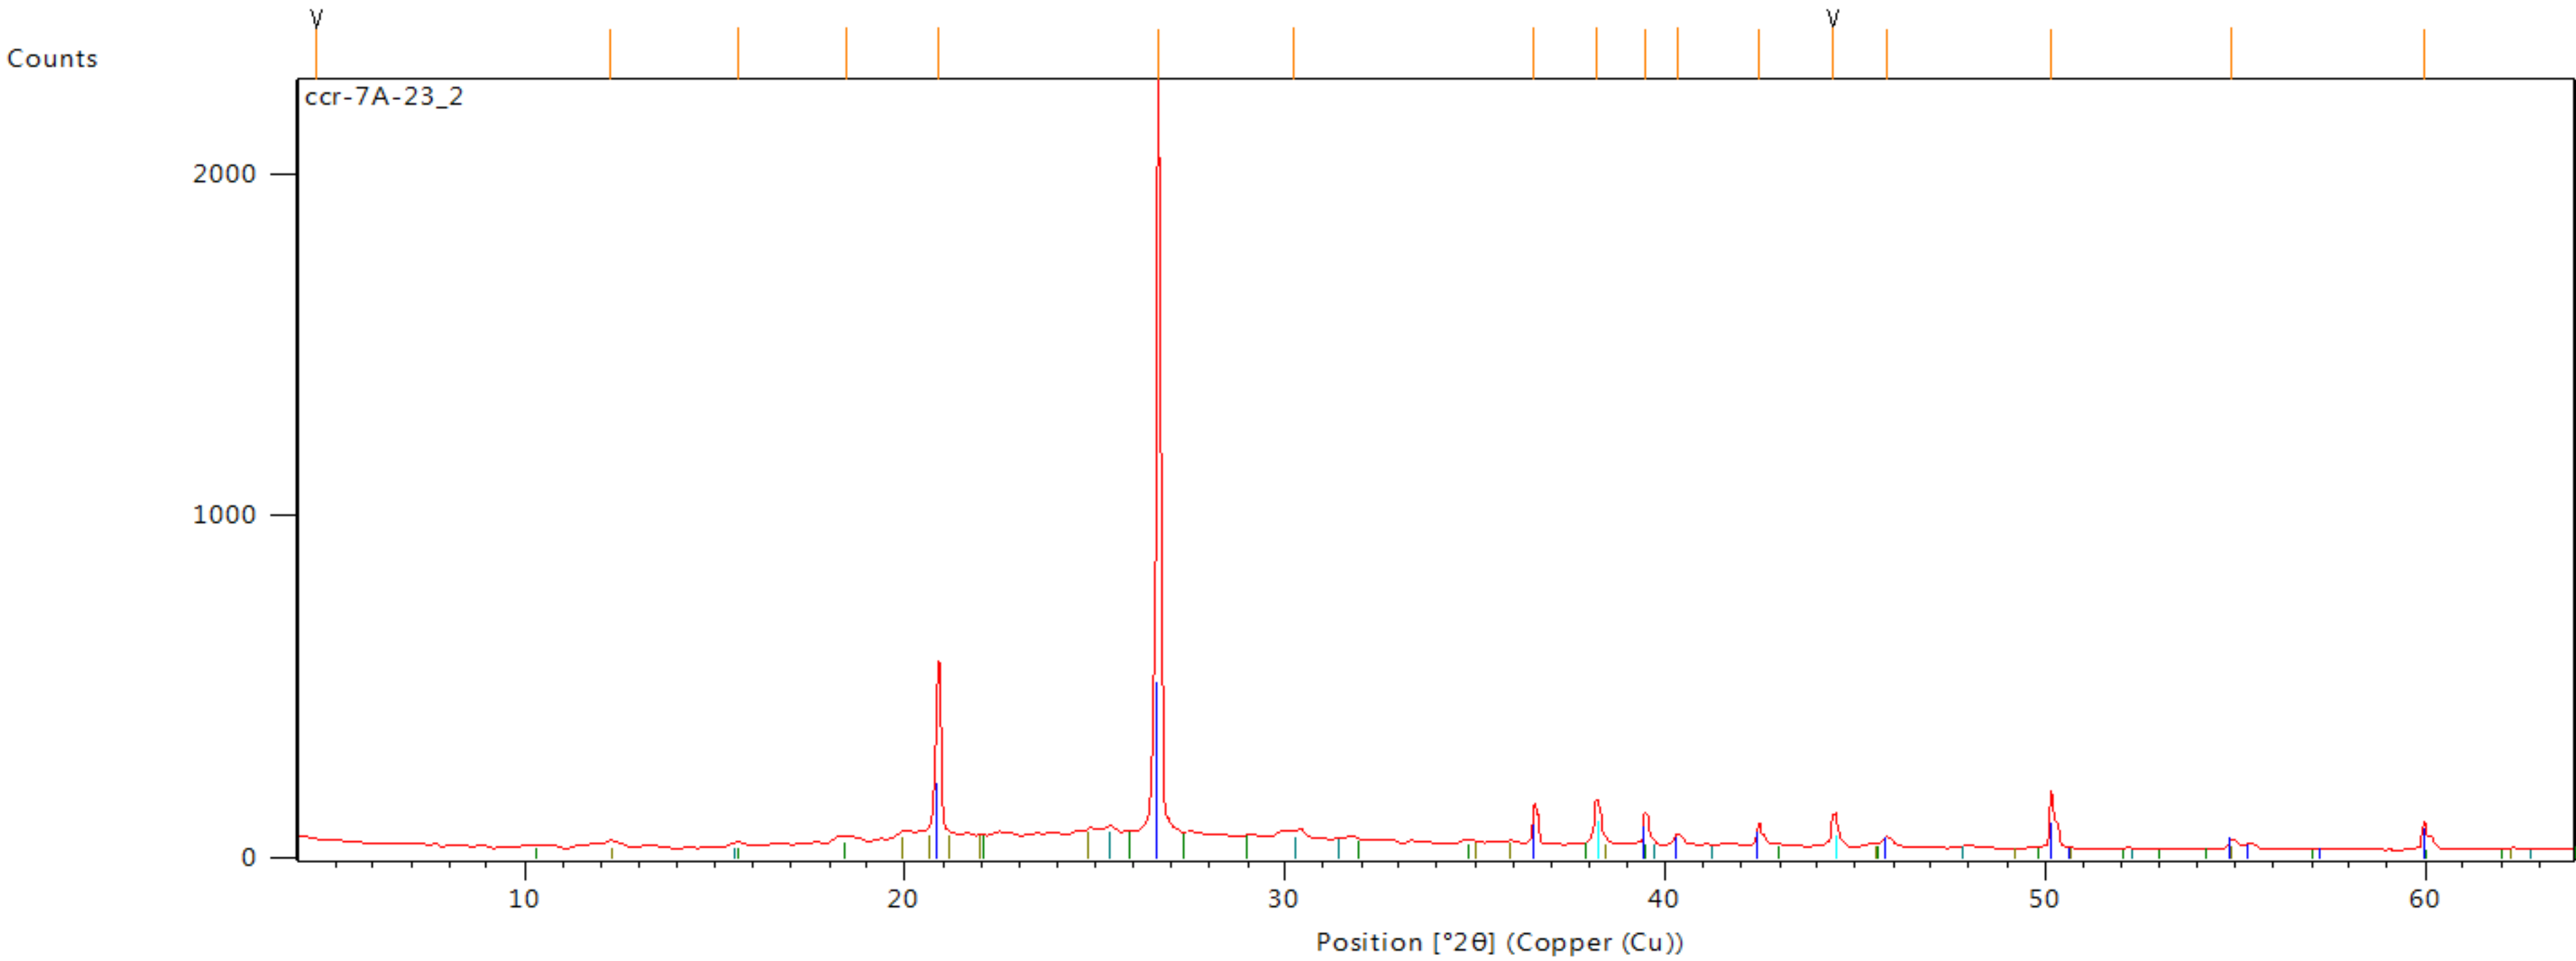

Peak List
00-004-0787; Aluminum, syn [NR]
00-005-0490; Quartz, low
00-001-0527; Kaolinite
00-017-0203; Wavellite
00-026-0991; Eylettersite

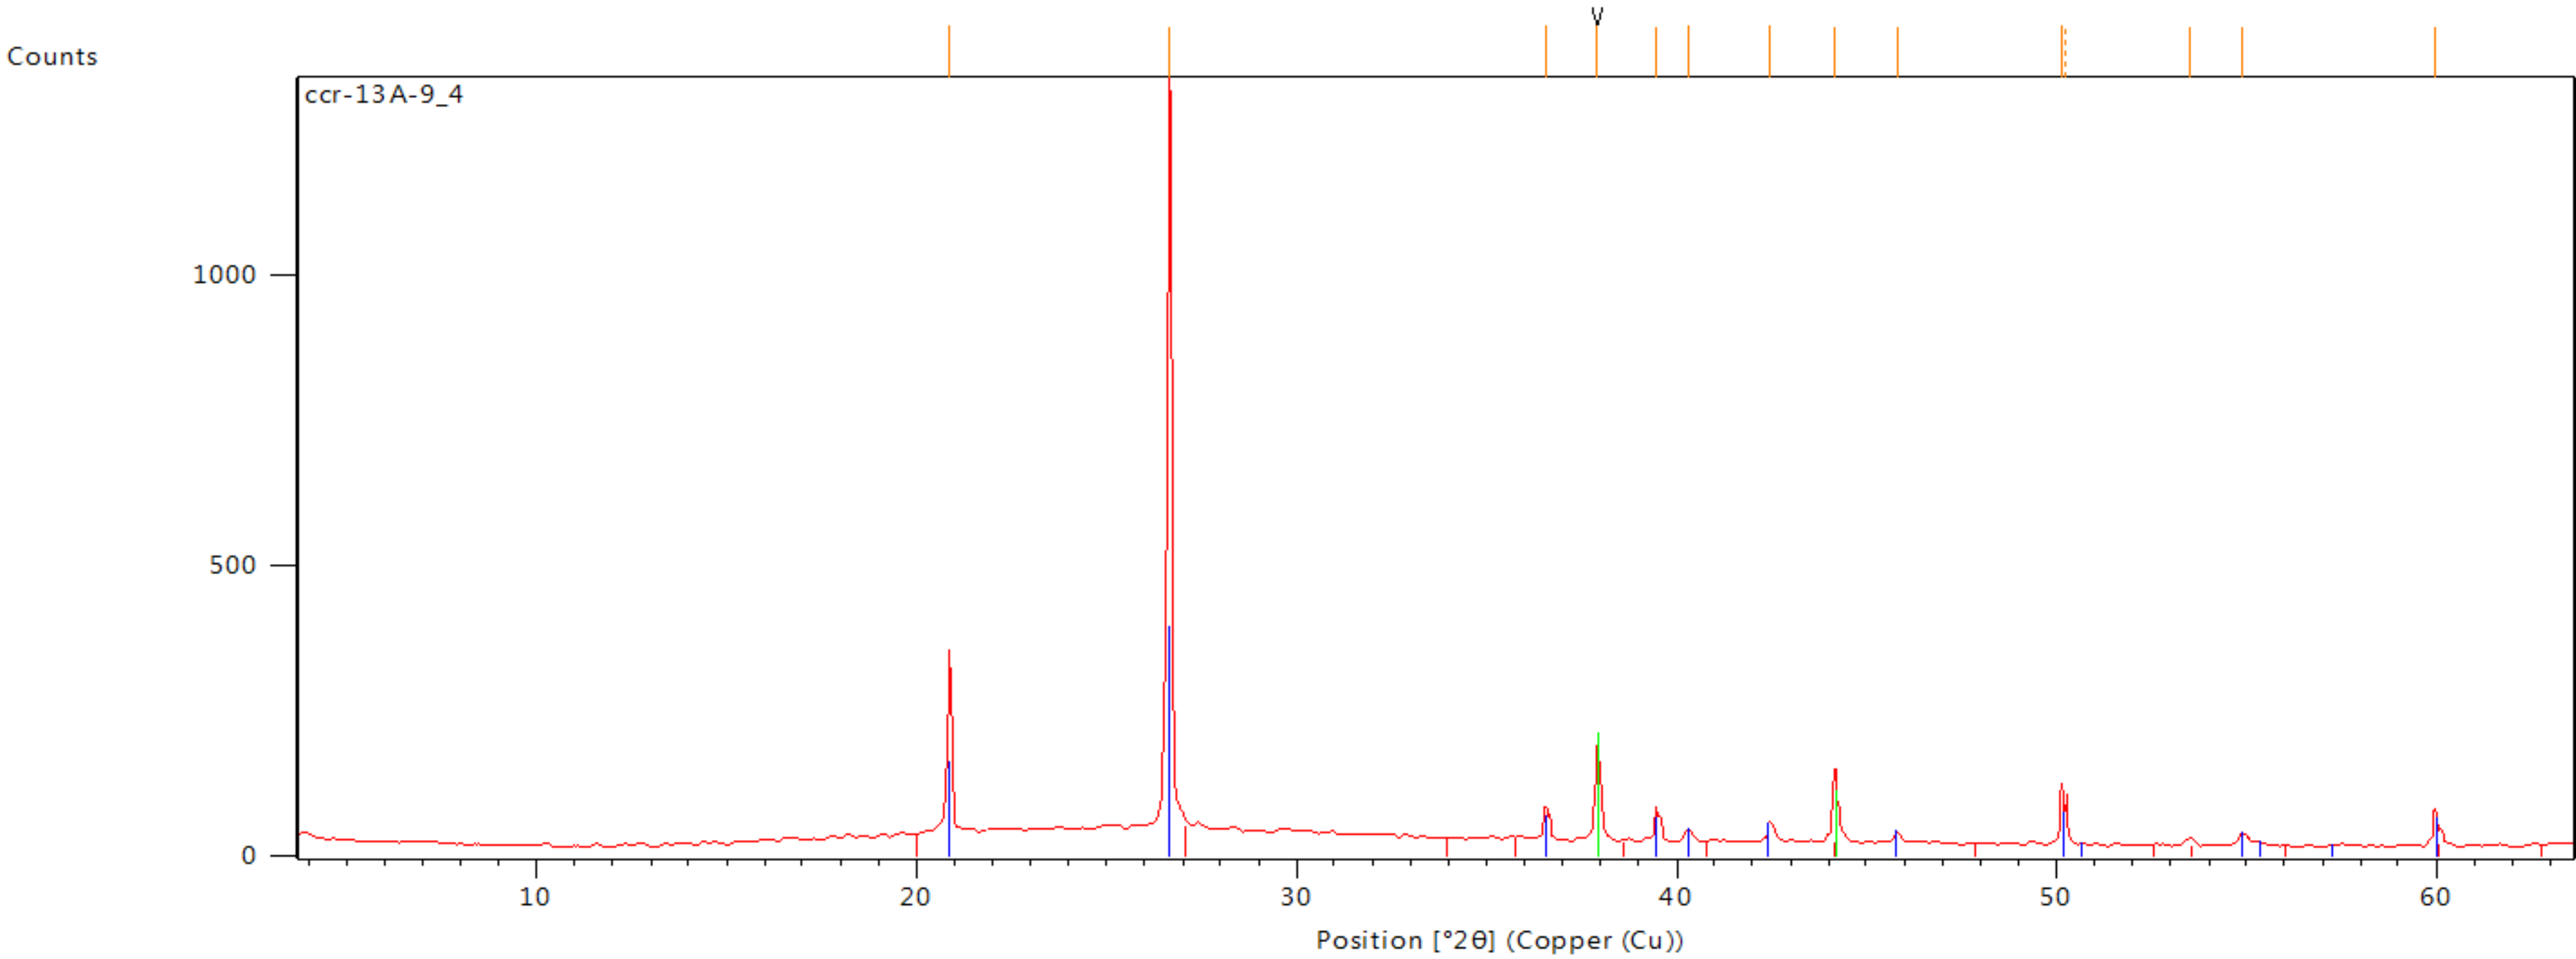


Peak List	
00-005-0490; Quartz, low	
00-001-0679; Zircon	
00-004-0787; Aluminum, syn [NR]	

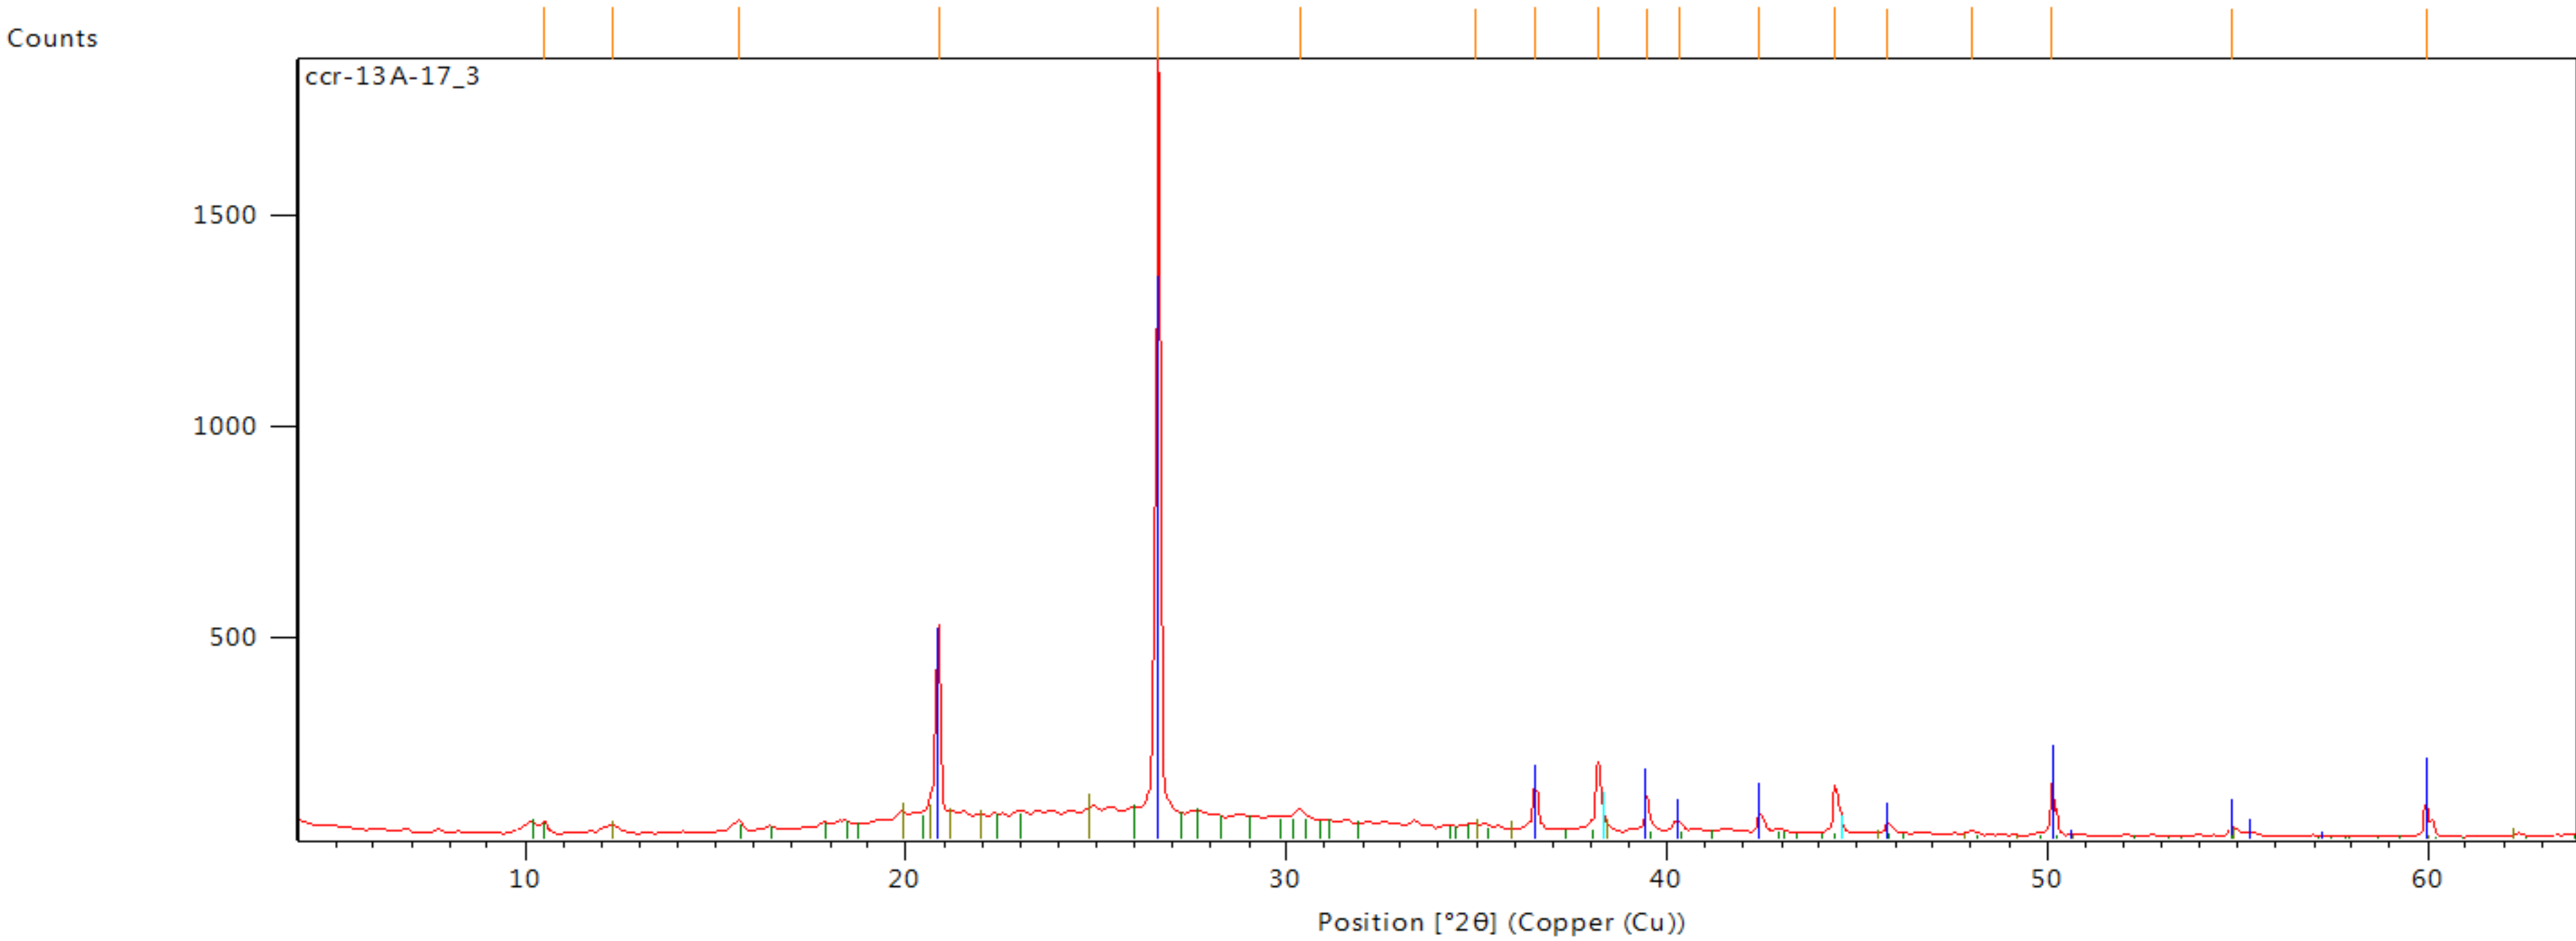

Peak List
00-005-0490; Quartz, low
00-004-0787; Aluminum, syn [NR]
00-027-0019; Wavellite
00-001-0527; Kaolinite

Counts

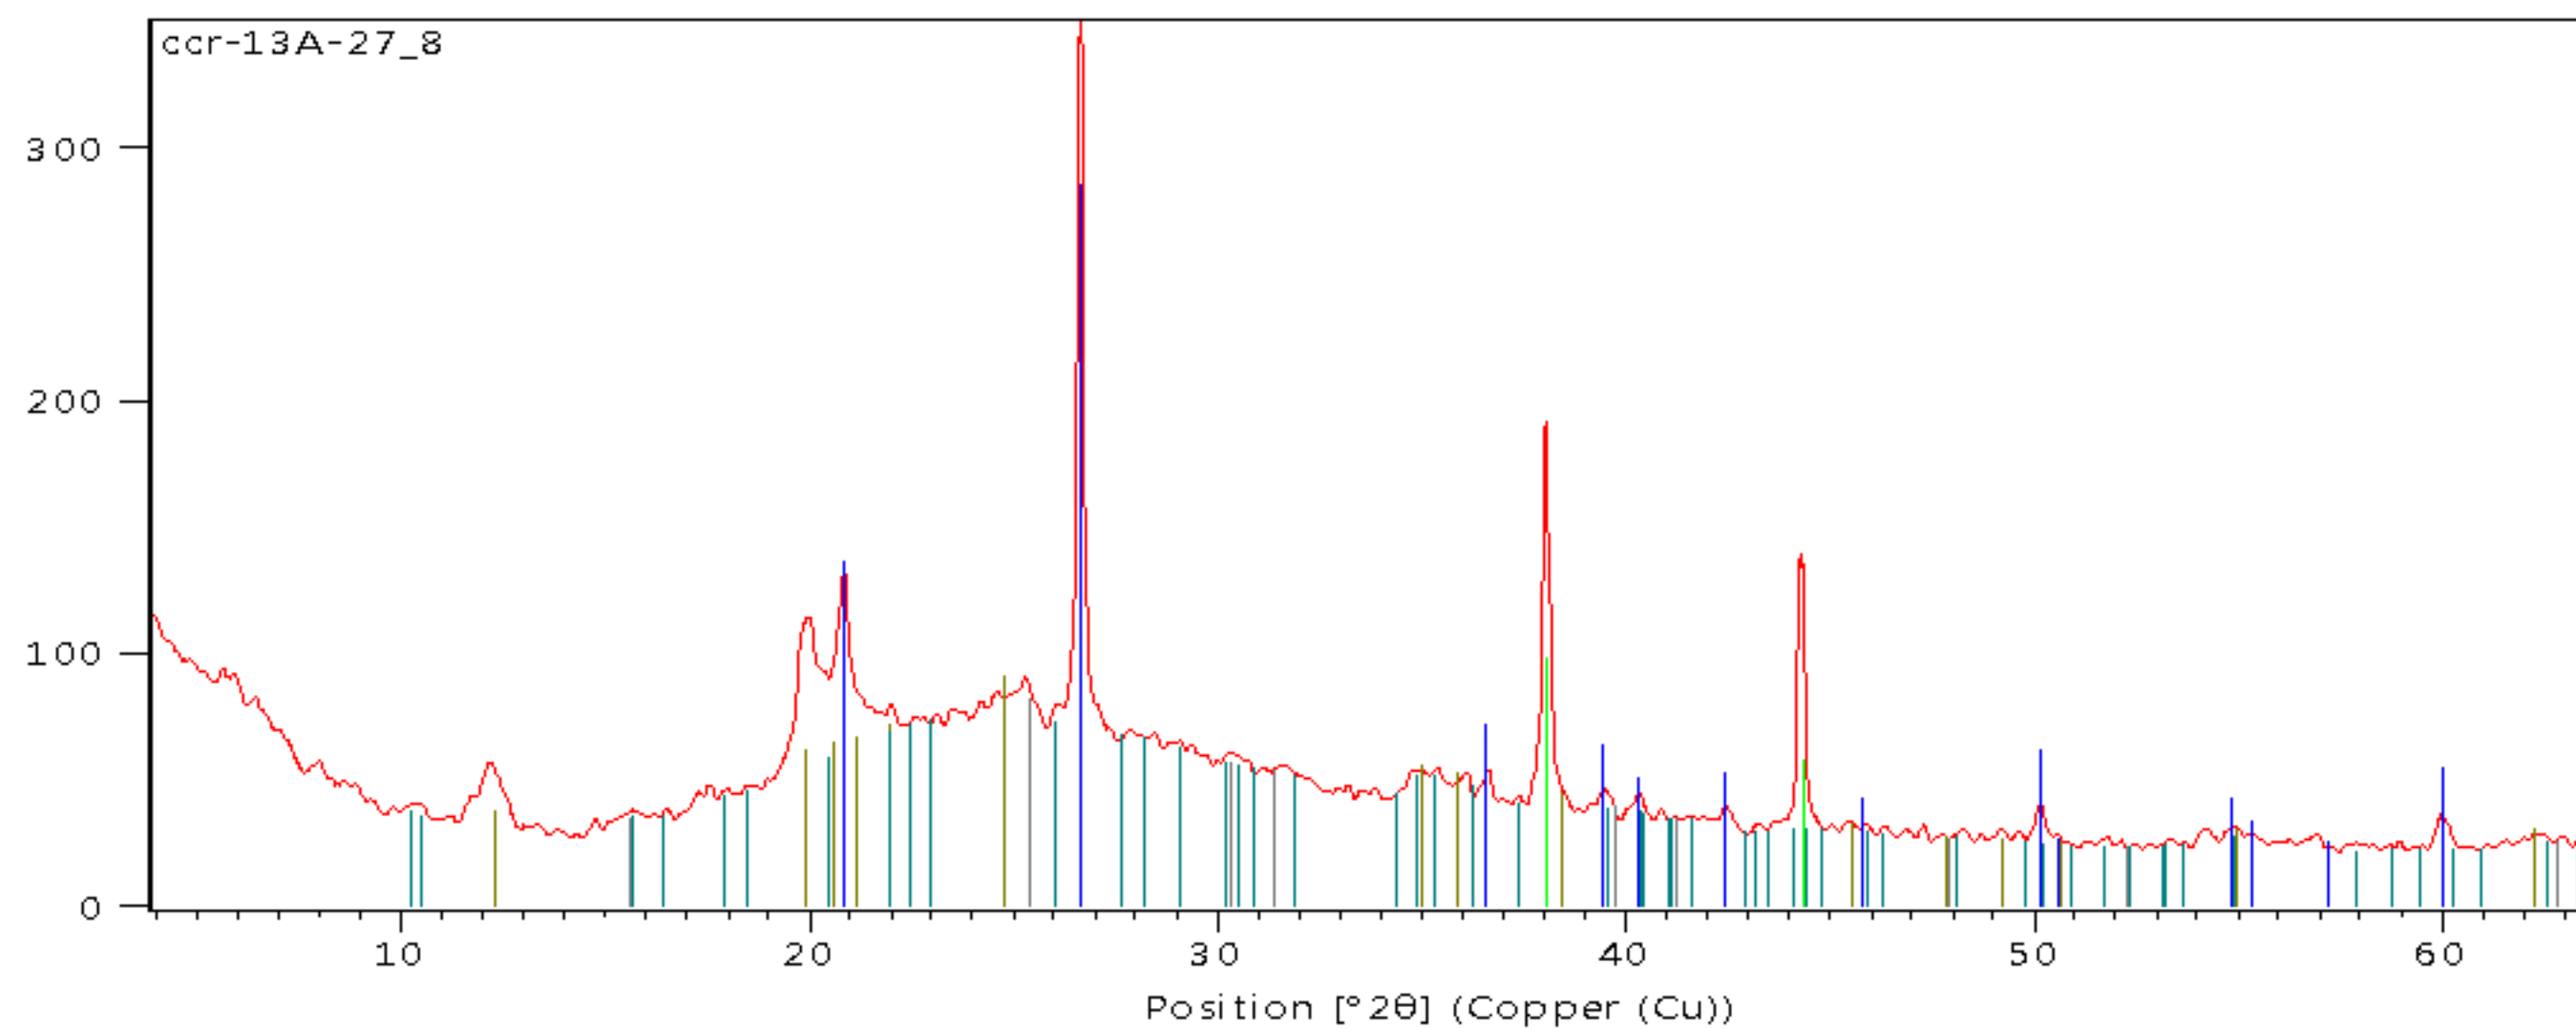

Peak List


00-001-0527; Kaolinite

00-025-0020; Wavellite


00-005-0490; Quartz, low

00-004-0787; Aluminum, syn [NR]


00-026-0991; Eylettersite

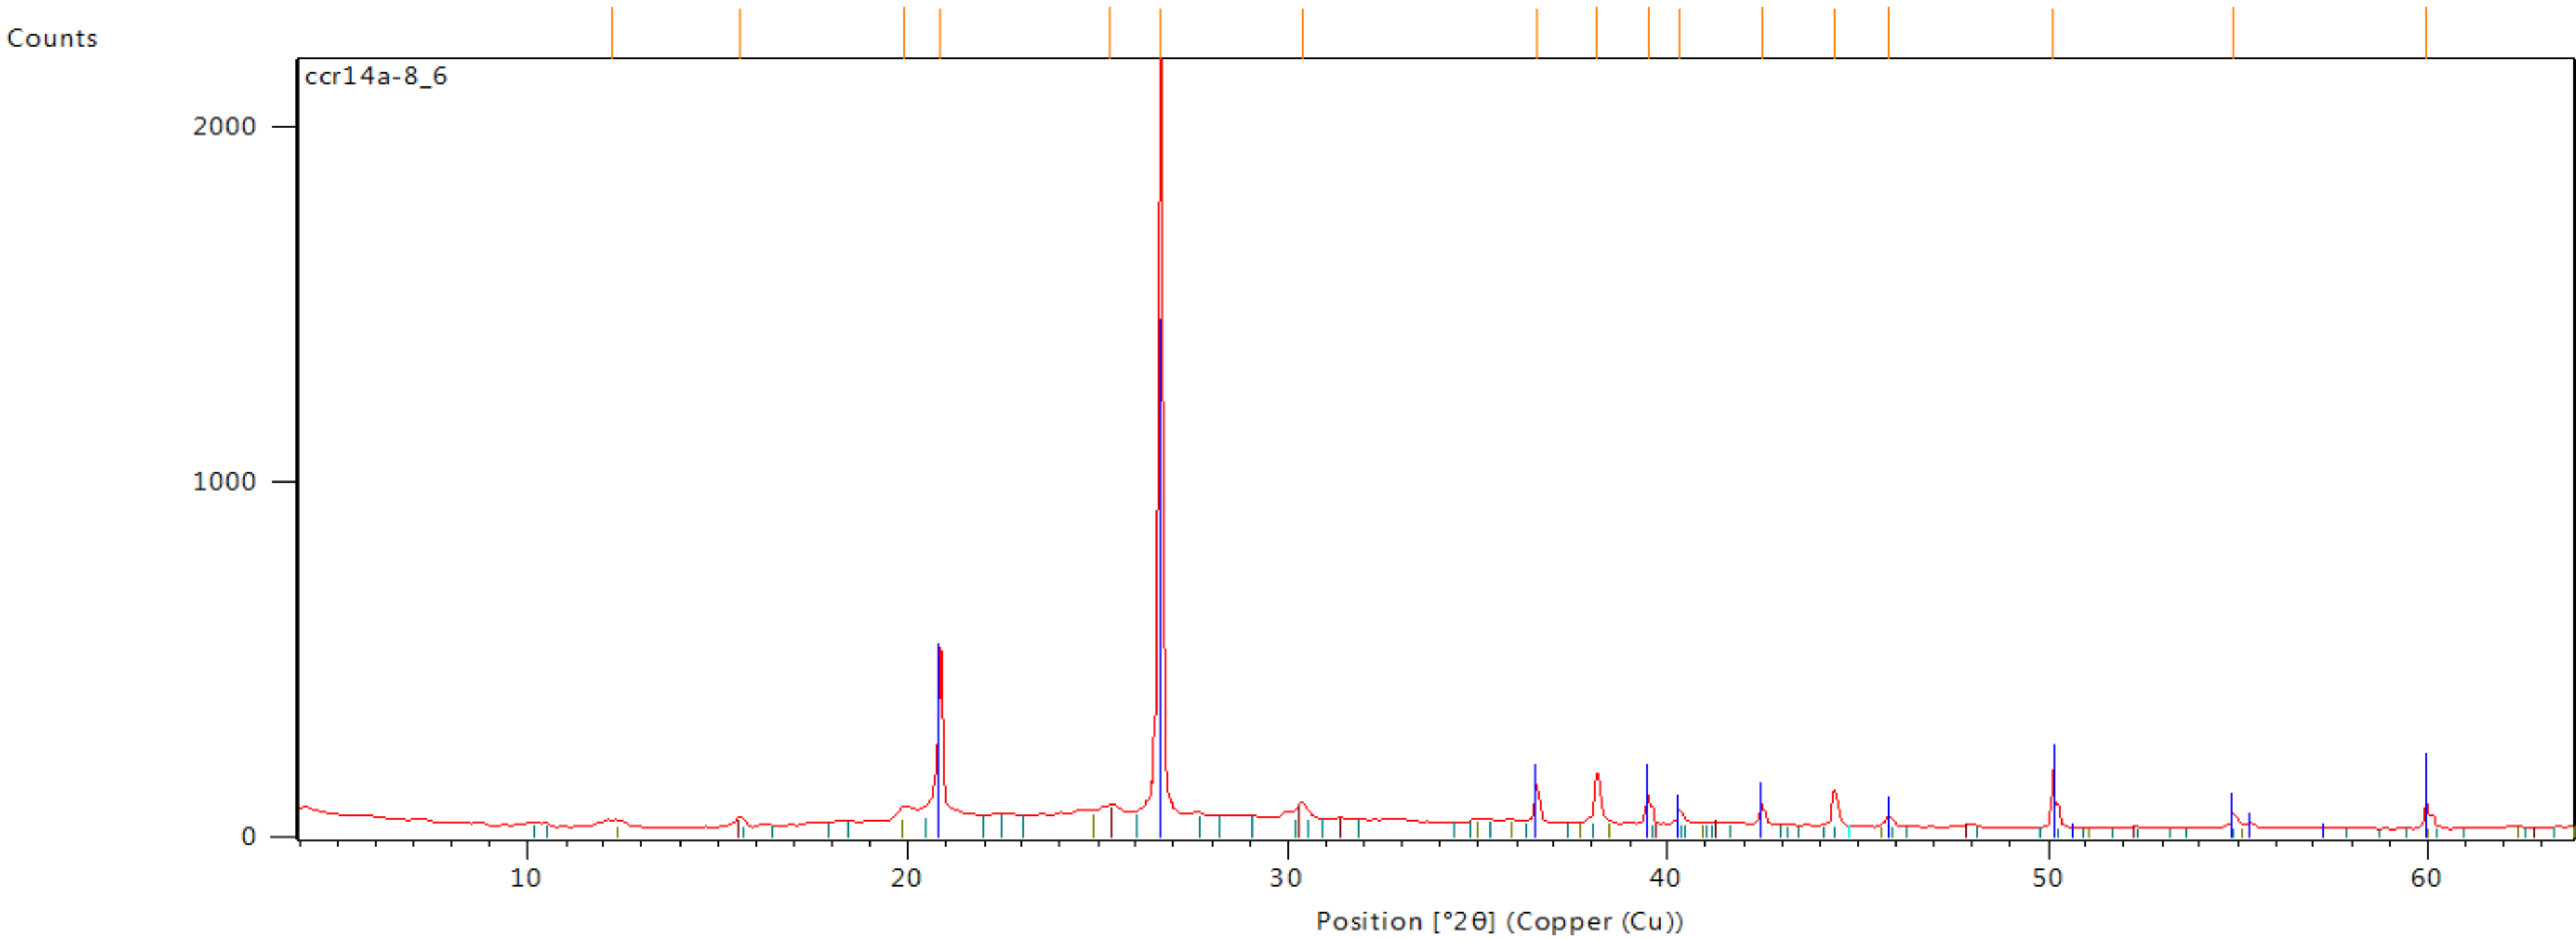

Peak List	
00-025-0020; Wavellite	
00-026-0991; Eylattersite	
00-005-0490; Quartz, low	
00-004-0787; Aluminum, syn [NR]	
00-006-0221; Kaolinite 1Md	

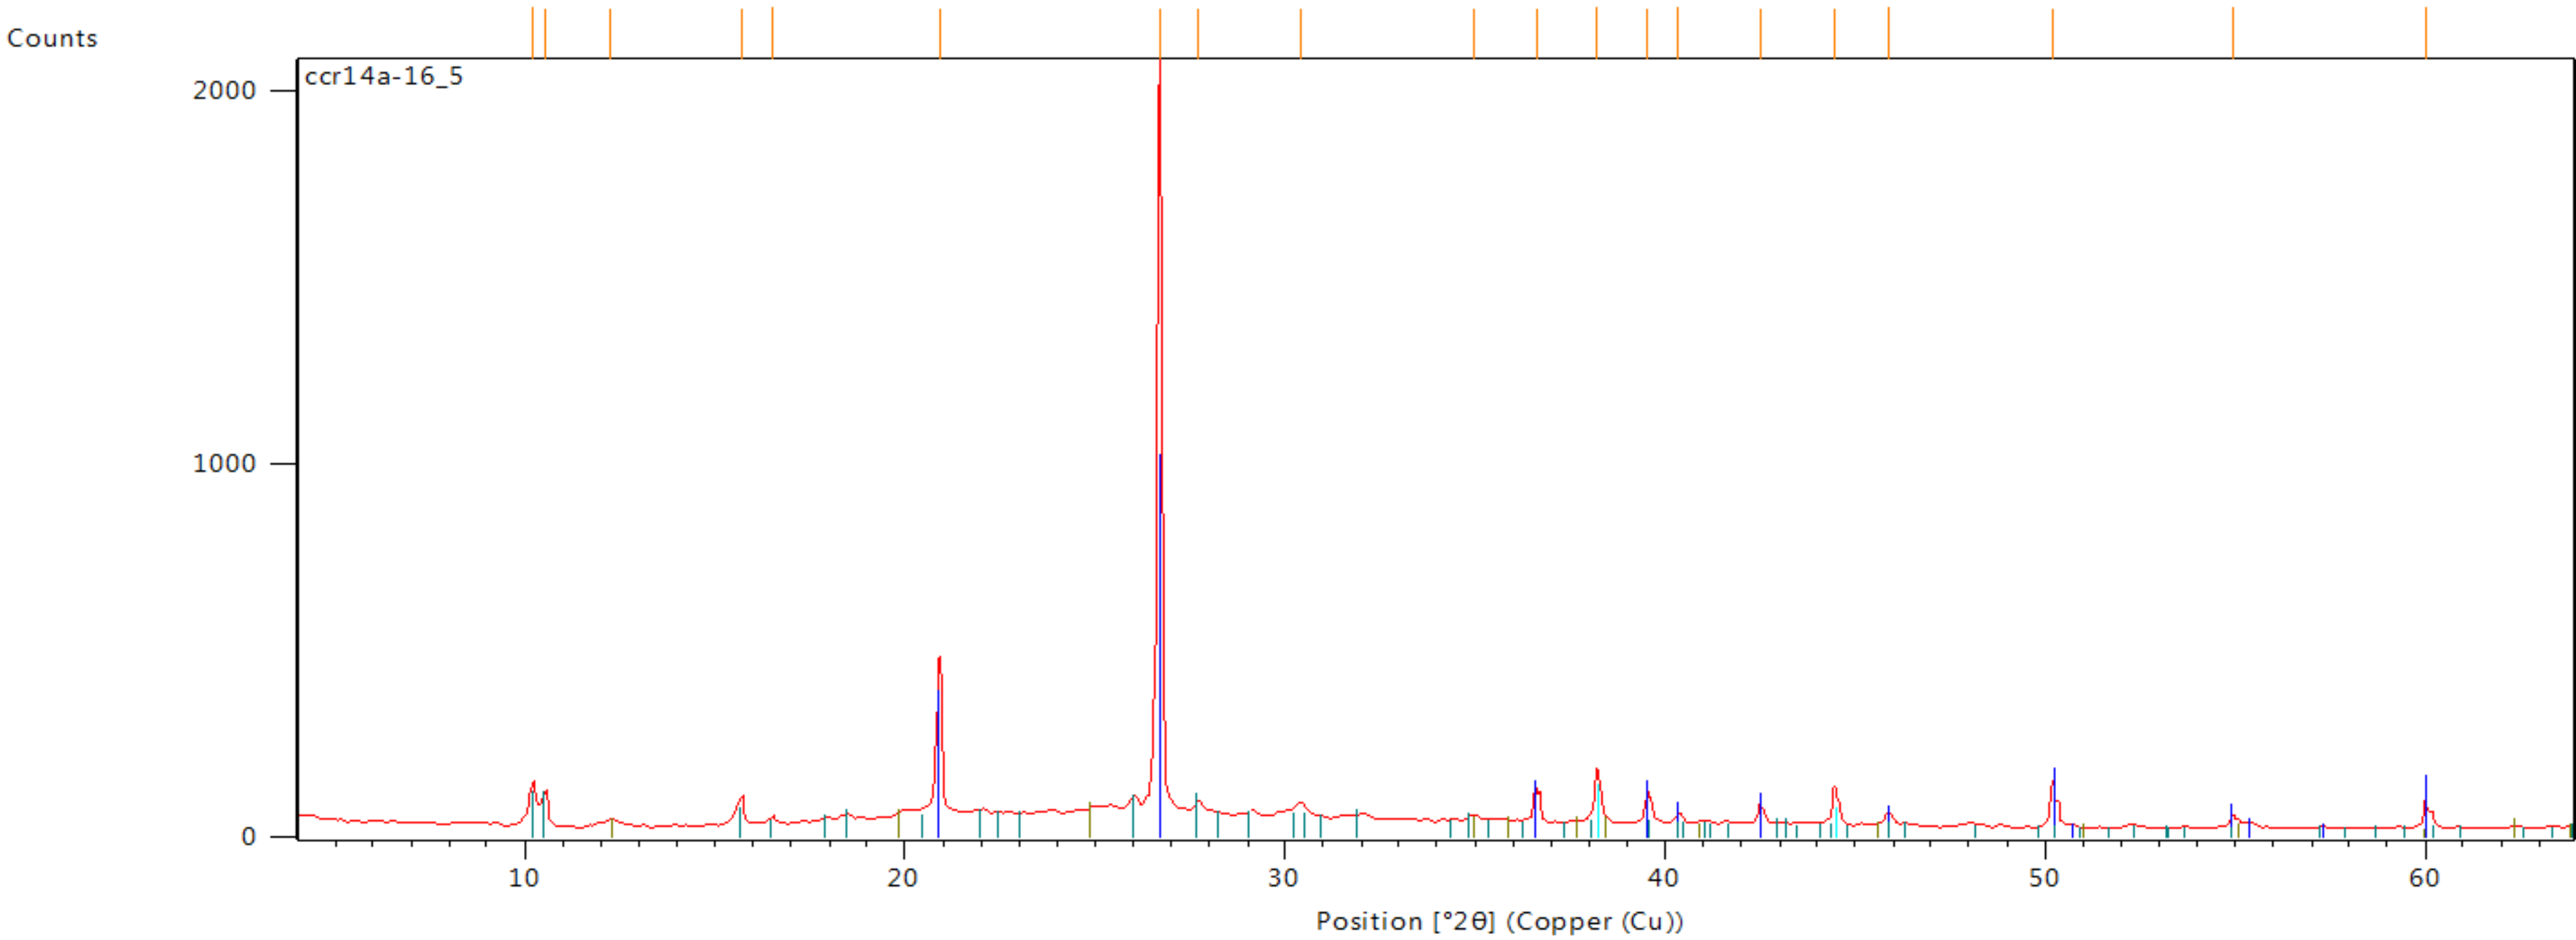

Peak List	
00-005-0490; Quartz, low	
00-006-0221; Kaolinite 1Md	
00-004-0787; Aluminum, syn [NR]	
00-025-0020; Wavellite	

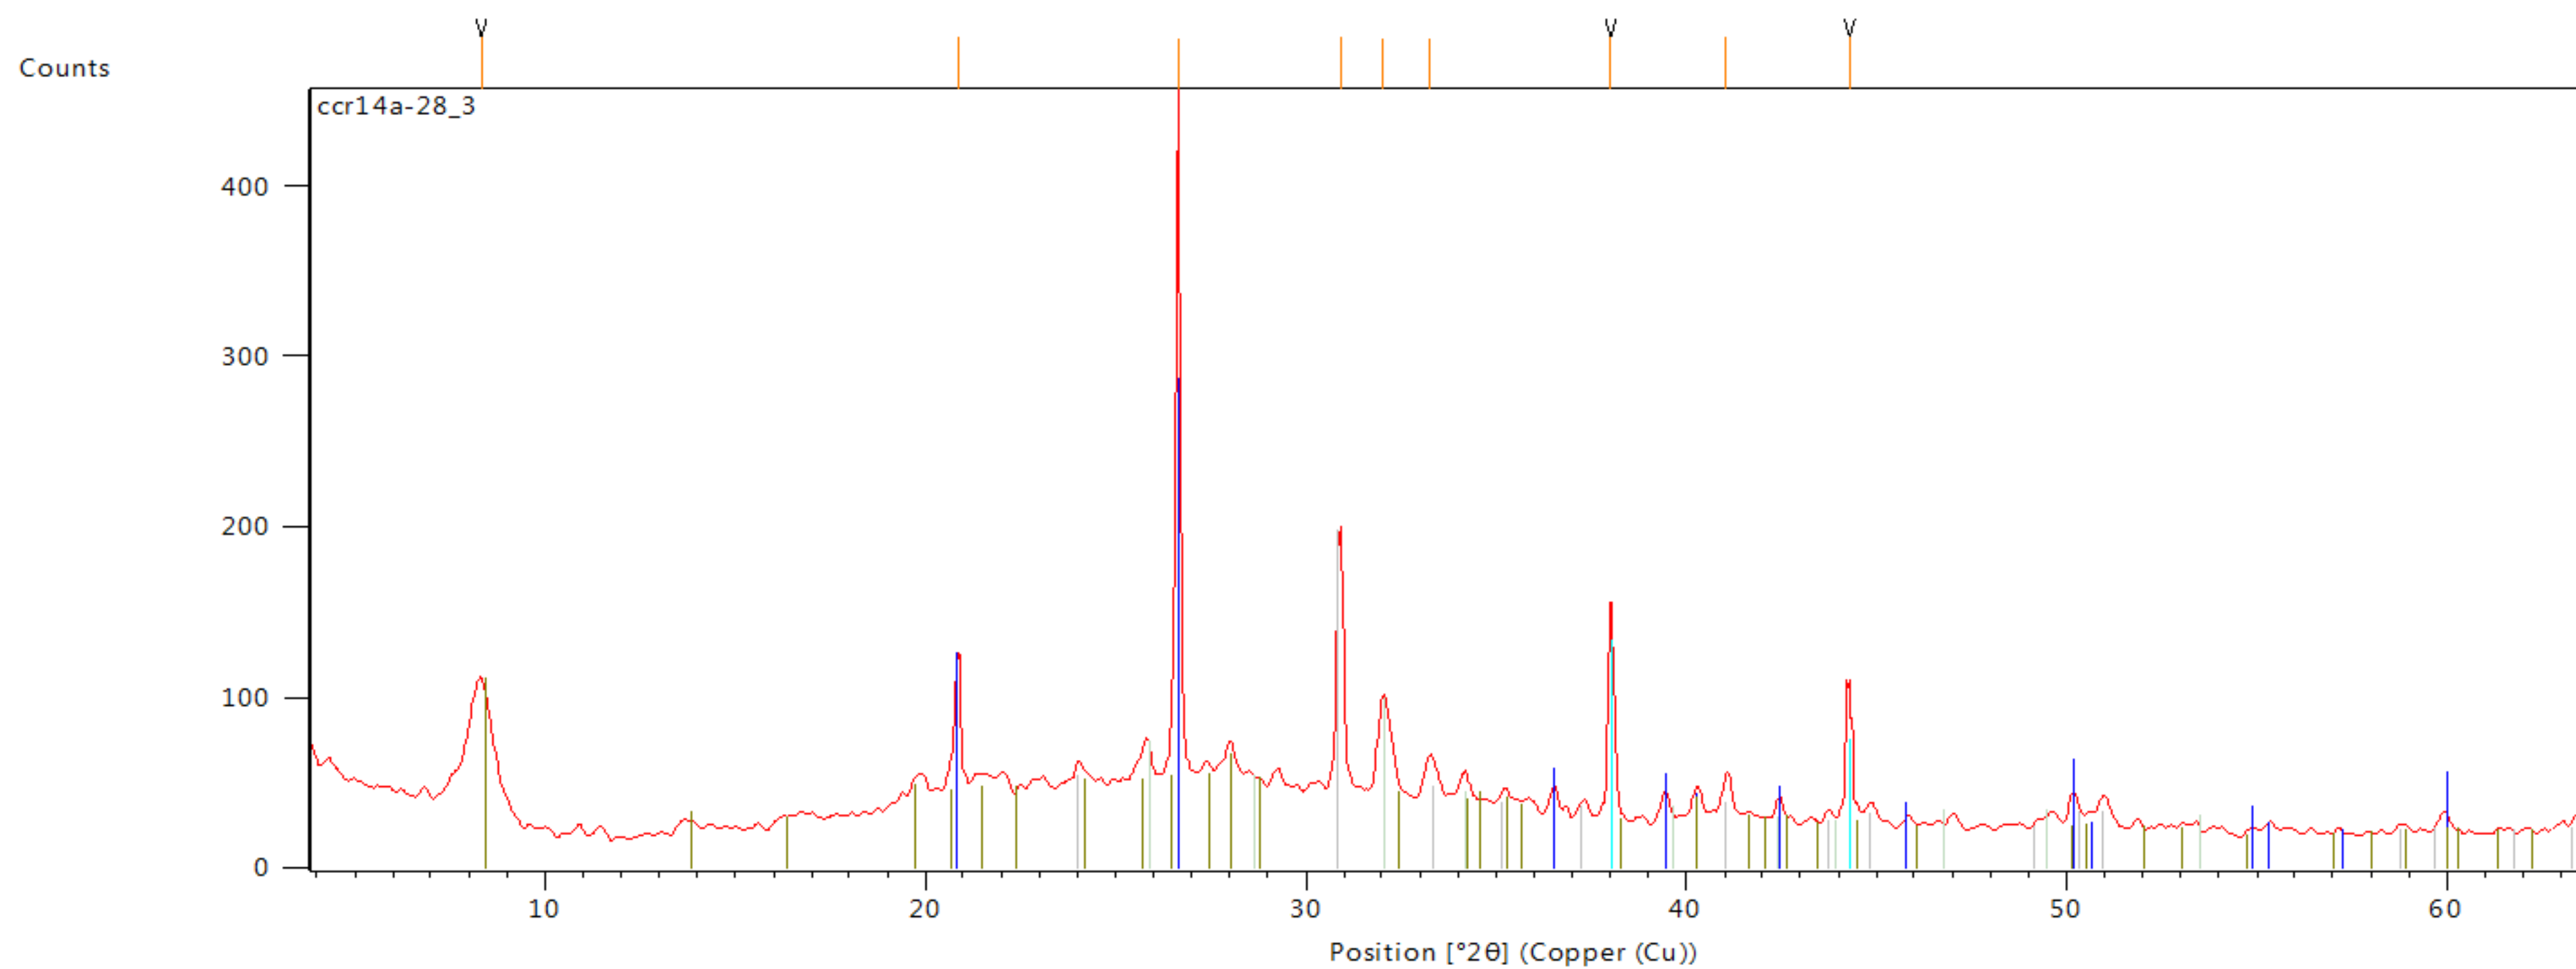

Peak List
00-004-0787; Aluminum, syn [NR]
00-005-0490; Quartz, low
00-029-0855; Palygorskite
00-034-0517; Dolomite, ferroan
00-001-1008; Hydroxyapatite

PetroLOGIC Solutions, Inc.

3997 Oak Hill Road
Douglasville, GA 30135
Tel: (678) 313-4146
email: rlkath@comcast.net



ATTACHMENT 3
GEOCHEMISTRY DATA

Lakeland Electric

	Al ₂ O ₃	TiO ₂	Fe ₂ O ₃	MgO	MnO	CaO	K ₂ O	NaO	P ₂ O ₅
<i>Sample Number</i>	wt%	wt%	wt%	wt%	wt%	wt%	wt%	wt%	wt%
CCR2A 18.7-19	1.37	1.34	0.35	<MDL	0.01	0.10	0.06	0.01	0.47
CCR2A 23-23.5	9.22	1.06	0.50	0.05	0.01	0.51	0.13	0.02	2.29
CCR4A 12.5-12.8	0.42	0.50	0.08	<MDL	0.00	0.19	0.03	<MDL	0.05
CCR4A 17-17.4	3.75	0.62	0.13	0.05	0.00	0.20	0.06	0.02	0.67
CCR4A 26.1-26.4	9.12	0.36	0.45	0.10	0.01	23.38	0.36	0.13	>2.30
CCR5A 19.3-20	1.11	0.31	0.06	<MDL	0.00	0.13	0.04	0.03	0.22
CCR5A 22.3-22.6	9.32	0.42	0.34	0.05	0.00	0.48	0.10	0.03	1.10
CCR7A 7-7.4	0.59	0.51	0.10	<MDL	0.00	0.20	<MDL	<MDL	0.11
CCR7A 14.6-15	0.73	0.62	0.13	<MDL	0.01	0.08	<MDL	<MDL	0.16
CCR7A 23.2-23.5	8.70	0.51	0.71	0.05	0.00	0.90	0.07	0.20	>2.30
CCR13A 9.4-10	0.54	0.94	0.12	<MDL	0.00	0.41	<MDL	<MDL	0.13
CCR13A 17.3-17.6	4.12	0.36	0.16	0.03	0.00	0.26	0.05	<MDL	1.29
CCR13A 27.8-28.2	17.87	0.68	1.41	0.81	0.01	0.59	0.66	0.05	>2.30
CCR14A 8.6-8.8	7.61	0.46	0.42	0.14	0.00	1.05	0.13	0.02	2.13
CCR14A 16.5-18	11.95	0.53	0.50	0.08	0.01	0.72	0.18	0.02	>2.30
CCR14A 28.3-28.6	2.99	0.17	3.37	6.37	0.02	20.09	0.43	0.26	>2.30

	Ag	As	Ba	Be	Bi	Ce	Cd	Co	Cr
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
CCR2A 18.7-19	0.27	0.30	128.00	0.17	0.29	57.9	<MDL	12.20	19.5
CCR2A 23-23.5	<MDL	<MDL	679.00	1.22	0.19	93.7	<MDL	10.10	42.9
CCR4A 12.5-12.8	<MDL	<MDL	6.00	0.01	0.03	6.1	<MDL	4.50	7.7
CCR4A 17-17.4	0.06	0.30	137.00	0.20	0.12	39.4	0.05	5.70	19.2
CCR4A 26.1-26.4	0.34	3.40	131.00	1.80	0.13	69.8	42.65	3.30	136.1
CCR5A 19.3-20	<MDL	<MDL	39.00	0.05	0.03	13.2	<MDL	2.80	6.6
CCR5A 22.3-22.6	0.06	0.70	617.00	1.22	0.31	60.0	0.16	10.30	49.6
CCR7A 7-7.4	0.14	0.60	18.00	0.05	0.05	12.3	<MDL	23.30	7.9
CCR7A 14.6-15	0.07	<MDL	12.00	0.05	0.02	10.1	<MDL	14.50	10.1
CCR7A 23.2-23.5	<MDL	<MDL	516.00	0.93	0.14	60.0	0.42	21.20	50.5
CCR13A 9.4-10	0.27	0.40	45.00	0.04	0.18	37.9	<MDL	18.40	11.4
CCR13A 17.3-17.6	0.14	<MDL	189.00	0.49	0.06	39.3	<MDL	20.10	23.4
CCR13A 27.8-28.2	0.48	0.20	136.00	1.58	0.30	64.7	0.12	15.10	162.8
CCR14A 8.6-8.8	0.22	<MDL	377.00	1.47	0.27	81.5	0.54	18.80	48.4
CCR14A 16.5-18	0.91	0.60	673.00	4.24	0.32	138.8	0.31	21.90	112.3
CCR14A 28.3-28.6	1.01	5.30	81.00	0.69	0.11	25.3	35.09	11.30	84.3

<MDL less than method detection limit

Lakeland Electric

	Cs	Cu	Ga	Ge	Hf	In	La	Li	Mo
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
CCR2A 18.7-19	0.30	6.40	7.25	0.04	1.77	0.02	32.7	1.10	2.70
CCR2A 23-23.5	0.70	2.60	11.27	0.08	1.84	0.03	50.1	3.90	2.10
CCR4A 12.5-12.8	<MDL	1.50	2.04	<MDL	0.51	<MDL	2.4	0.70	1.70
CCR4A 17-17.4	0.40	3.40	6.76	0.03	1.09	0.03	20.7	4.20	2.20
CCR4A 26.1-26.4	1.50	8.50	10.30	0.06	1.76	0.06	63.2	3.20	2.30
CCR5A 19.3-20	0.10	0.90	2.41	0.02	0.44	0.01	6.5	6.10	1.10
CCR5A 22.3-22.6	0.40	1.40	9.16	0.05	1.44	0.07	30.6	7.50	1.50
CCR7A 7-7.4	<MDL	1.30	2.21	0.01	0.65	0.01	4.5	1.80	1.50
CCR7A 14.6-15	<MDL	2.00	2.81	0.01	0.55	0.02	4.0	1.20	1.60
CCR7A 23.2-23.5	0.30	1.20	10.57	0.06	1.55	0.04	31.8	7.00	2.10
CCR13A 9.4-10	0.10	3.10	3.95	<MDL	1.60	0.01	20.1	2.20	4.10
CCR13A 17.3-17.6	0.30	2.20	5.30	0.05	1.06	0.02	21.3	6.40	0.90
CCR13A 27.8-28.2	4.20	6.50	19.57	0.05	5.21	0.16	39.0	20.60	2.10
CCR14A 8.6-8.8	1.00	4.00	9.10	0.06	3.10	0.05	45.2	5.40	1.30
CCR14A 16.5-18	1.00	11.60	11.94	0.12	2.97	0.06	83.6	3.00	1.70
CCR14A 28.3-28.6	1.20	1.30	4.03	0.04	0.78	0.01	21.3	8.30	2.80
	Nb	Ni	Pb	Rb	Re	S	Sb	Sc	Se
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
CCR2A 18.7-19	17.45	1.50	25.00	4.00	<MDL	245.0	0.37	2.7	0.30
CCR2A 23-23.5	16.51	6.90	29.00	6.00	<MDL	315.0	0.64	4.8	0.30
CCR4A 12.5-12.8	4.81	1.30	<MDL	<MDL	<MDL	219.0	0.13	0.9	0.40
CCR4A 17-17.4	10.05	6.30	13.00	3.00	<MDL	344.0	0.23	1.8	0.80
CCR4A 26.1-26.4	7.58	4.10	11.00	16.00	0.00	624.0	1.07	8.2	0.50
CCR5A 19.3-20	4.14	2.00	6.00	2.00	<MDL	112.0	0.10	0.7	<MDL
CCR5A 22.3-22.6	7.17	10.90	24.00	5.00	0.01	144.0	0.76	8.6	0.30
CCR7A 7-7.4	5.81	2.40	4.00	<MDL	0.03	<MDL	0.16	0.8	<MDL
CCR7A 14.6-15	6.32	1.30	4.00	<MDL	0.02	142.0	0.13	0.9	<MDL
CCR7A 23.2-23.5	9.17	10.70	22.00	3.00	0.03	261.0	0.35	5.9	1.30
CCR13A 9.4-10	14.68	1.60	16.00	<MDL	0.02	218.0	0.41	1.5	0.80
CCR13A 17.3-17.6	6.31	4.70	12.00	3.00	0.03	291.0	0.29	2.3	0.30
CCR13A 27.8-28.2	15.13	21.20	21.00	41.00	0.01	270.0	1.24	82.1	<MDL
CCR14A 8.6-8.8	8.44	10.00	26.00	8.00	0.03	345.0	0.39	18.2	0.20
CCR14A 16.5-18	10.31	5.70	31.00	10.00	0.03	534.0	0.45	13.5	0.20
CCR14A 28.3-28.6	3.66	56.60	6.00	20.00	0.01	1645.0	1.41	2.7	0.50
	Sn	Sr	Ta	Te	Th	Tl	U	V	W
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
CCR2A 18.7-19	1.40	207.0	1.64	0.08	8.5	0.03	5.0	19.00	1.2
CCR2A 23-23.5	1.30	929.0	1.09	0.03	12.9	0.22	50.4	59.00	1.1
CCR4A 12.5-12.8	0.90	12.0	0.66	0.01	1.7	<MDL	1.2	6.00	0.5
CCR4A 17-17.4	1.50	227.0	1.65	0.03	6.8	0.04	5.3	16.00	0.9
CCR4A 26.1-26.4	1.50	308.0	0.12	0.05	9.7	0.50	185.5	119.00	0.8
CCR5A 19.3-20	0.60	63.0	0.46	<MDL	2.1	0.01	4.1	5.00	0.4
CCR5A 22.3-22.6	1.10	748.0	0.06	0.02	8.2	0.10	34.2	35.00	66.3
CCR7A 7-7.4	0.80	30.0	0.60	<MDL	1.7	<MDL	1.4	6.00	184.8
CCR7A 14.6-15	0.80	18.0	0.69	0.01	2.0	<MDL	0.9	6.00	97.1
CCR7A 23.2-23.5	1.20	786.0	<MDL	0.03	8.8	0.04	35.0	33.00	173.9
CCR13A 9.4-10	1.10	91.0	1.44	0.01	4.8	0.03	3.0	13.00	104.3
CCR13A 17.3-17.6	0.50	458.0	0.30	0.01	6.3	0.08	22.4	25.00	175.2
CCR13A 27.8-28.2	2.50	210.0	0.12	0.02	23.4	1.00	164.4	247.00	77.8
CCR14A 8.6-8.8	0.90	815.0	0.18	0.02	11.4	0.23	96.2	50.00	153.1
CCR14A 16.5-18	1.50	1185.0	1.04	<MDL	16.6	0.28	467.0	48.00	185.1
CCR14A 28.3-28.6	0.80	461.0	<MDL	<MDL	4.0	0.60	34.8	123.00	37.0

<MDL less than method detection limit

	Y	Zn	Zr
	ppm	ppm	ppm
<i>CCR2A 18.7-19</i>	12.10	4.00	71.0
<i>CCR2A 23-23.5</i>	49.30	11.00	70.2
<i>CCR4A 12.5-12.8</i>	1.10	<MDL	17.6
<i>CCR4A 17-17.4</i>	9.40	4.00	37.7
<i>CCR4A 26.1-26.4</i>	96.30	87.00	51.8
<i>CCR5A 19.3-20</i>	3.00	<MDL	15.9
<i>CCR5A 22.3-22.6</i>	33.30	7.00	44.0
<i>CCR7A 7-7.4</i>	2.20	4.00	42.5
<i>CCR7A 14.6-15</i>	1.40	4.00	30.7
<i>CCR7A 23.2-23.5</i>	25.80	7.00	60.9
<i>CCR13A 9.4-10</i>	6.80	3.00	76.1
<i>CCR13A 17.3-17.6</i>	17.00	5.00	43.5
<i>CCR13A 27.8-28.2</i>	33.90	49.00	167.2
<i>CCR14A 8.6-8.8</i>	48.90	12.00	93.3
<i>CCR14A 16.5-18</i>	93.50	10.00	94.2
<i>CCR14A 28.3-28.6</i>	30.70	49.00	19.0

<MDL less than method detection limit



PetroLOGIC Solutions, Inc.

3997 Oak Hill Road
Douglasville, GA 30135
Tel: (678) 313-4146
email: rlkath@comcast.net





ATTACHMENT 4



SCANNING ELECTRON MICROSCOPY DATA

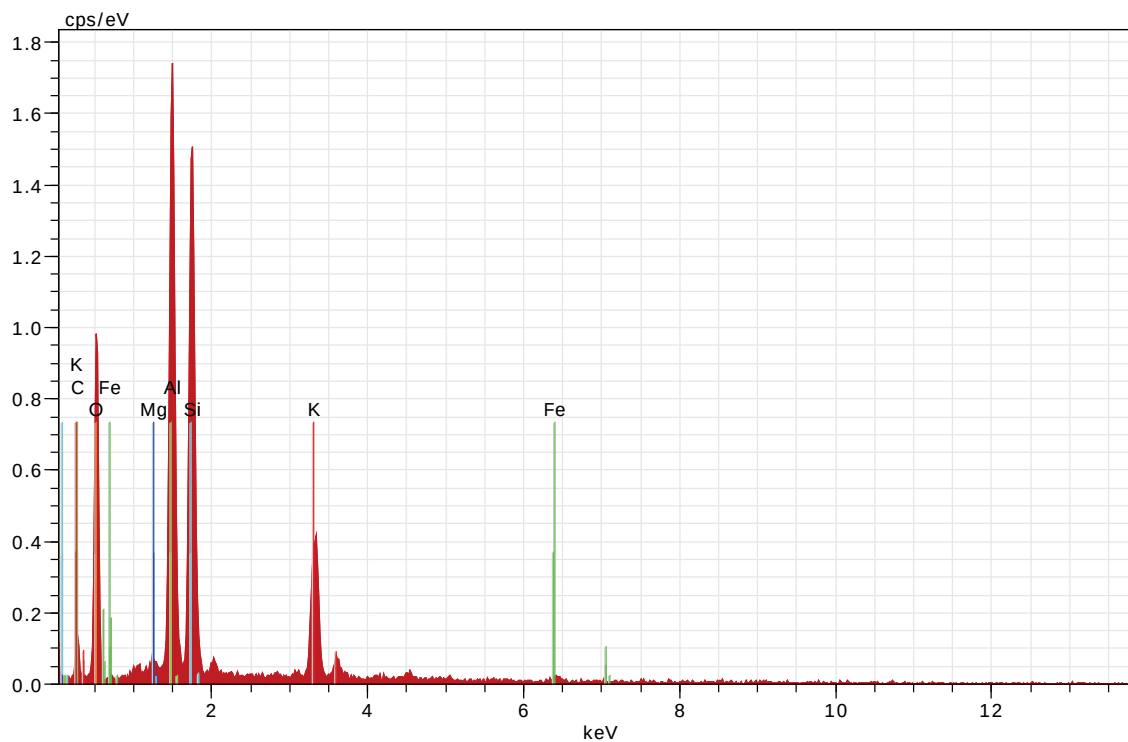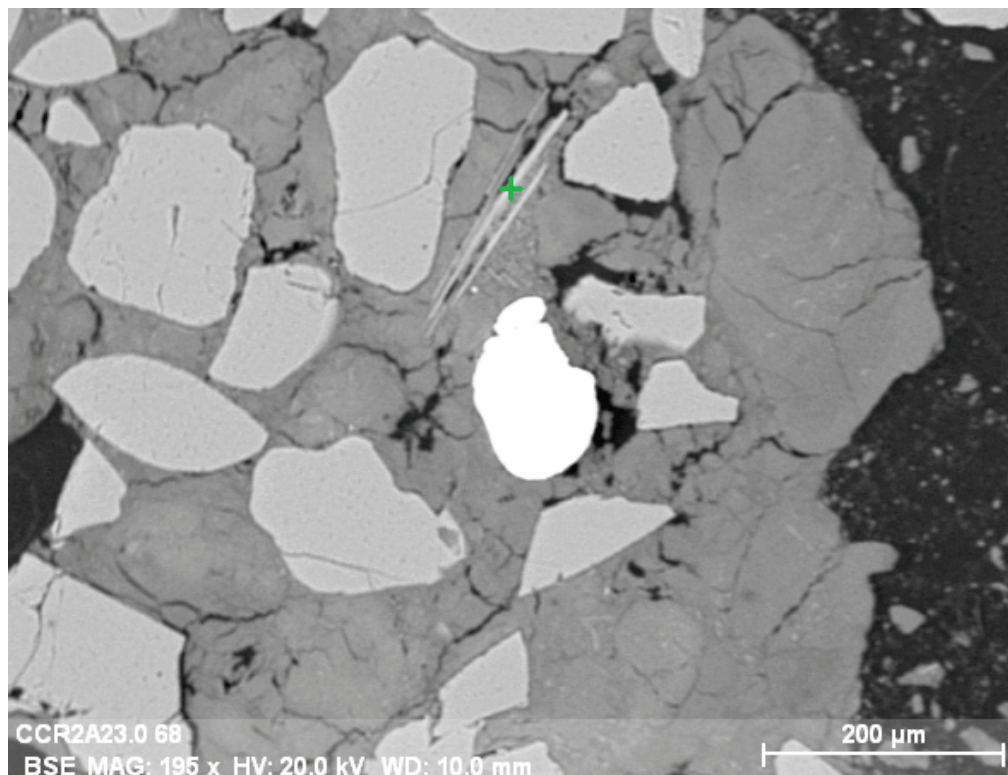



CCR2A 23.0-23.5: BSE image (top) and EDS spectrum (bottom) for muscovite; green crosshair on BSE image marks analysis location.

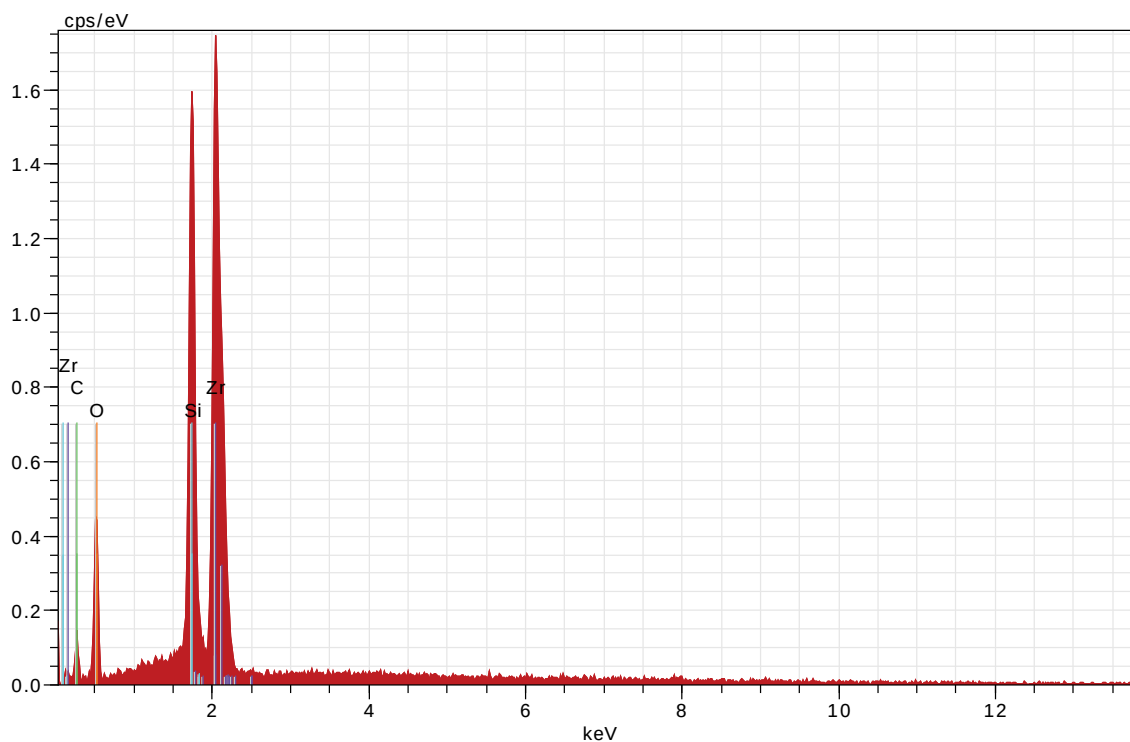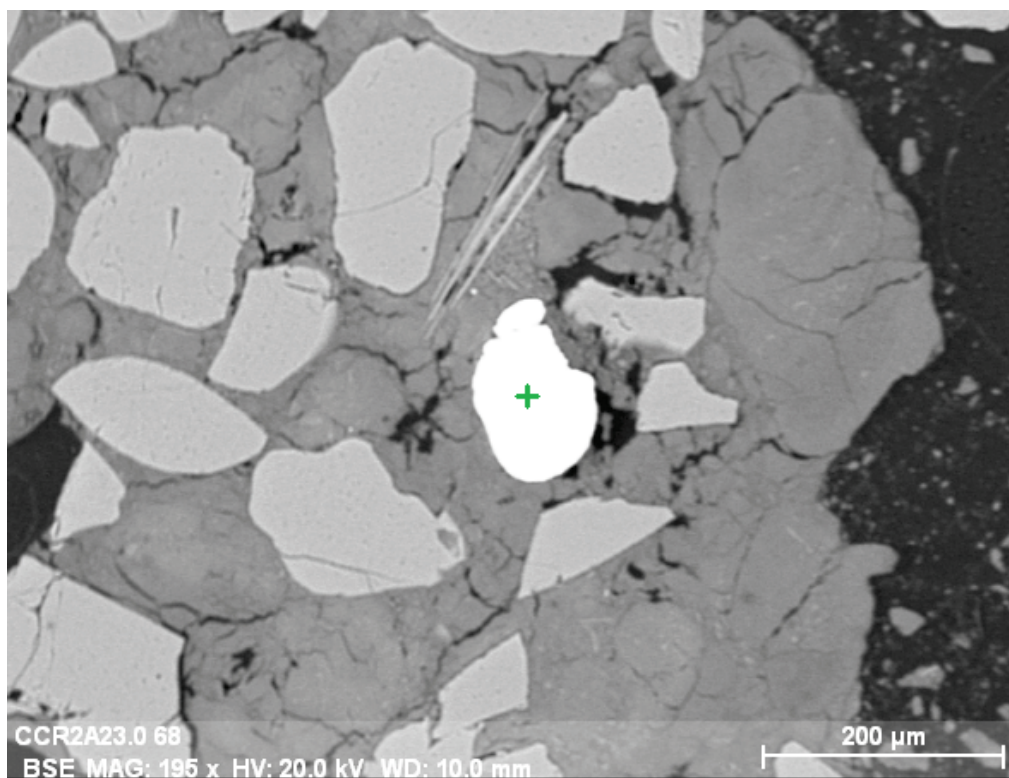



CCR2A 23.0-23.5: BSE image (top) and EDS spectrum (bottom) for zircon; green crosshair on BSE image marks analysis location.

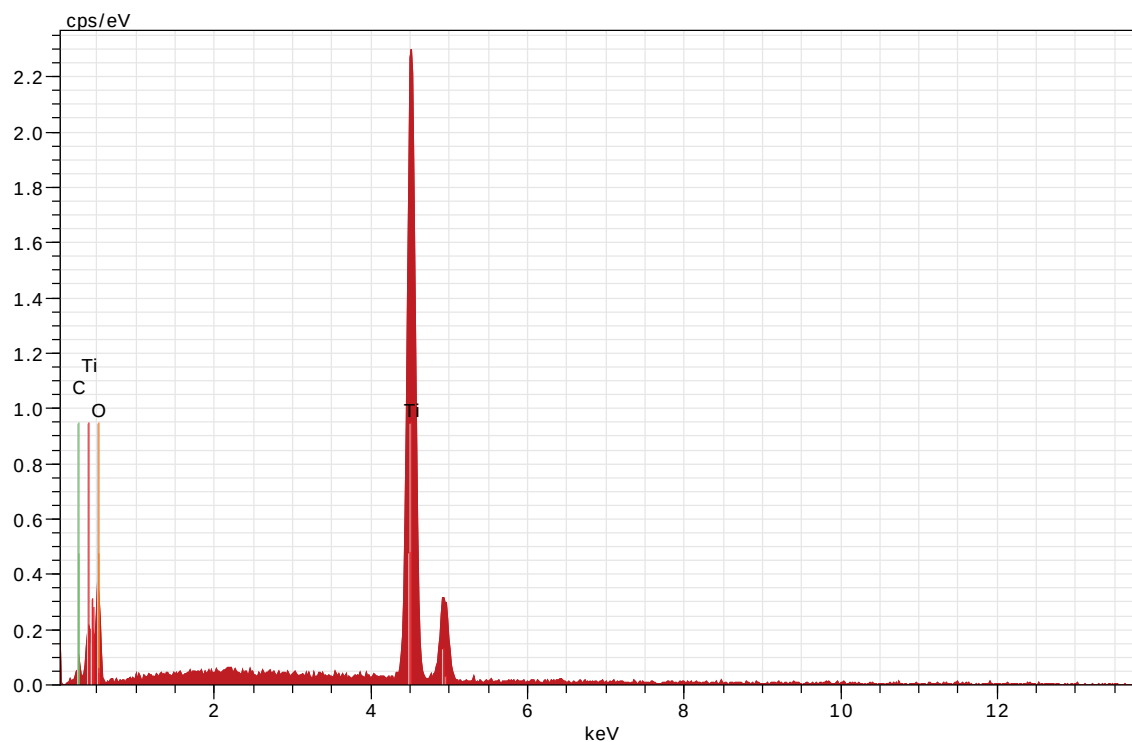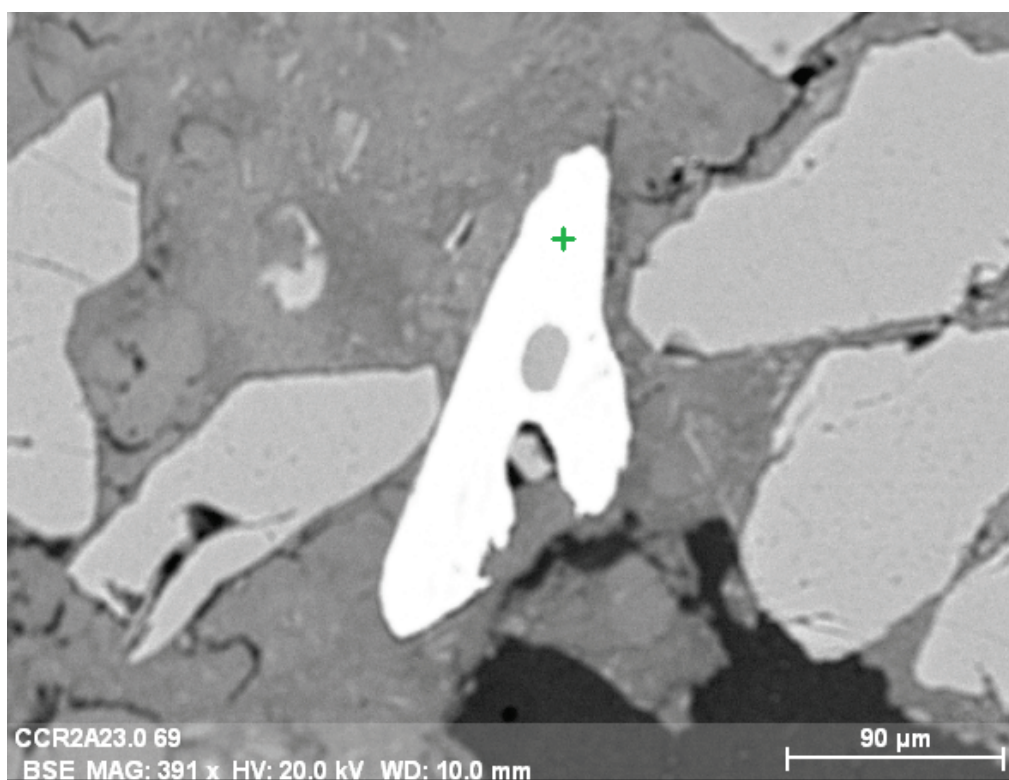



CCR2A 23.0-23.5: BSE image (top) and EDS spectrum (bottom) for rutile; green crosshair on BSE image marks analysis location.

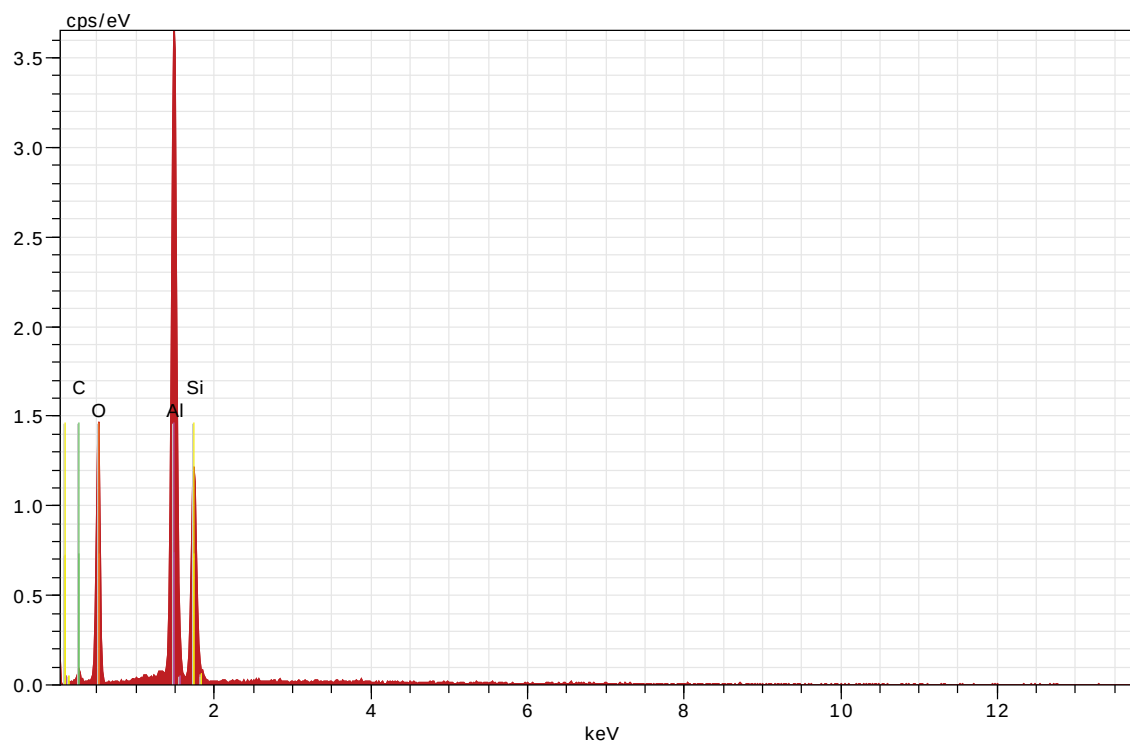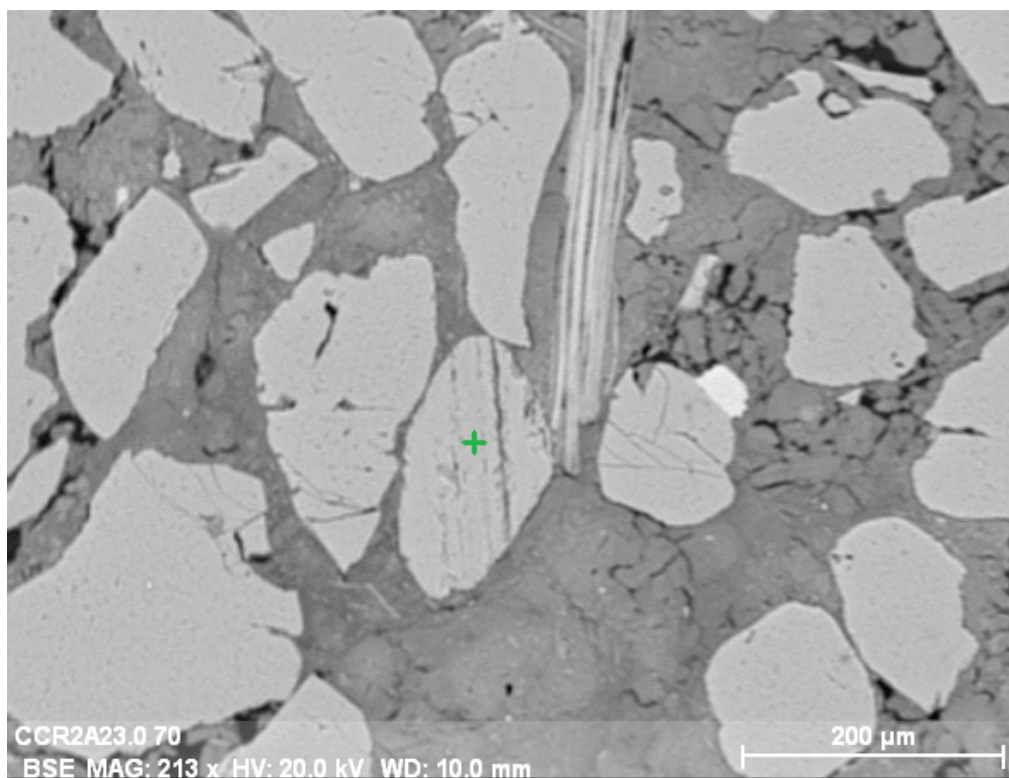



CCR2A 23.0-23.5: BSE image (top) and EDS spectrum (bottom) for kyanite; green crosshair on BSE image marks analysis location.

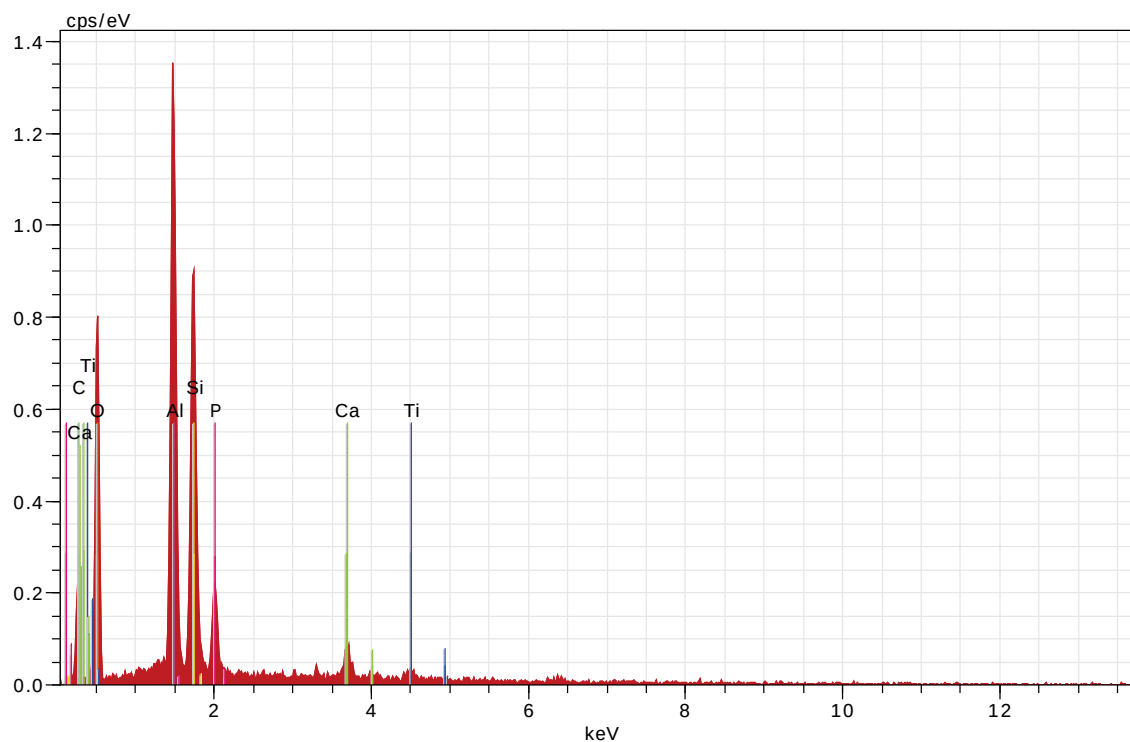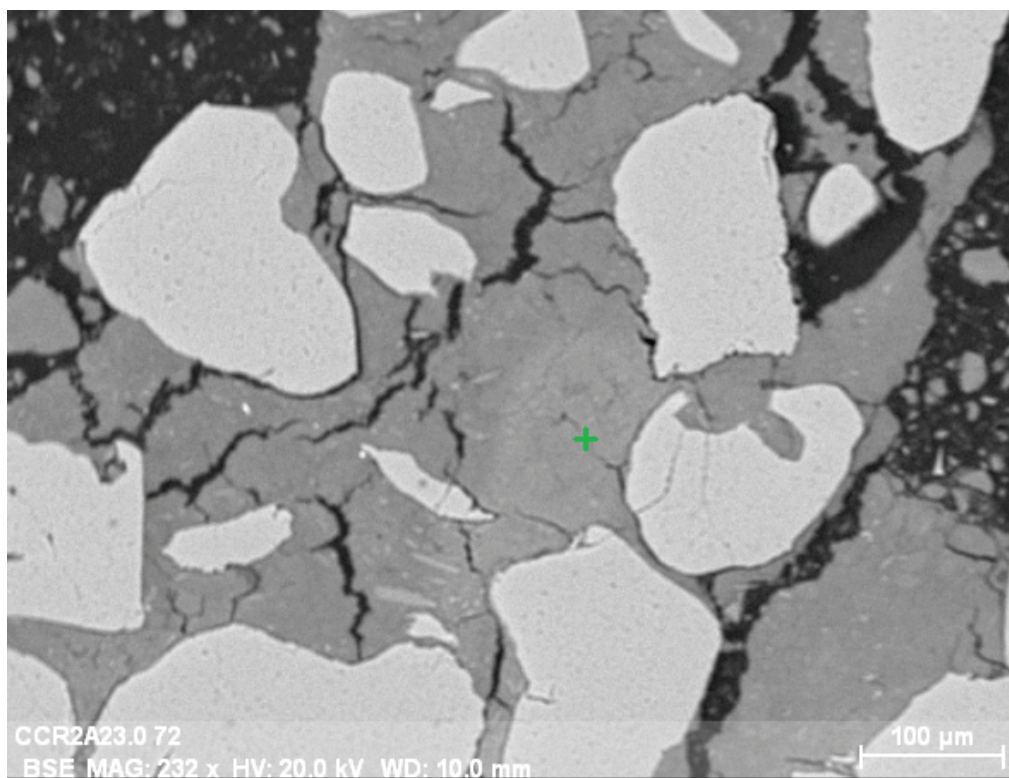



CCR2A 23.0-23.5: BSE image (top) and EDS spectrum (bottom) for wavellite and clay matrix; green crosshair on BSE image marks analysis location.

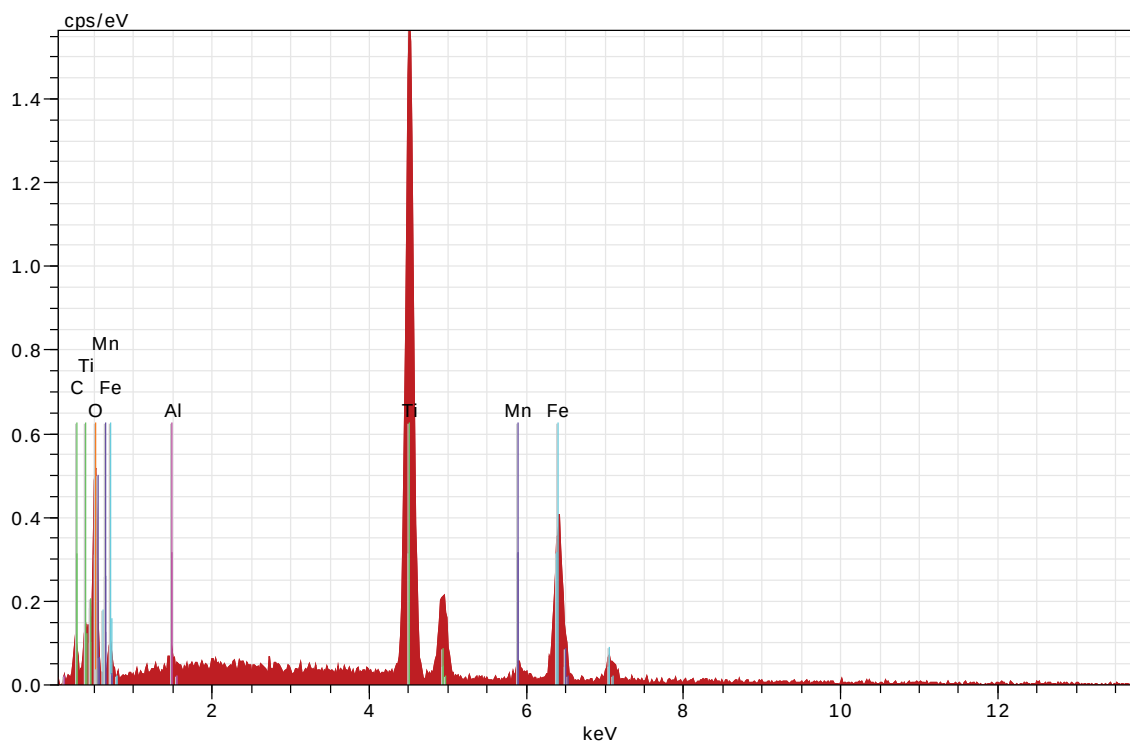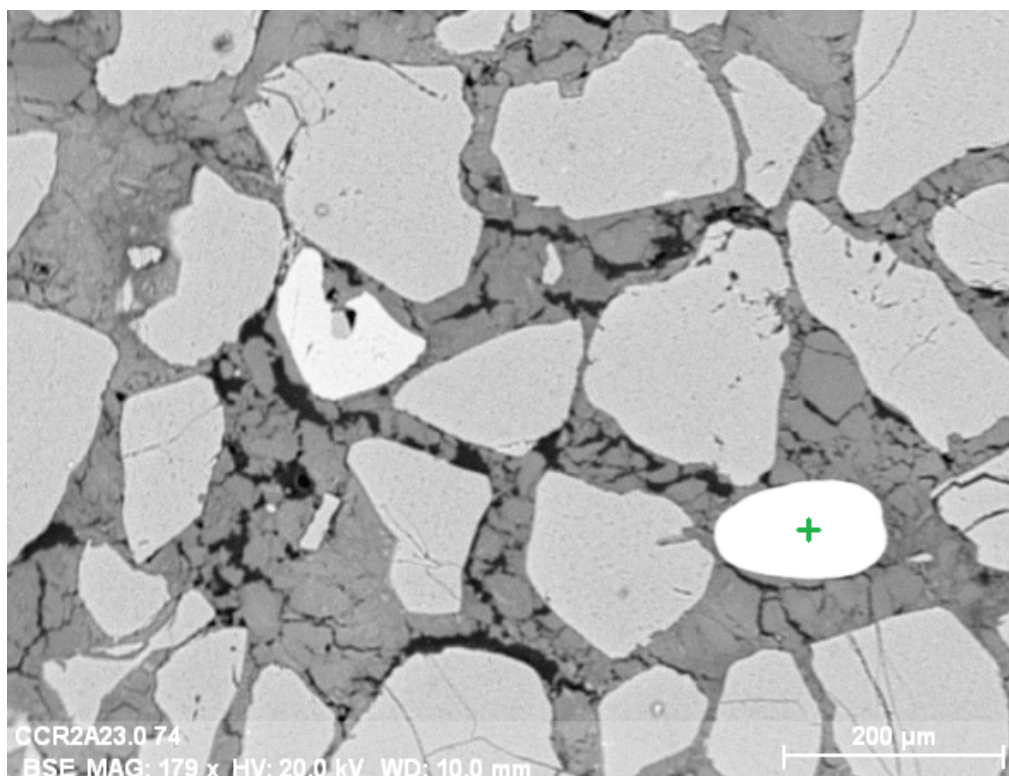



CCR2A 23.0-23.5: BSE image (top) and EDS spectrum (bottom) for ilmenite; green crosshair on BSE image marks analysis location.

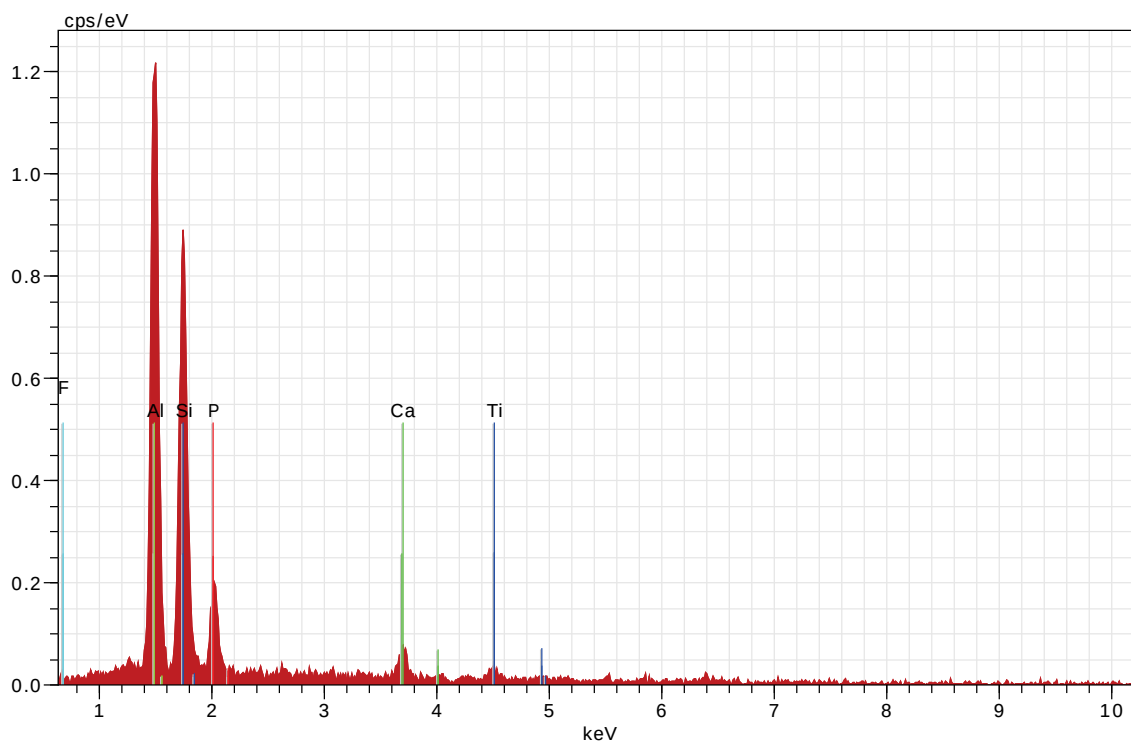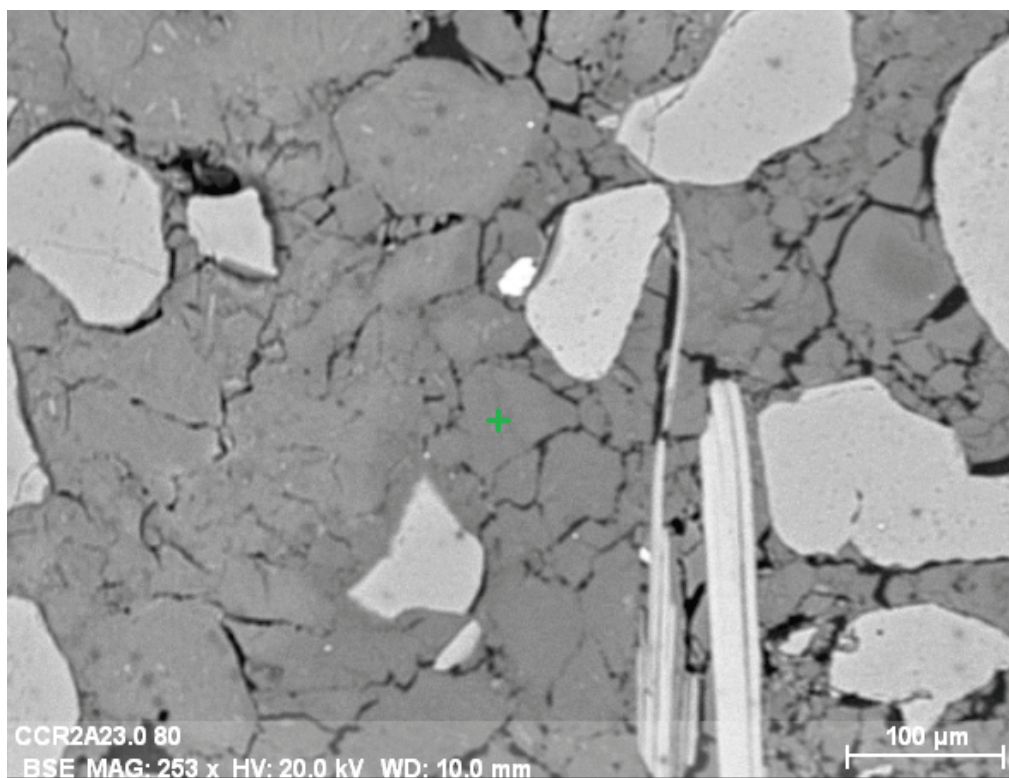



CCR2A 23.0-23.5: BSE image (top) and EDS spectrum (bottom) for wavelite and clay matrix; green crosshair on BSE image marks analysis location.

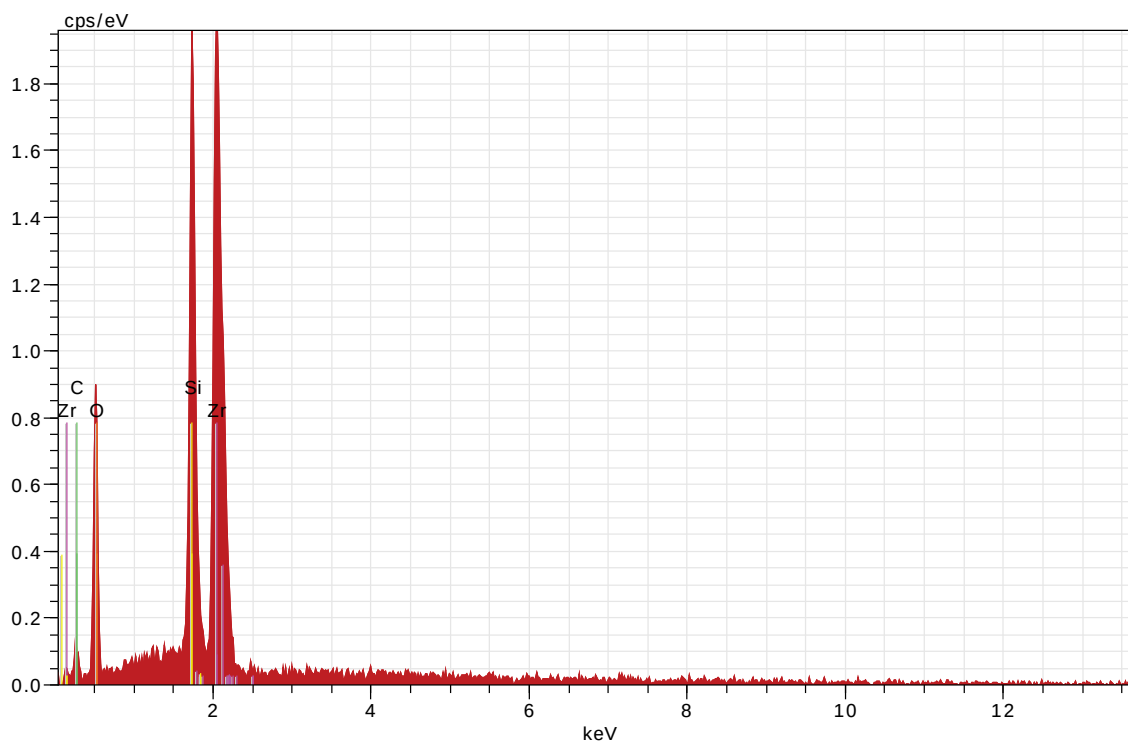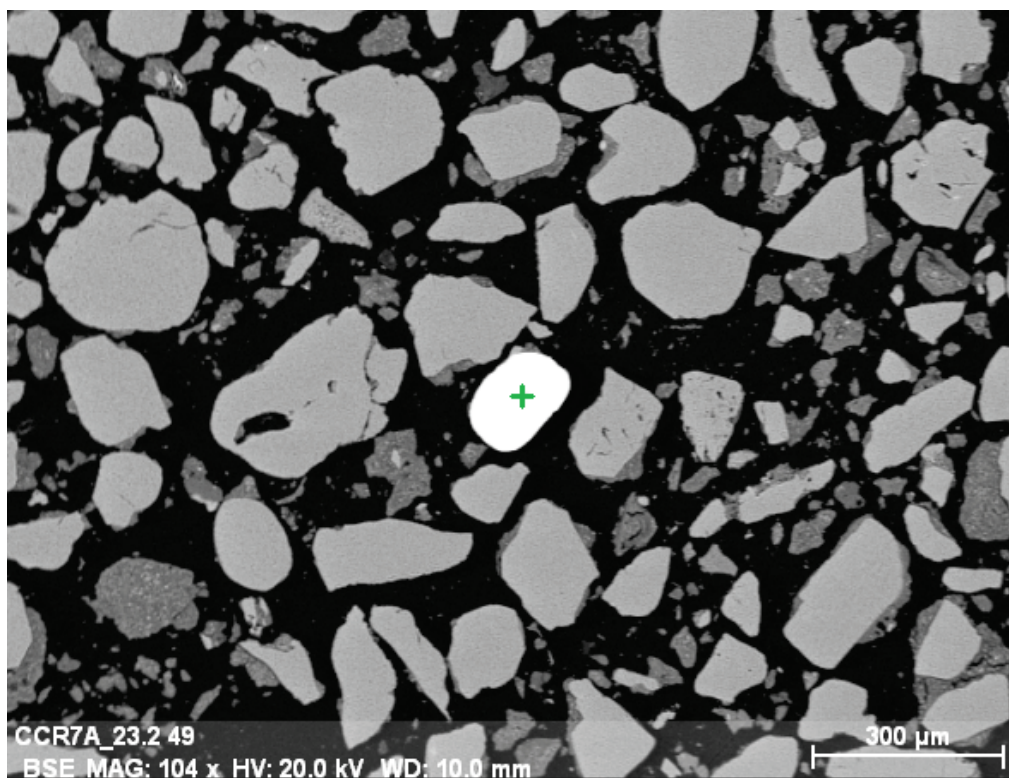



CCR7A 23.2-23.5: BSE image (top) and EDS spectrum (bottom) for zircon; green crosshair on BSE image marks analysis location.

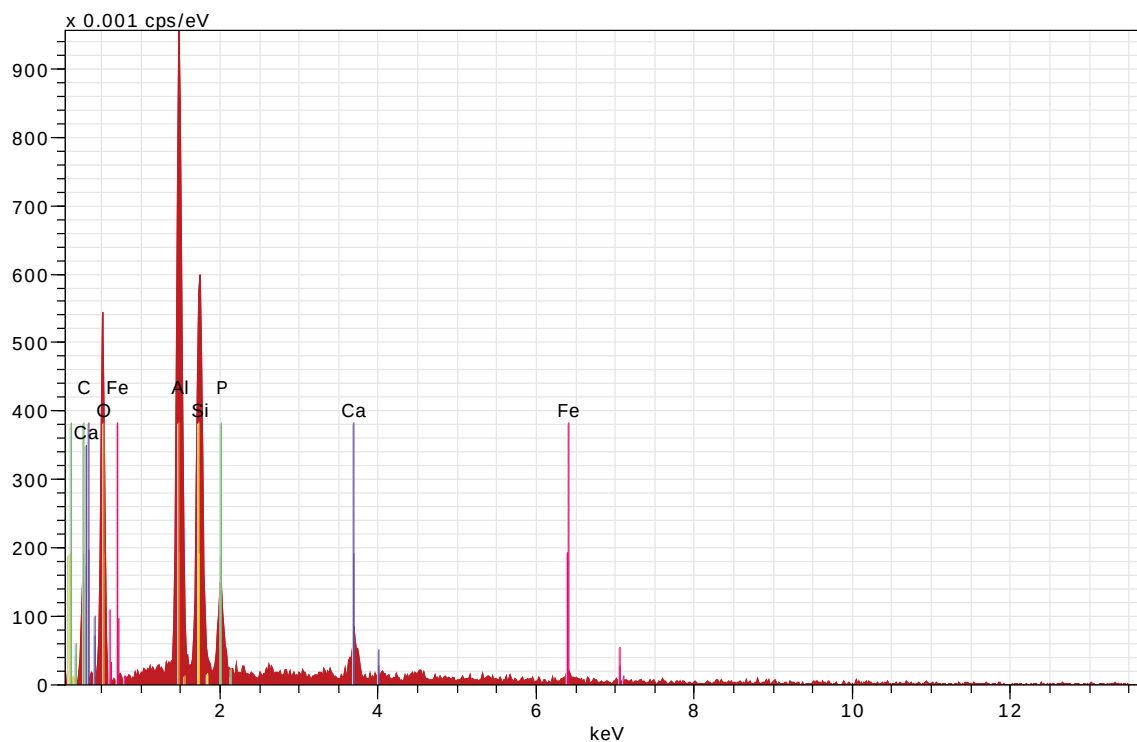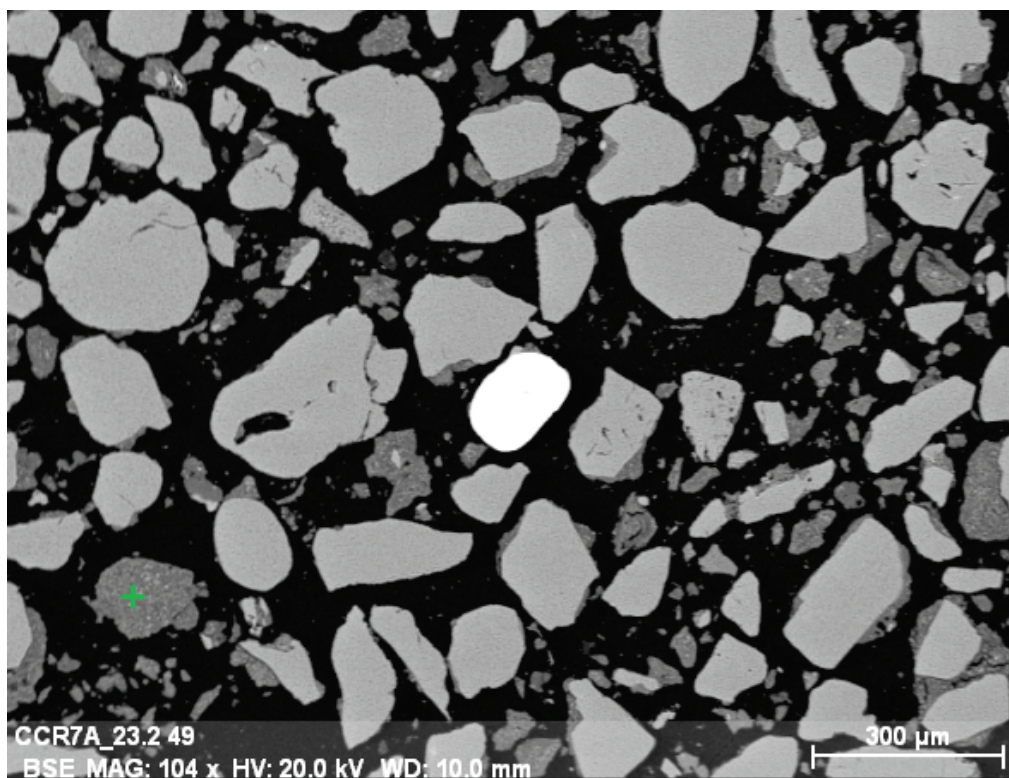



CCR7A 23.2-23.5: BSE image (top) and EDS spectrum (bottom) for Ca- and Al-phosphate matrix; green crosshair on BSE image marks analysis location.

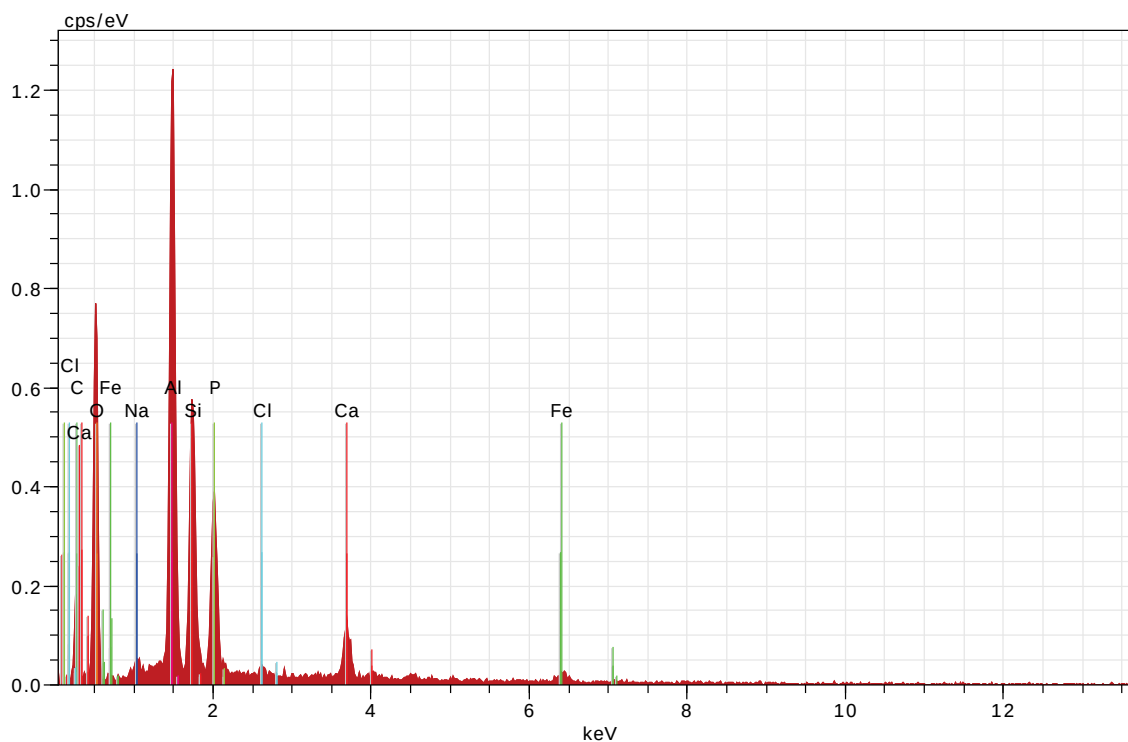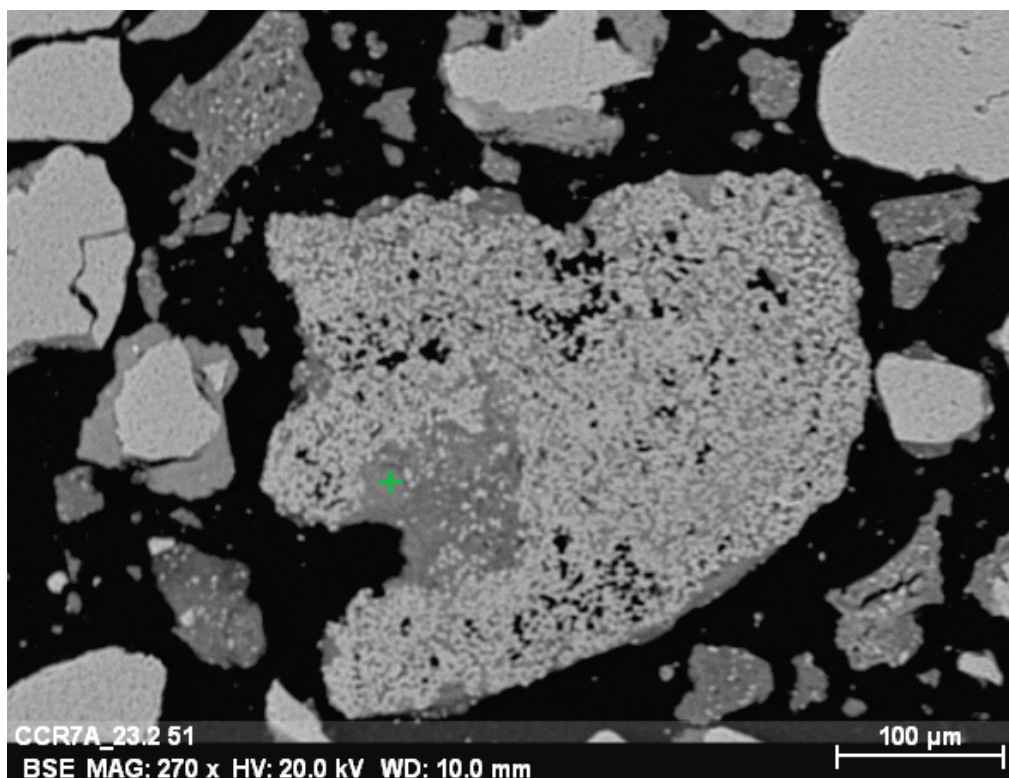



CCR7A 23.2-23.5: BSE image (top) and EDS spectrum (bottom) for wavellite and apatite matrix; green crosshair on BSE image marks analysis location.

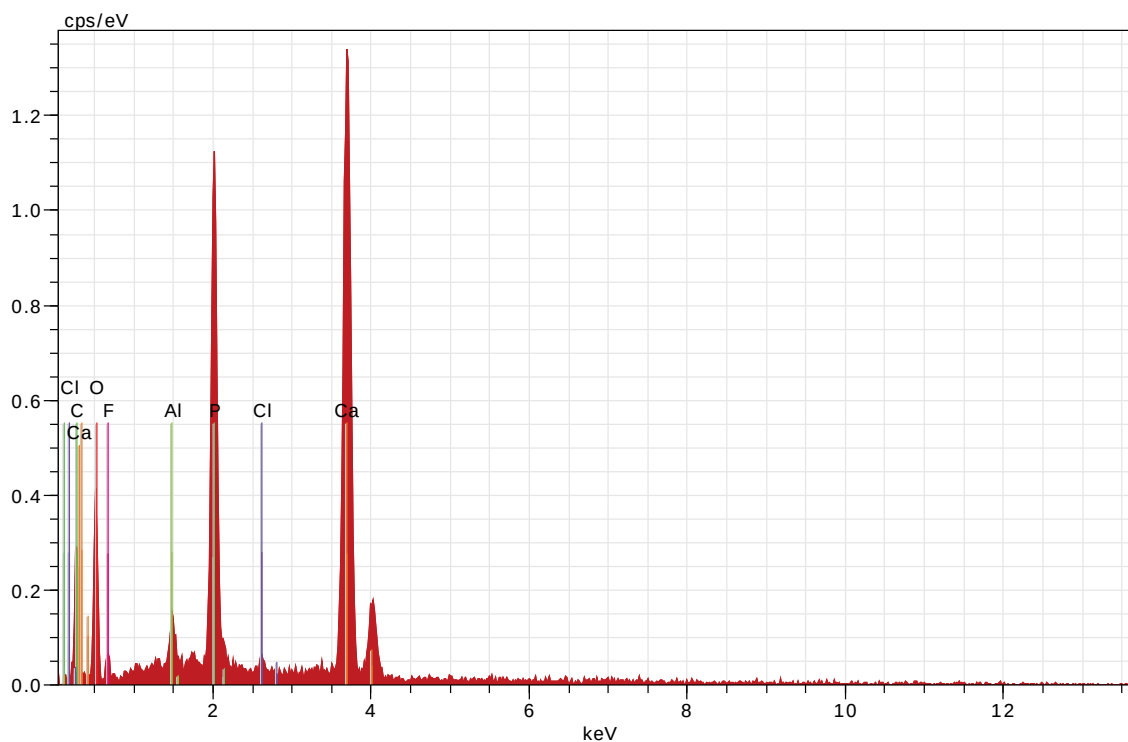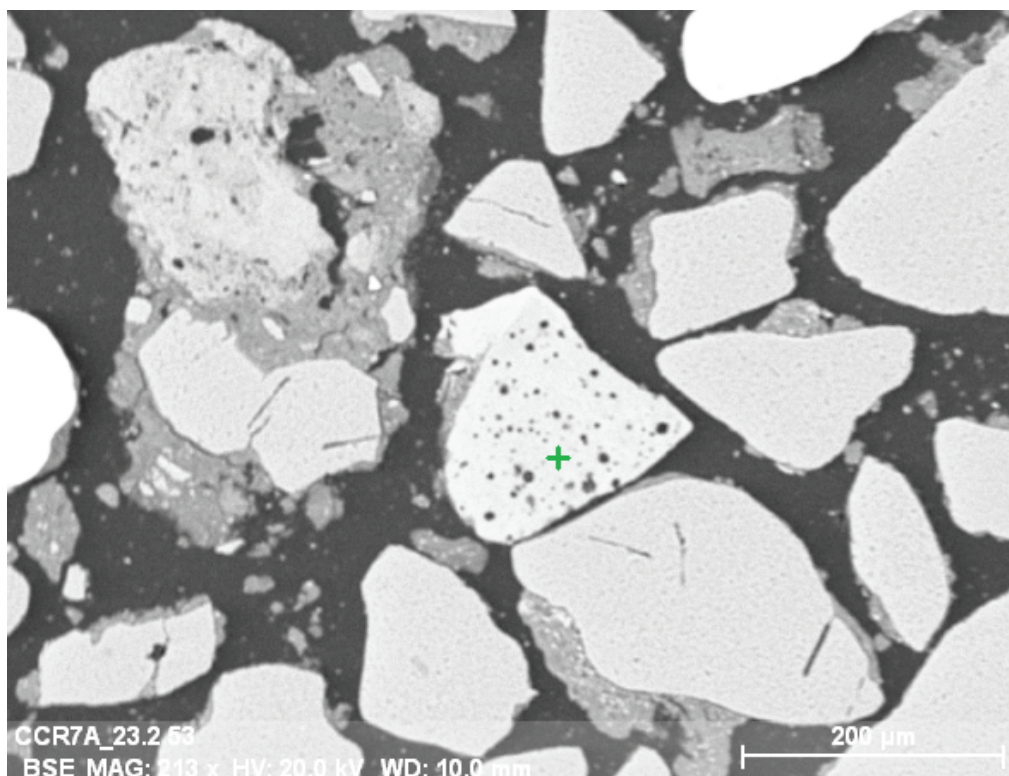



CCR7A 23.2-23.5: BSE image (top) and EDS spectrum (bottom) for apatite matrix; green crosshair on BSE image marks analysis location.

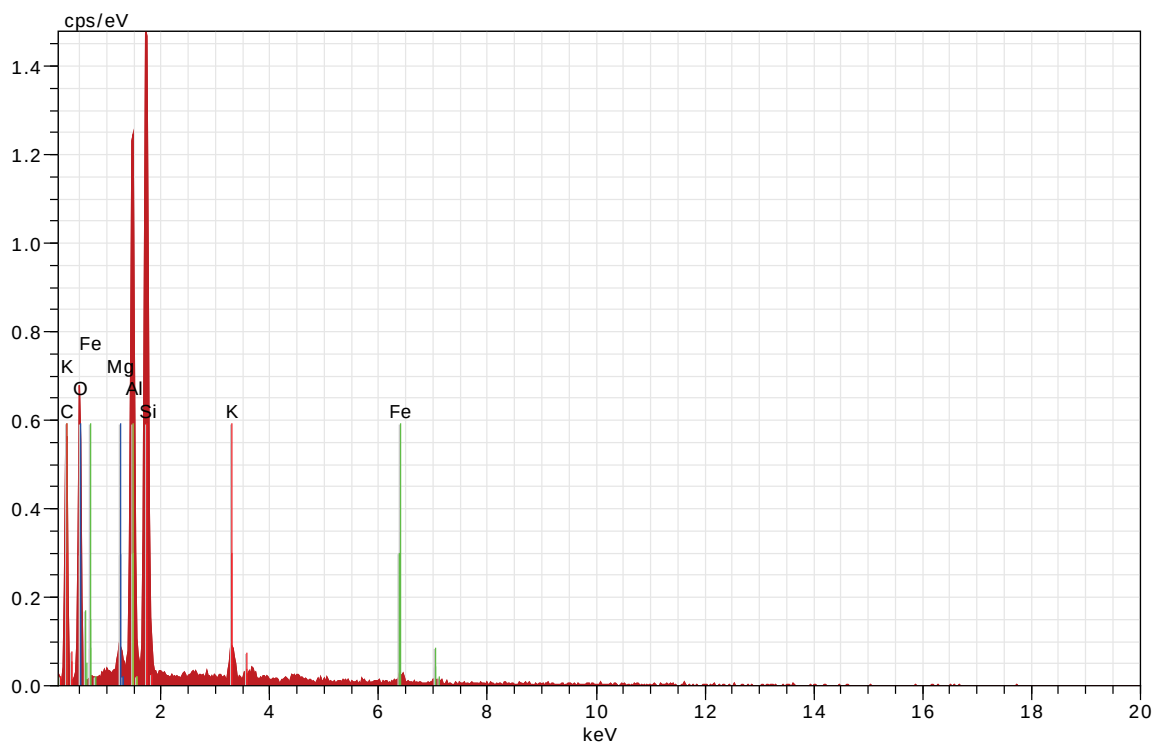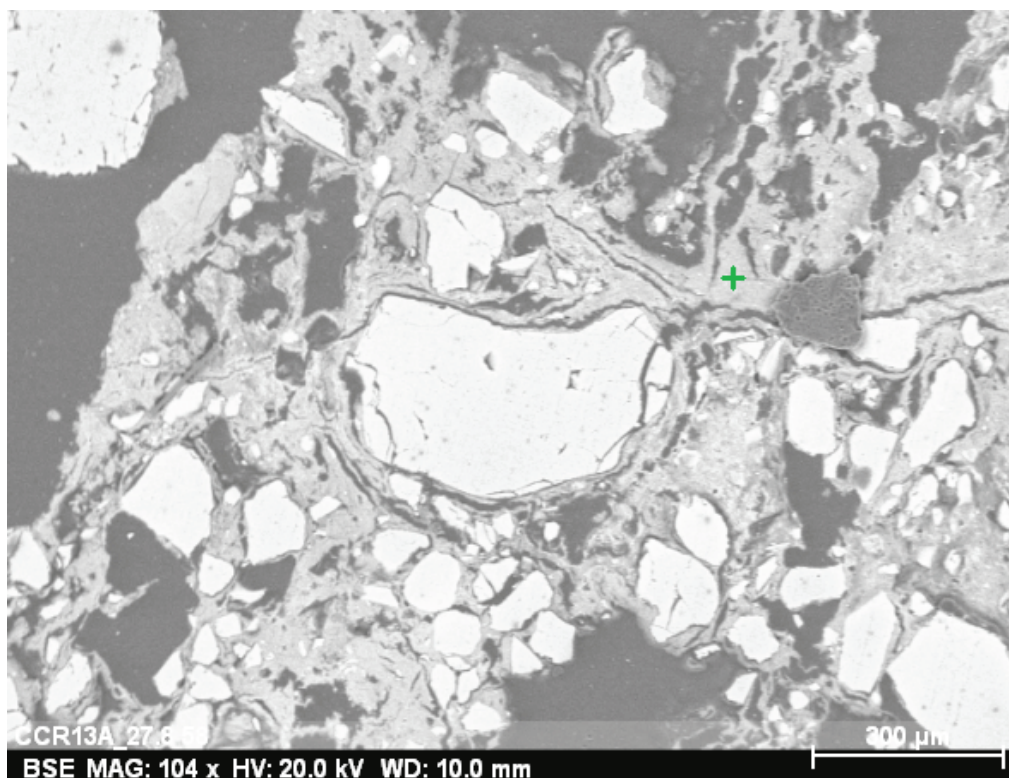


CCR13A 27.8-28.2: BSE image (top) and EDS spectrum (bottom) for kaolinite and muscovite matrix; green crosshair on BSE image marks analysis location.

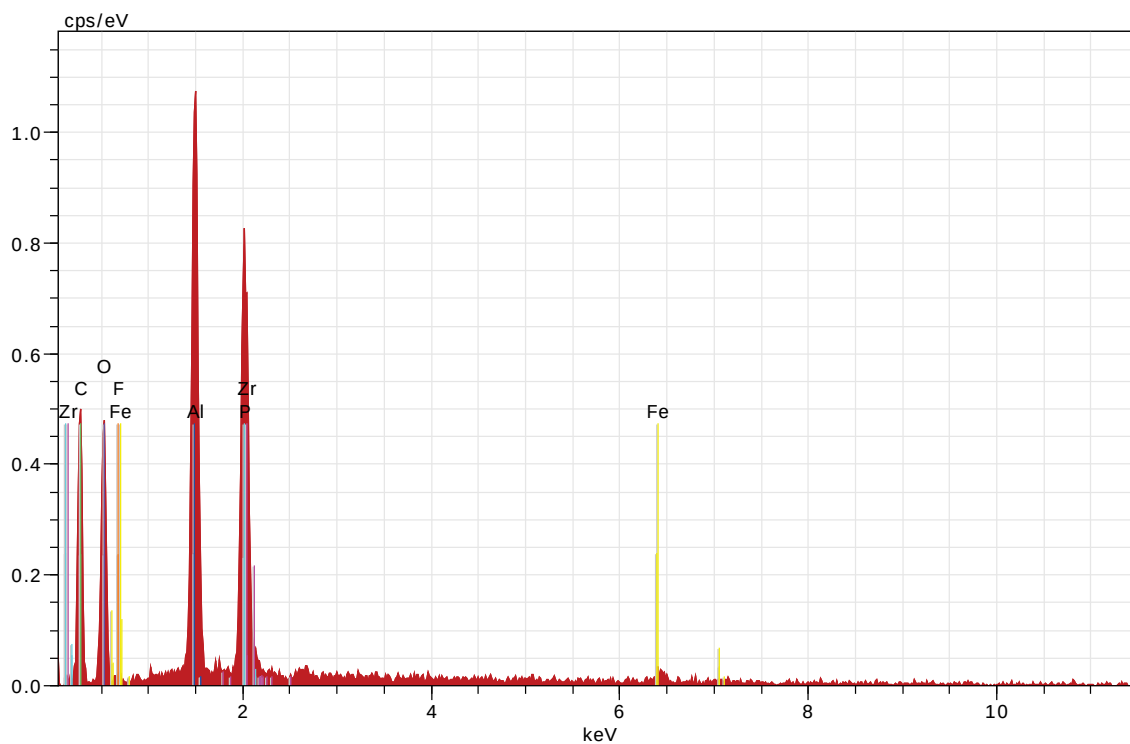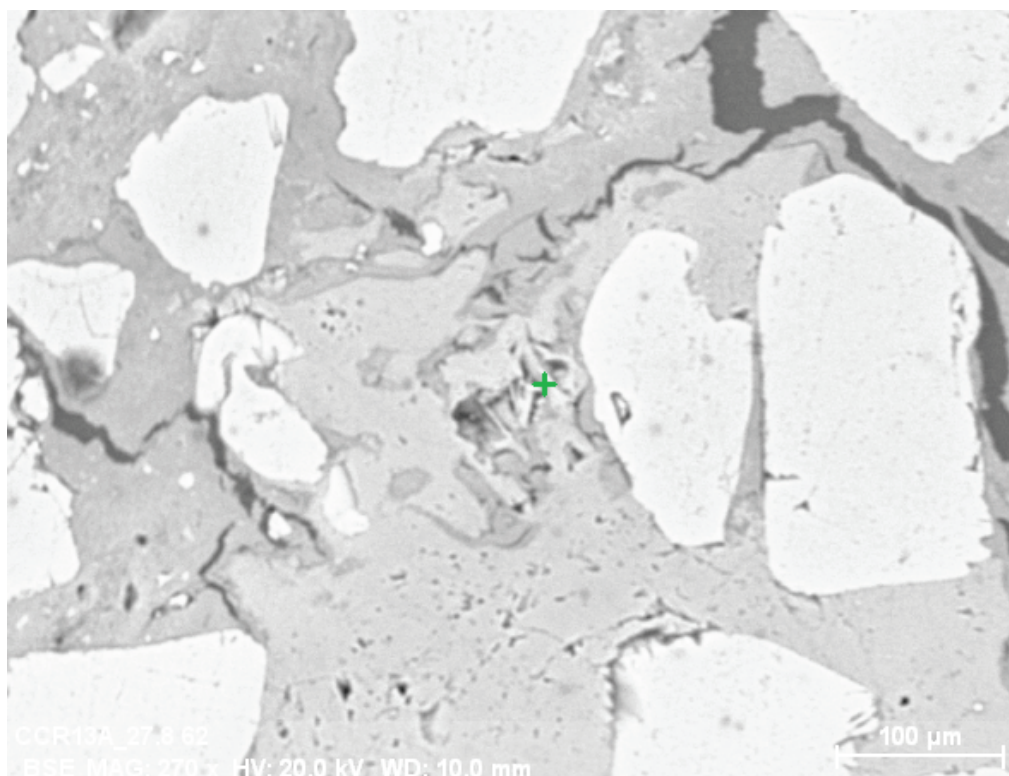



CCR13A 27.8-28.2: BSE image (top) and EDS spectrum (bottom) for wavellite; green crosshair on BSE image marks analysis location.

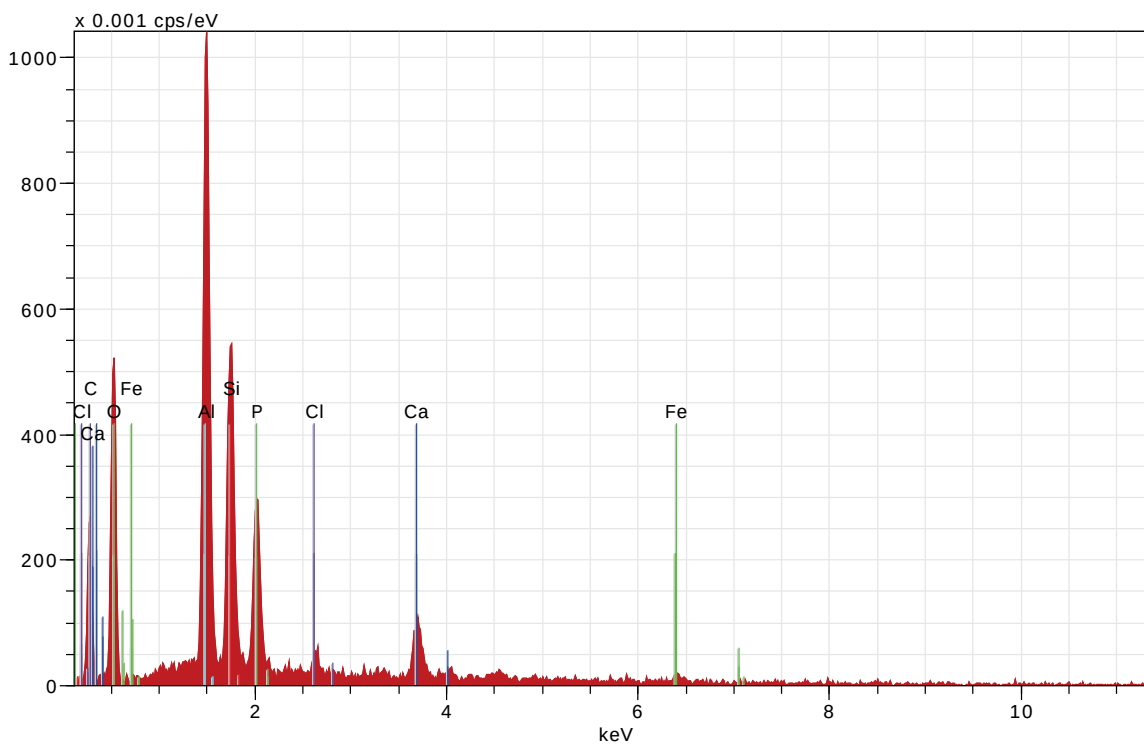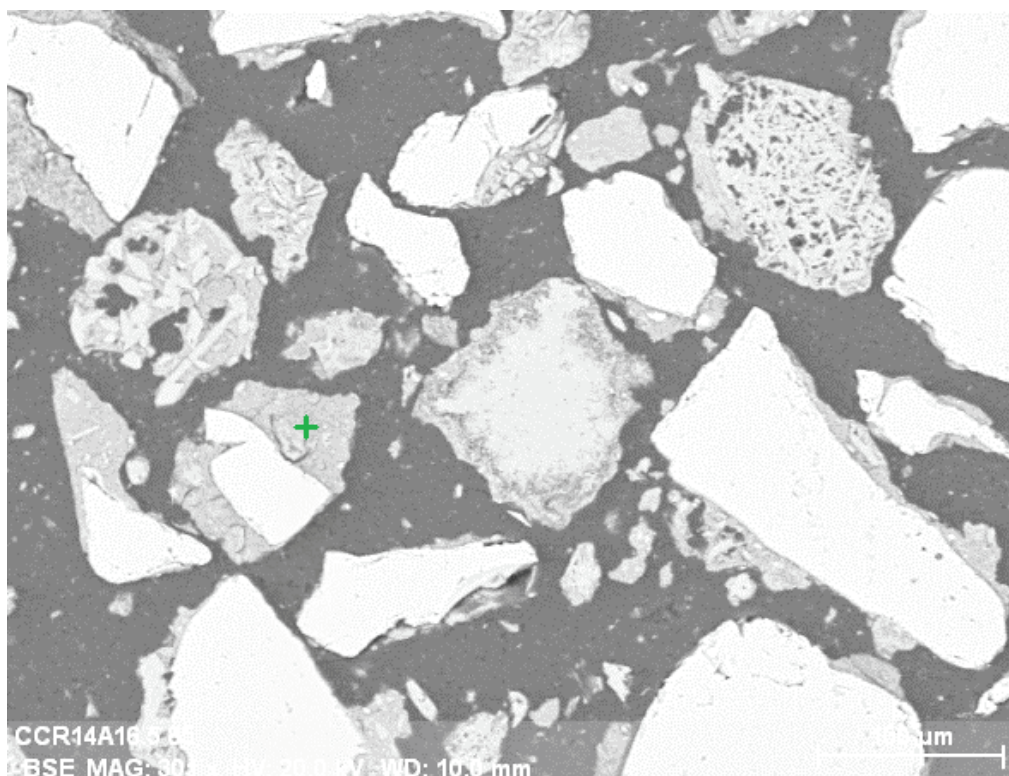



CCR14A 16.5-18.0: BSE image (top) and EDS spectrum (bottom) for apatite and wavellite matrix; green crosshair on BSE image marks analysis location.

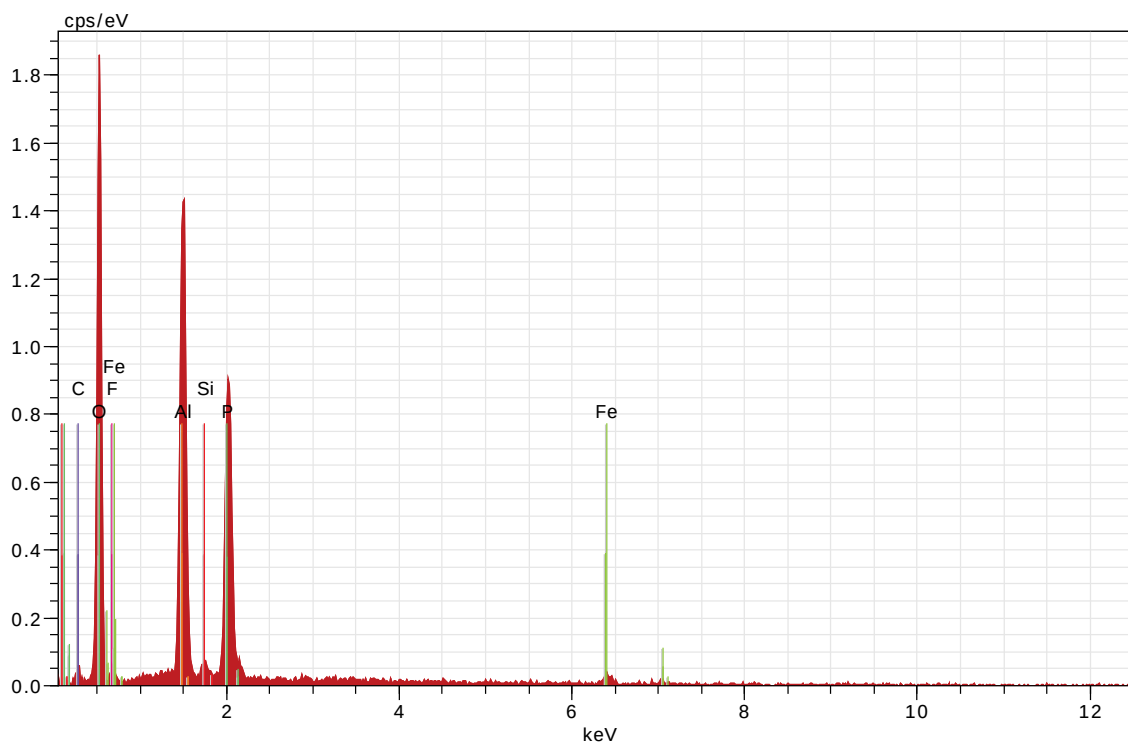



CCR14A 16.5-18.0: BSE image (top) and EDS spectrum (bottom) for wavellite; green crosshair on BSE image marks analysis location.

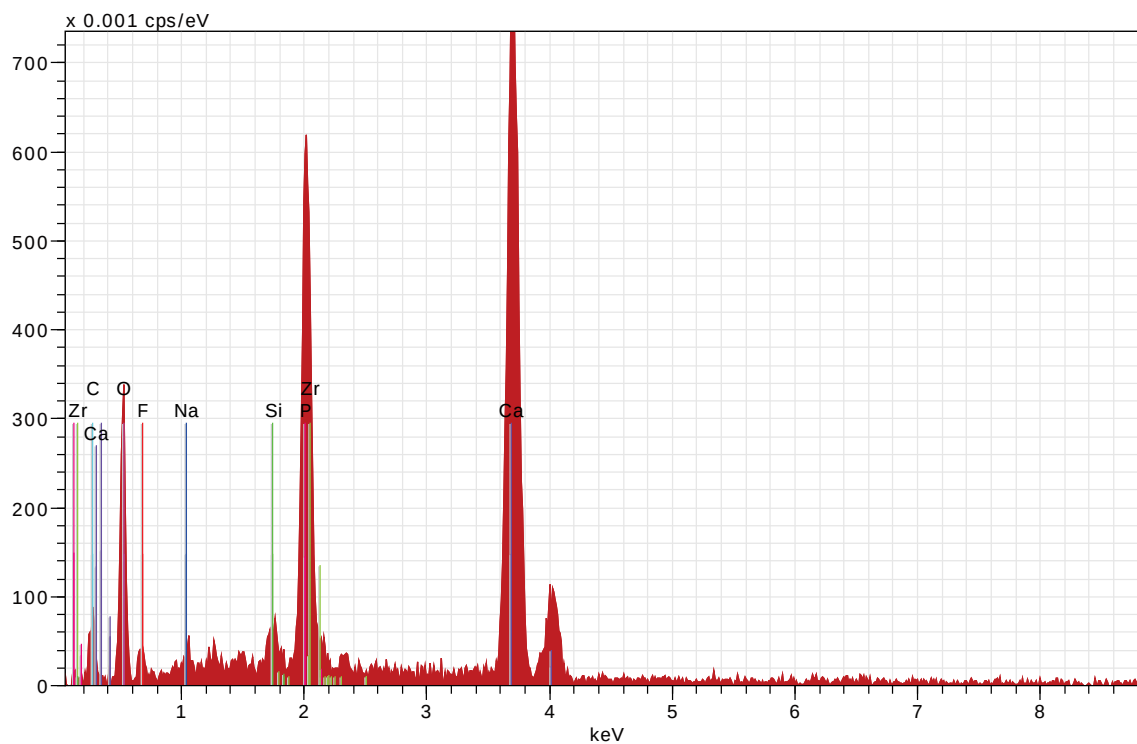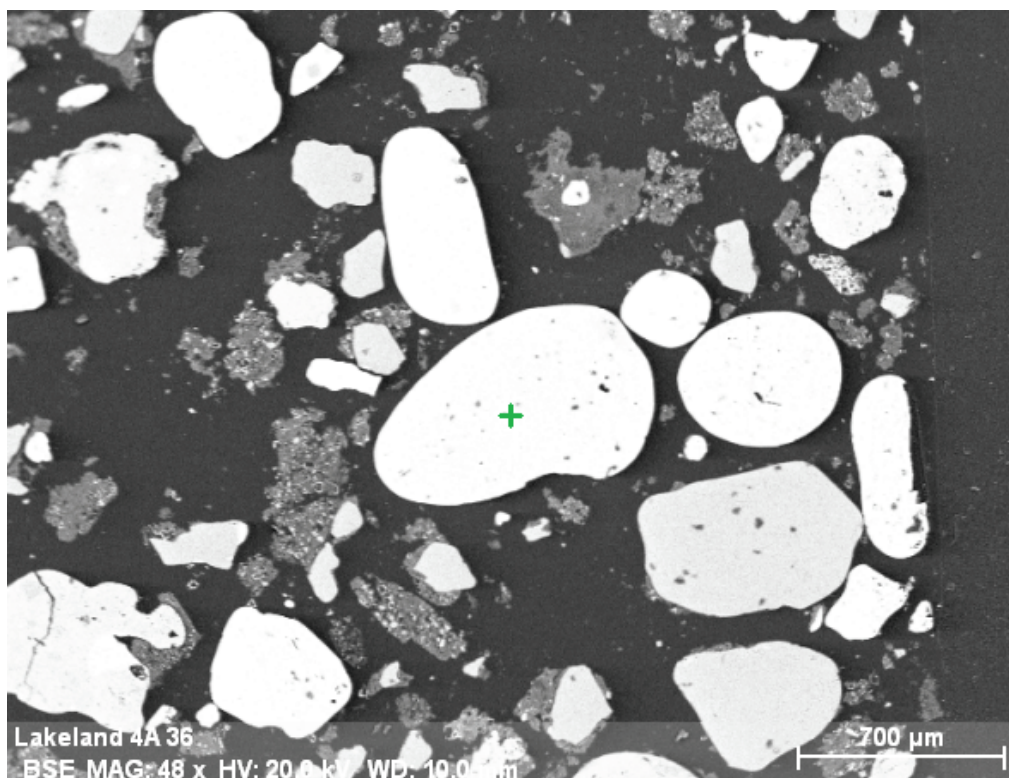

CCR14A 28.3-28.6: BSE image (top) and EDS spectrum (bottom) for collophane (apatite) "ball" with quartz inclusions (light gray); green crosshair on BSE image marks analysis location.

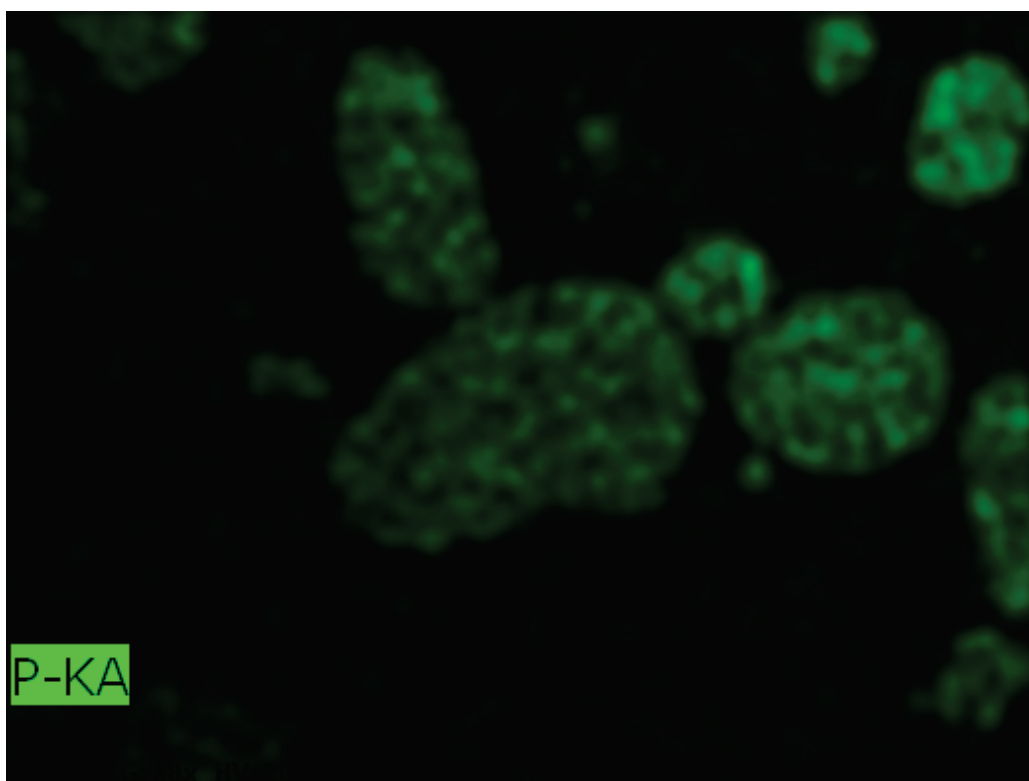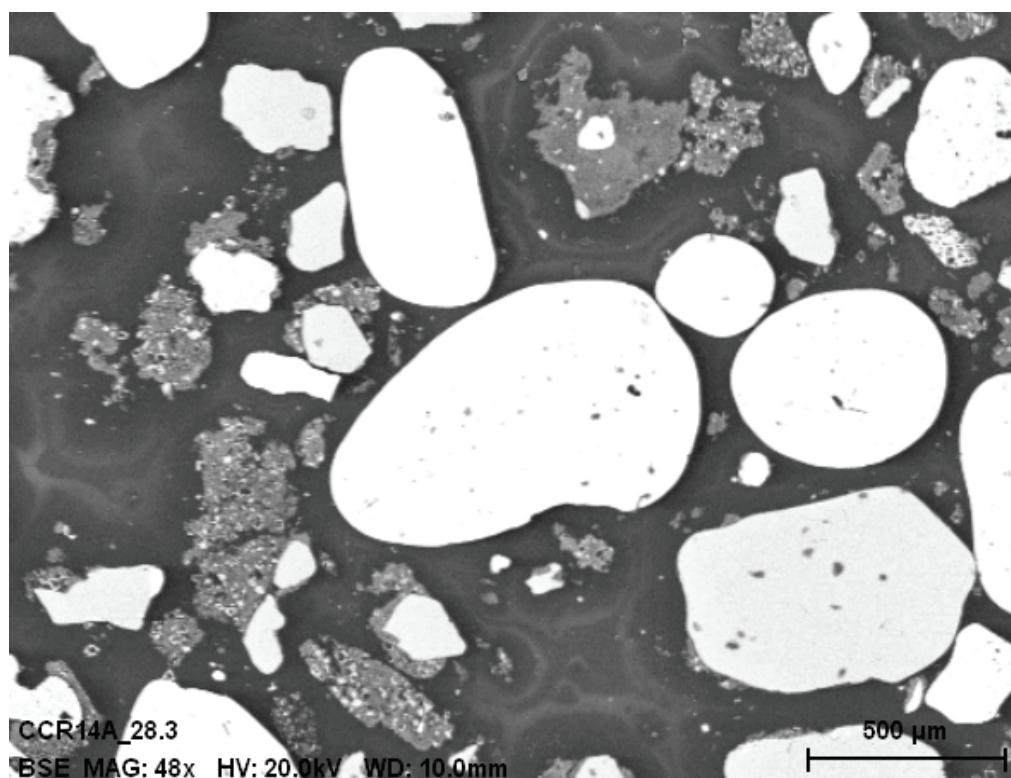

CCR7A 23.2-23.5: BSE image (top) and phosphorous map (bottom) of collophane apatite with quartz inclusions.

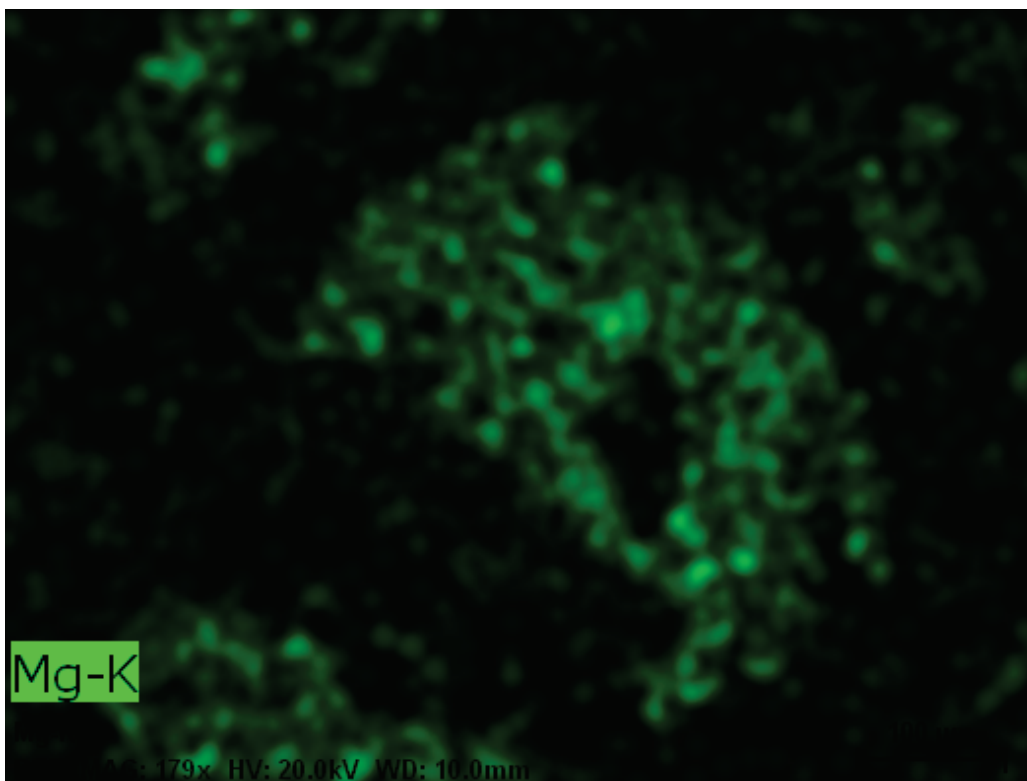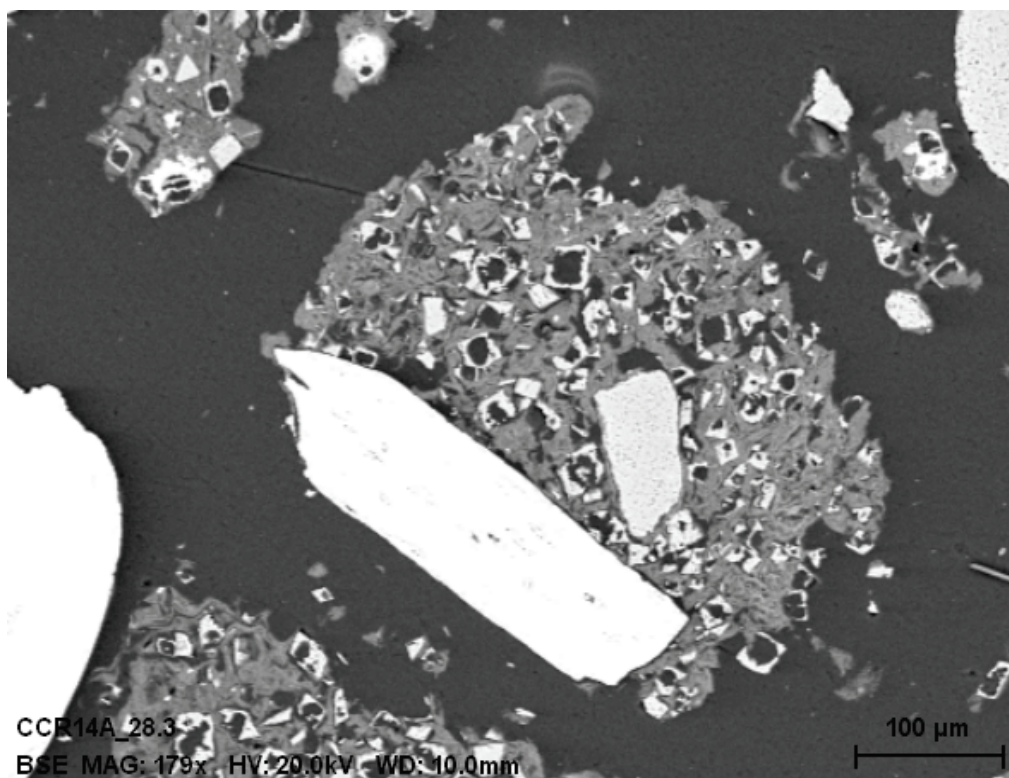

CCR7A 23.2-23.5: BSE image (top) of dolomite (high relief rhombohedral grains) in a clay matrix and magnesium map (bottom) of dolomite.



golder.com